

A.Dian Permana- 1_Baru2022.pdf

by

Submission date: 09-Dec-2022 08:03AM (UTC+0700)

Submission ID: 1975832591

File name: A.Dian Permana-1_Baru2022.pdf (1.4M)

Word count: 7390

Character count: 38367



Combinatorial Approach of Thermosensitive Hydrogels and Solid Microneedles to Improve Transdermal Delivery of Valsartan: an *In Vivo* Proof of Concept Study

Nirmayanti¹ · Julika Fajrika Nur¹ · Muh. Nur Amir¹ ·

Nirmayanti¹ · Alhidayah Alhidayah¹ · Jessica Theodor Usman¹ · Andi Dian Permana¹

2022

Received: 6 July 2022 / Accepted: 8 November 2022
© The Author(s), under exclusive license to American Association of Pharmaceutical Scientists

Abstract

Due to the limitations of oral administration of valsartan, in this study, we sustained transdermal delivery and improved bioavailability of valsartan, while the thermosensitive gel formula was made using Poloxamer 407 and P. Thermosensitive gels were evaluated for their gelation temperature, pH values, drug properties, *in vitro* drug release, *in vitro* permeation, and *ex vivo* permeation. Compared to oral administration, it was found that with and without microneedles, it was found that the increase of microneedles' needle length permeation was produced by 1.55 mm MINS with the use of microneedles could affect the permeation of valsartan. Specifically, the amount of drug permeated of 2.27 ± 0.001 mg. Importantly, the transdermal approach could significantly improve the bioavailability of valsartan in *in vivo* studies showed the improvement of the bioavailability of valsartan compared to oral administration, showing the effectiveness of this combination approach.


Keywords solid microneedle · transdermal thermosensitive gel · valsartan

Introduction

Hypertension is a disease that is defined as persistently elevated arterial blood pressure (BP) ≥ 140 mmHg and/or diastolic BP ≥ 90 mmHg. Hypertension is one of the primary risk factors for cardiovascular disease [1]. Management of hypertension has become an international health priority [2]. In 2021, as much as approximately 46% of the global adult population was reported to have hypertension [3]. Globally, the prevalence of hypertension increases in exposure to lifestyle risk factors [4]. Hypertension, therewith pre-hypertension, and other hazariously high blood pressure, is liable for several health issues [5]. Valsartan is a selective angiotensin receptor blocker that is used orally. Oral bioavailability of VALS is 10–35% and shows a first-pass effect. VALS can be diminished by food intake, which the pharmacological effects [6]. Accordingly, to develop an alternative delivery route for VALS has been previously reported that transdermal drug delivery could be potentially utilized to overcome the limitations of the oral route [7–9]. Regarding its properties, VALS has a low molecular weight of 435.5 Da, melting point of 116–117°C, pKa of 4.78, mean biological half-life of 7.5 h and log partition coefficient of 4.5. Additionally, VALS is a candidate that is promising for transdermal drug delivery, and there are no reports of skin irritation caused by VALS [1, 5].

✉ Andi Dian Permana
andi.dian.permana@farmasi.unhas.ac.id

¹ Faculty of Pharmacy, Hasanuddin University, Makassar 90245, Indonesia

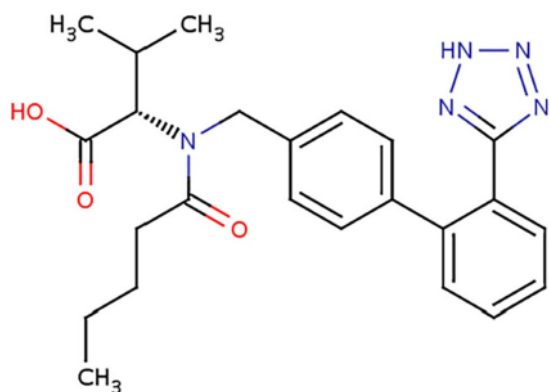

57
Fig. 1 Chemical structure of valsartan

23
The major issue in the transdermal delivery system is the presence of *stratum corneum* (SC), the lipophilic layer of skin. It has been reported that VALS has a log partition coefficient of 5.8 [16], showing its lipophilicity which could decrease its ability to reach 45 dermal circulation for further systemic absorption [17]. One of the strategies adopted to bypass the SC barrier is using solid microneedles (MNs) as physical penetration enhancers attributed to their painless properties and insignificant infection risk at the application site [18]. Among several types of solid MNs, Dermalrollers® has been widely used to improve transdermal delivery of numerous active pharmaceutical ingredients [18–20]. MNs as a pretreatment could create micropores in 56 skin and close by ~48 h and would need to be repeated. Therefore, a suitable delivery system is required in order to reduce the application frequency for patient compliance. One of the transdermal delivery systems is thermosensitive gel, the formulation that changes from liquid to gel under an increase in temperature. This approach could potentially be used to reduce the frequency of MN application because it would quickly enter into micropores when applied and change into gel slowly, which would create *in situ* gel depot in the micropores that would continue to deliver drug even if the micropores close [21]

The most frequently used thermosensitive polymer in gel preparations is Poloxamer 407 [22]. However, a Poloxamer 407 solution with more than 20% concentration would form a hydrogel at ambient temperature and reduce the gelation temperature of the preparation to <25°C so that it can form a gel at ambient temperature [23, 24]. Several studies have shown the limitation of the single use of Poloxamer 407 [25–29], showing the necessity to combine this thermosensitive polymer with another polymer. To overcome this, the addition of another type of poloxamer, Poloxamer 188 has been previously used to modify the gelation temperature of the preparation. It was reported that combining the two

1
Table 1 Design of VALS Thermosensitive-Gel Formulation

Ingredients % (w/w)	F1	F2	F3	F4	F5
Valsartan	1	1	1	1	1
Ethanol 95%	10	10	10	10	10
Poloxamer 407	17	17	17	18	16
30 Poloxamer 188	1	3	5	2	4
Distilled water	Ad 100	Ad 100	Ad 100	Ad 100	Ad 100

types of poloxamer could potentially m 16 late the gelation temperature of the preparations [30]. To the best of our knowledge, there have been no studies developing VALS in thermosensitive hydrogels for transdermal delivery and its combination with MN delivery system. In this study, we developed thermosensitive hydrogel containing VALS and evaluated their physical and thermosensitive properties. The selected formulation was then combined with solid MNs with different lengths and were evaluated for their permeation profile using a rat skin model. Finally, the bioavailability of VALS using this combination approach was evaluated and compared to oral administration.

55 Materials and Methods

Materials

Valsartan (Purity: >98.0%) was obtained from Tokyo Chemical Industry (Tokyo, Japan). Poloxamers 407 and 188 were kindly provided by BASF Indonesia, Jakarta). Solid microneedles (Dermalrollers®) were purchased 36 from SQY® (Guangdong, China). Other compounds used in this study were of analytical grade.

Design of Formulation

52
The poloxamer solution was prepared using the cold method by slowly adding the poloxamer combination that was weighed accurately into cold distilled water (4°C). Table 1 shows the composition of the formulation. The solution was further stirred constantly to form a poloxamer solution. The poloxamer solution was then stored in the refrigerator overnight until a clear solution was formed. Following this, VALS was dissolved in ethanol 95% and mixed in an already-prepared poloxamer solution at 4°C [15, 17].

Evaluation of Physical Properties

Gelation Temperature

Gelation temperature 8 was determined by placing 2 mL of each formula into a test tube [24, 31]. The test tube was

put into a water bath at 20°C. Furthermore, the test tube was rotated at 90° every 1°C increase in temperature until the temperature reached 65°C. The gelation temperature recorded was the temperature at which the gel did not move when the test tube was rotated. The test was run in triplicate.

pH Determination

The pH of the VALS thermosensitive gel was measured using a digital pH meter, and the test was performed in triplicate [32].

Drug Content

VALS thermosensitive gel (0.1 mL), equal to 10 mg of VALS, was pipetted out. It was diluted with ethanol, and the absorbance of the mixture was measured at 230.2 nm with a UV-Vis spectrophotometer (Dynamica, HALO XB-10). The drug content was calculated against the absorbance of the control VALS solution at 230.2 nm. [33]. The concentration of VALS was determined by plotting the absorbance values to the calibration curve prepared from the standard solution of VALS in the concentration range of 0.5–32 µg/mL.

Spreadability

The spreadability of VALS thermosensitive gel was determined at gelling state by placing an amount of 0.5 g gel in a 2-cm-diameter circle premarked on a glass piece over a second glass plate. A weight of 500 g was rested on the top of the glass piece for 5 min. The diameter increased appropriately to the preparation's spreading was recorded in triplicate [15].

Viscosity and Rheological Properties

The viscosity of VALS thermosensitive gel was determined using a viscometer (Brookfield, USA) at various temperatures (4 ± 0.1°C, 25 ± 0.1°C, and 35 ± 0.1°C). The study was performed by placing each formulation on the lower plate of the apparatus, and the viscometer was run using spindle number 63 at 60 rpm. The rheological behavior was determined by calculated viscosity against the various velocities (rpm) of VALS thermosensitive gel [14, 15].

In Vitro Release Study

The *in vitro* release of VALS from thermosensitive gels was measured by dissolution model without membrane, as previously described [17], with minor modifications. The amount of 5 g VALS thermosensitive gel was taken, put in a glass vial, and equilibrated to the gelation temperature at 37 ± 1°C. Following this, 2.5 mL of PBS was poured smoothly on the

upper gels without interfering with the gel surface. Then, 1 mL was collected at regular time intervals (0.5 h, 1 h, 2 h, 3 h, 4 h, 5 h, 6 h, 7 h, 8 h, and 24 h) for release quantification. For maintaining the sink condition, fresh PBS medium (1 mL) was added to the glass vials each time. The absorbance of samples was measured using a UV-Vis spectrophotometer (Dynamica, HALO XB-10, UK) at 231.4 nm, and the amount of VALS released was calculated. The release study of free VALS was also evaluated as a control. The concentration of VALS was determined by plotting the absorbance values to the calibration curve prepared from the standard solution of VALS in the concentration range of 0.5–32 µg/mL.

In Vitro Permeation Study

Franz diffusion cell was used to assess the *in vitro* permeation of VALS. The cellophane membrane was used as a membrane for the study. The receptor compartment was filled with PBS (pH 7.4) and magnetic bar was placed inside for stirring. The membrane was placed in between the receptor and donor compartment. The cell was held at 37 ± 1°C and agitated by a magnetic stirrer at 100 rpm. An amount of 1-g gel preparation was placed in the donor compartment. About 1 mL sample was taken at regular time intervals. After each time, an equal volume of fresh PBS (pH 7.4) heated to 37 ± 1°C was added to the receptor compartment to keep the sink conditions. The sample absorbance was measured using a UV-Vis spectrophotometer (Dynamica, HALO XB-10, UK) at 231.4 nm [18, 33]. The *in vitro* permeation study of free VALS was also evaluated as a control. The concentration of VALS permeating was calculated by plotting the absorbance values to the calibration curve prepared from the standard solution of VALS in the concentration range of 0.5–32 µg/mL.

Ex Vivo Permeation Study

Similarly, the Franz diffusion cell was also used to investigate the *ex vivo* permeation study [20, 35, 36]. The abdominal skin of female Sprague-Dawley rats was shaved and used as a biological membrane for the study. Initially, the hair of the rats was shaved, and the hair removal cream was applied to the shaved area. The rats were euthanized using ether and were sacrificed. Following this, the skins were collected. The skin was washed with distilled water and equilibrated in PBS before the experiment. The *ex vivo* experiment was approved by the Health Ethical Committee at the Faculty of Medicine, Hasanudin University, Indonesia. The receptor compartment was filled with 10 mL of PBS (pH 7.4) and magnetic bead for stirring. In an attempt to evaluate the effect of solid MN treatment on the penetration through the skin, the skin sample was pretreated with a DermaRoller®

in various lengths (0.5 mm, 1 mm, and 1.5 mm) before it was placed onto the donor compartment. The skin (surface area of 1.77 cm²) was placed between the receptor and the donor compartment. The cell was maintained at 37 ± 1 °C and agitated by a magnetic stirrer at 200 rpm. An amount of 1 g of gel was placed in the donor compartment. About 1 mL sample was withdrawn at regular intervals (0.5 h, 1 h, 2 h, 3 h, 4 h, 5 h, 7 h, 8 h, and 24 h) and replaced by 1 mL fresh PBS (pH 7.4) heated to 37 ± 1 °C to keep the sink conditions. The sample absorbance was assessed using a UV-Vis spectrophotometer (Dynamica, HALO XB-10) at 231.4 nm. The concentration of VALS was determined by plotting the absorbance values to the calibration curve prepared from the standard solution of VALS in the concentration range of 0.5–32 µg/mL.

In Vivo Study

The *in vivo* investigation was conducted to investigate the penetrability of VALS from thermosensitive hydrogels after the application of solid MNs. The study was performed on healthy male Wistar rats weighing 213.08 ± 14.17 g. All the animals were acclimatized for 1 week in the conditions of the laboratory. The *in vivo* experiment was approved by the Health Ethical Committee at the Faculty of Medicine, Hasanuddin University, Indonesia. There were three groups in this study: the first group received thermosensitive gels containing VALS after the administration of solid MNs; the second group received thermosensitive gels containing VALS without the administration of solid MNs; and the third group received oral administration of VALS. All groups received VALS with a dose of 10 mg/kg of body weight. At predetermined interval times (1 h, 2 h, 3 h, 4 h, 6 h, 8 h, 12 h, and 24 h), the blood was collected, and the plasma samples were separated for further analysis.

Sample Preparation, Extraction and Analysis

VALS was extracted from plasma using a simple extraction method using methanol. Briefly, 750 µL of methanol was used to extract VALS from 100 µL of plasma. The extraction was performed by mixing methanol and plasma samples using a vortex for 20 min. Following this, the samples were centrifuged at 12,000 rpm for 15 min, and the supernatant was collected and dried for 3 h, obtaining dry residue. The quantification of VALS extracted from plasma samples was performed using bromophenol blue method as reported previously [37], with slight modifications. The residue was reconstituted using 450 µL methanol and mixed with 50 µL bromophenol blue solution in methanol (1.3 × 10⁻³ M). The concentration of VALS was determined by measuring the absorbance of the solution at 424 nm using a UV-Vis spectrophotometer (Shimadzu Co., Ltd., Tokyo, Japan). The

concentration of VALS in plasma samples was determined by plotting the absorbance values to the calibration curve prepared from the standard solution of VALS in plasma in the concentration range of 1–64 µg/mL. Afterwards, the curves consisting of the VALS concentration and time of application were prepared. The pharmacokinetic profiles were calculated using PK Solver [38].

Statistical Analysis

All the data were presented as means ± standard deviation (SD) of the mean. SD of the results was measured using Microsoft® Excel® 2010 (Microsoft Corporation, Redmond, USA). The statistical analysis was performed using GraphPad Prism® version 5 (GraphPad Software, San Diego, California, USA). The *p* < 0.05 indicated a significant difference in all cases.

Result and Discussion

VALS Thermosensitive Gel Formulation


In this study, a thermosensitive transdermal gel formulation of VALS was carried out, and several physical characteristics, release profile, and drug permeation in rat skin were performed in an *ex vivo* study. VALS thermosensitive gel was made in five different formulas containing a combination of Poloxamer 407 and Poloxamer 188 as thermosensitive polymers. The representative image of the resulting preparation is depicted in Fig. 2. The results of organoleptic observations showed that all the thermosensitive gel preparations were slightly clear with a smell of alcohol. This was in accordance with previous research, showing that gels should appear transparent [39]. In addition, the resulting preparation of thermosensitive gel was in liquid form at room temperature and gel form when the gelation temperature was reached.

Evaluation of Physical Properties

Effect of Poloxamer Concentration on Gelation Temperature

Gelation temperature testing was carried out to obtain the temperature required by VALS thermosensitive transdermal gel to transform into gel form. The thermosensitive transdermal gel should have a gelation temperature similar to the physiological skin temperature of 32 ± 1 °C. Hence, when the transdermal gel is applied, the preparation would become gel on the skin [40]. The gelation temperatures of VALS thermosensitive transdermal gel are exhibited in Fig. 2. The test results show that the gelation temperatures of all formulations obtained were in the range of 27.67–40.67 °C. The

Fig. 2 **a** VALS thermosensitive gel a in room temperature **b** in body temperature; **b** gelation temperature of VALS thermosensitive gel (mean \pm SD, $n=3$)

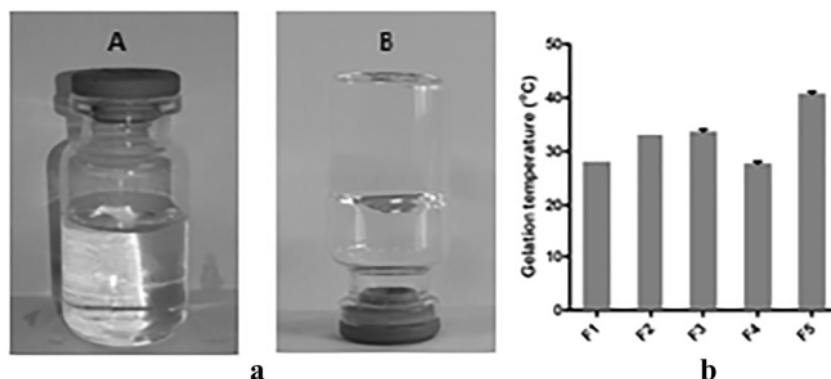

results showed that F2 and F3 had gelation temperatures that were most similar to the physiological skin temperature. Thermosensitive gels with the same concentration of Poloxamer 407 and Poloxamer 188 showed that gelation temperature increased when the concentration of Poloxamer 188 was raised. On the other hand, increasing the concentration of Poloxamer 407 decreased the gelation temperature of the thermosensitive gel [41]. The difference in gelation temperature of each formula was due to differences in the hydrophilic and hydrophobic structure of poly(propylene oxide) (PPO) and poly(ethylene oxide) (PEO) from Poloxamer 407 and Poloxamer 188 [28]. The basic structure of poloxamer consists of one PPO block flanked by two PEO blocks with different block lengths and produces various variations of poloxamers [42]. The hydrophobic and hydrophilic ratios of Poloxamer 407 and Poloxamer 188 are 3:7 and 2:8, which makes Poloxamer 407 more hydrophobic. The PPO hydrophobic block would cause a decrease in gelation temperature, while the PEO hydrophilic block would increase the gelation temperature. Thus, the greater the PPO ratio of the VALS gel formulation, the lower the gelation temperature of the preparation [34]. The data obtained showed that the gelation temperature of each formula was significantly different ($p < 0.05$).

Effect of Poloxamer on pH, Drug Content, and Spreadability

The pH test was carried out to investigate whether the skin could well tolerate the pH of the transdermal gel preparation. Generally, skin can tolerate the administration of the topical preparation with the pH values ranging from 4 to 7 [43]. Preparations with a pH outside this range could potentially cause problems, such as irritation, itching, or burning of the skin [44]. As shown in Table II, all the measured pHs were found to be in the range. Statistical analysis showed that the poloxamer concentration increased the pH of the preparation but was not significant ($p > 0.05$) [45]. Meanwhile, the results obtained in Table II reveal that the drug

Table II The Result of pH, Drug Content and Spreadability Test of VALS Thermosensitive Gel (Means \pm SD, $n=3$)


Formula	pH	Drug content (%)	Spreadability (cm ²)
F2	4.05 \pm 0.0	99.19 \pm 0.03	7.15 \pm 0.2
F3	4.15 \pm 0.0	97.11 \pm 0.02	0.2

content in both formulations was found to meet the requirements for drug content standards within 95–105% [46]. Based on these data, it was known that the content of each drug in both formulations was not statistically different ($p > 0.05$). Accordingly, it can be seen that the difference in the concentration of poloxamer did not significantly influence the drug content in the preparation and also shows that the gel preparation had uniform drug content that ensured a more accurate dosage when given to the patient. Additionally, the spreadability of all formulations shown in Table II indicates that F2 had a higher spreadability than F3. This was because F3 contained poloxamer with a higher concentration, which made the preparation's viscosity higher, and the spreadability decreased. Based on these data, it was known that the spreadability of the VALS gel in the two formulations has a significant difference ($p < 0.05$) due to the difference in the concentration of poloxamer in these hydrogels. Spreadability is one of the most important physical characteristics in a semi-solid preparation because it is responsible for administering the dose to the target and also for the ease of application [47].

Effect of Poloxamer Concentration on Viscosity and Rheological Properties

Viscosity is the most crucial rheological parameter to indicate the flow of preparation [48]. The results are depicted in Fig. 3, indicating that the viscosity of F3 was higher than that of F2 due to the fact that F3 contained a higher concentration of poloxamer combination when compared to F2. The

Fig. 3 **a** Viscosity of VALS thermosensitive gel in different temperatures; **b** rheology of VALS thermosensitive gel with variety of spindle rotation (rpm) (means \pm SD., $n = 3$)

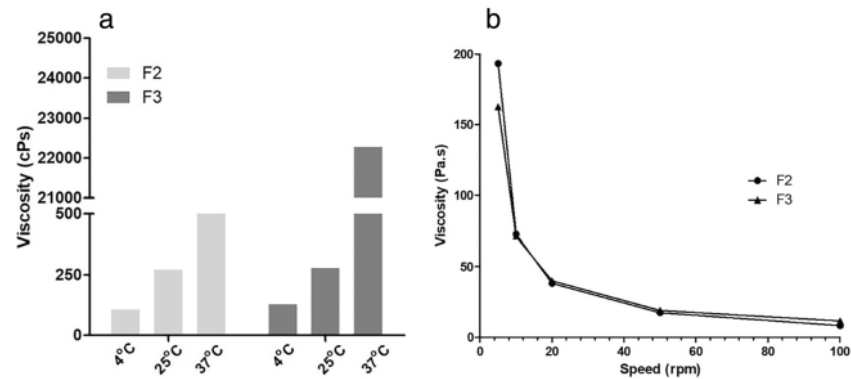

cross-linking of the hydrophobic groups of the poloxamer affects the gel strength. The fewer cross-links formed, the softer the gel, and the lower the viscosity of the gel [49]. From these data, it was also found that an increase in temperature can increase the viscosity of the preparation, especially when at body temperature, which indicates that at cold temperatures and room temperature, the preparation was still in liquid form. Furthermore, the preparation turned into a gel when it reached body temperature. Importantly, rheology studies the flow of a liquid preparation, especially non-Newtonian liquids exhibited by materials such as polymers. This long chain molecule most often exhibits a pseudoplastic type of flow, showing a visco[35] decrease when the force increases. In the gel rheology test, the following results are shown in Fig. 3. These results indicate that both formulas F2 and F3 had a pseudoplastic flow type because there was a decrease in viscosity and an increase in spindle speed during measurement. Based on these data, it was observed that the poloxamer concentration significantly affected the viscosity of the formulas ($p < 0.05$).

Effect of Poloxamer Concentration in *In Vitro* Release and Permeation of VALS

The incorporation of VALS into thermosensitive gel could potentially sustain the release and permeation of VALS. The following graph presented in Fig. 4a shows that the amount of drug released from the preparation after 24 h from F2 was 47.35 ± 0.23 mg, and F3 was 49.36 ± 0.24 mg. On the other hand, 49.36 ± 0.27 mg of VALS released only after 2 h in case of free VALS. This indicated the sustained release behavior was achieved following the incorporation of VALS into thermosensitive hydrogels. Moreover, Fig. 4b shows the amount of *in vitro* drug permeated from the preparation after 24 h. VALS permeated from F2 and F3 were 3.05 ± 0.21 mg and 3.65 ± 0.25 mg, respectively. Released without controlled release manner, 3.45 ± 0.19 mg of VALS permeated within 3 h. Performed in *ex vivo* study, the amount

of VALS permeated from the formulation after 24 h were 1.35 ± 0.05 mg and 1.64 ± 0.06 mg for F2 and F3, respectively. With respect to the permeation profile of free VALS, the sustained release pattern was not also observed, showing the amount of 1.46 ± 0.02 mg of VALS permeated after 3 h in *ex vivo* permeation studies. Analyzed statistically, the release and permeation profiles of VALS in *in vitro* and *ex vivo* studies from both formulations were significantly different ($p < 0.05$). The difference in the release profile might be due to the concentration of poloxamer used. The increase in the concentration of Poloxamer 188 could increase drug release from the preparation [50]. Poloxamer 188 has a relatively shorter chain and a smaller molar ratio or tendency to interact with water. Thus, it could potentially increase the water molecules around the hydrophilic PPO block in Poloxamer 407, which made the preparation tend to be eroded, and the drug could be more easily released from the preparation. According to the results, F3 was selected for further studies.

Effect of MNs in *Ex Vivo* Permeation of VALS

Finally, to improve the transdermal delivery of VALS from thermosensitive hydrogels, solid MNs were used. In the permeation profile investigation using MNs, three types of Dermaroller® with different needle lengths (0.5 mm, 1.0 mm, and 1.5 mm) were used to see the effect of MN needle length on VALS permeation in F3, which showed better physical characteristics, release profile, *in vitro* permeation, and *ex vivo* permeation. Figure 5a shows the amount of permeated VALS for up to 24 h. In the test without MNs, VALS permeated was found to be only 1.64 ± 0.05 mg. On the other side, preparations combined with MNs showed an increase in the amount of drug permeated. The combination with 0.5 mm MNs showed the amount of drug permeated of 2.32 ± 0.01 mg; the combination with 1.0 mm MNs was 2.65 ± 0.02 mg; and the combination with 1.5 mm MNs was 3.43 ± 0.02 mg. These results showed that the use of MNs could successfully

Fig. 4 The result of *in vitro* release of VALS thermosensitive gel **a**; *in vitro* permeation of VALS thermosensitive gel **b**; and ex vivo permeation of VALS thermosensitive gel **c** (means \pm SD., $n = 3$)


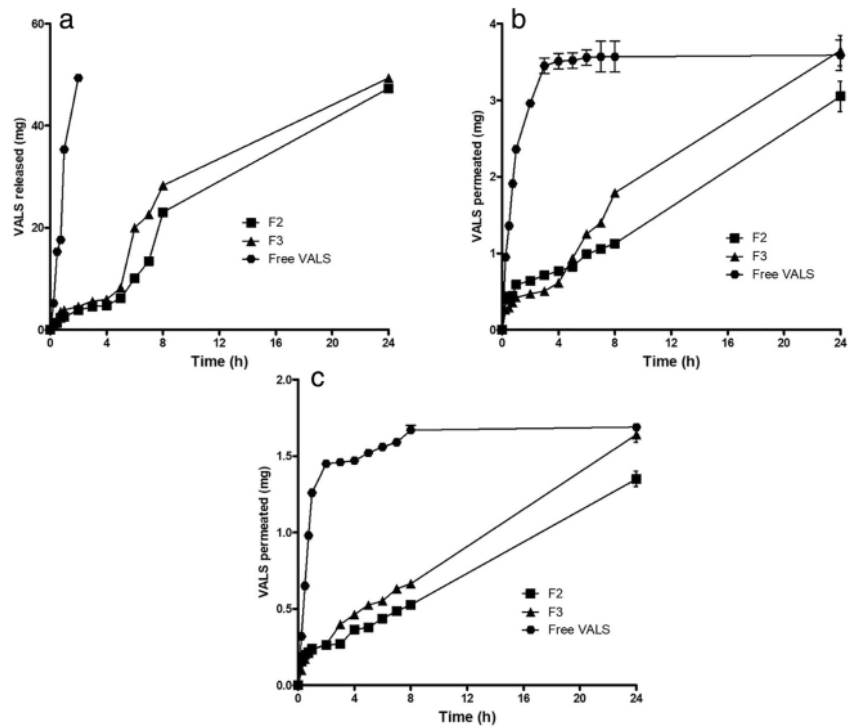


Fig. 5 The result ex vivo permeation of VALS from thermosensitive hydrogel F3 with and without MNs **a**; mean plasma concentration of VALS at several interval times following different administration routes **b** (means \pm SD., $n = 3$)

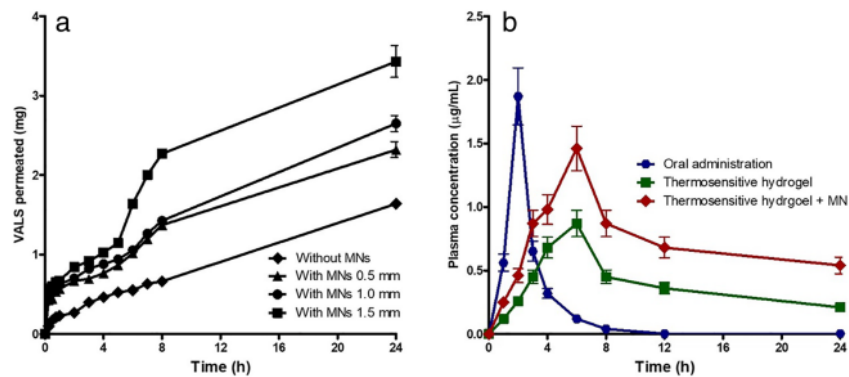

increase the permeation of transdermal preparations because it could form micropores on the skin. Therefore, the drug would easily pass through the SC, the skin's first barrier component. Furthermore, it was observed that the longer the MN needle, the greater the amount of drug permeated [21]. The results showed a significant increase in the amount of permeated VALS ($p < 0.05$) when VALS was combined with MNs so that it could potentially increase the amount of VALS that entered the body.

In Vivo Study

As previously discussed, this study was designed to overcome the bioavailability issue of VALS when administered through oral administration. In this study, the pharmacokinetic profiles of VALS delivered from the combination of thermosensitive gel and solid MNs were compared to the administration of thermosensitive gel without solid MNs and the conventional oral administration. The plasma

Table III Pharmacokinetic Parameters of VALS Following the Oral Administration, the Transdermal Delivery of Thermosensitive Hydrogel and the Combination of Hydrogel With MNs (Means \pm SD., $n = 3$)

Parameter	Unit	Oral	Thermosensitive hydrogel	Thermosensitive hydrogel + MNs
$t_{1/2}$	h	2.52 \pm 0.32	14.75 \pm 2.11	25.33 \pm 3.09
T_{max}	h	2.00	6.00	6.00
C_{max}	$\mu\text{g/mL}$	1.87 \pm 0.23	0.87 \pm 0.98	1.46 \pm 0.21
C_{0-t}	$\mu\text{g/mL} \times \text{h}$	3.97 \pm 0.45	9.08 \pm 1.02	17.26 \pm 1.98
AUC 0-inf	$\mu\text{g/mL} \times \text{h}$	3.98 \pm 0.51	13.55 \pm 1.65	37.00 \pm 4.56
MRT 0-inf	h	2.97 \pm 0.35	21.73 \pm 2.33	37.46 \pm 4.87

concentrations of VALS following three different administrations are depicted in Fig. 5b. Moreover, several pharmacokinetic parameters were evaluated, such as $t_{1/2}$, T_{max} , C_{max} , AUC, and MRT, as depicted in Table III. The $t_{1/2}$ is the time where the concentration of the drugs in the body decreases by half of the initial dose. C_{max} represents the highest concentration of the administered drugs in the body. Importantly, AUC values are utilized to assess the total drug exposure in the body during the evaluation time. The MRT represents the average time of the drugs administered residing in the body [51]. Following oral administration, it was found that $t_{1/2}$, T_{max} , and C_{max} values of VALS were 2.52 \pm 0.32 h, 2 h, and 1.87 \pm 0.23 $\mu\text{g/mL}$. These values were also similarly observed in a previous study performing pharmacokinetic determination of VALS using a similar dose with VALS dose used in our study [43]. After the transdermal delivery using thermosensitive hydrogel, the values were 14.75 \pm 2.11 h, 6 h, and 0.87 \pm 0.98 $\mu\text{g/mL}$ for $t_{1/2}$, T_{max} , and C_{max} , respectively. Importantly, with the combination with MNs, that $t_{1/2}$, T_{max} , and C_{max} values of VALS were 25.33 \pm 3.09 h, 6 h, and 1.46 \pm 0.21 $\mu\text{g/mL}$. The results showed that compared to oral administration, transdermal delivery could improve the bioavailability of VALS, indicated by the improvement of AUC values. The highest AUC value was achieved after the combination of thermosensitive hydrogel and MNs, showing the value of 17.26 \pm 1.98 $\mu\text{g/mL} \times \text{h}$. This value was significantly higher ($p < 0.05$), compared to AUC values of oral administration and thermosensitive hydrogel groups. Moreover, the residence time of VALS was also significantly improved through transdermal delivery, showing the controlled release manner of VALS. As discussed previously, the pores created by MNs would allow the effective permeation of the thermosensitive hydrogels. Due to the thermosensitive properties, the transformation of the formulation into gel in the body temperature would be beneficial to sustain the release of VALS to the systemic circulation from the skin. Accordingly, the combination of thermosensitive and MNs offers two main benefits. First,

it could improve the bioavailability of VALS. Second, this approach could sustain the *in vivo* release of VALS. This could potentially reduce the administration frequency of the treatment, leading the patient compliance during the hypertension therapy.

Overall, the results obtained in this study served as a proof of concept, showing that the permeation of VALS through the skin from thermosensitive hydrogel could potentially be improved using solid MNs. This could be beneficial in the treatment of hypertension. However, *in vivo* animal works using hypertension model should now be carried out to investigate the effectiveness of this combination approach. In addition, dose determination, drug toxicity, and skin irritation studies should also be considered.

Conclusion

This study investigated the potency of a transdermal delivery system to enhance the VALS permeated through the skin layer using poloxamer-based thermosensitive gel. According on the findings presented in this study, it was shown that VALS thermosensitive gel was successfully prepared using combination of Poloxamer 188 and Poloxamer 407, where concentration of poloxamer affected the physical properties of thermosensitive gel. Furthermore, the combination of VALS transdermal thermosensitive gel and solid MNs enhanced the permeation of VALS in *ex vivo* rat skin and improved the bioavailability of VALS in *in vivo* study. The major advancement of the combinatorial delivery system we have presented in this work led to higher permeation through the skin that could improve the efficiency of hypertension therapy, hypothetically. Building from these stated results, further studies including *in vivo* efficacy studies should be carried out to completely investigate the therapeutic efficacy of this approach in hypertension animal models.

Author Contribution Nirmayanti Nirmayanti: conceptualization, methodology, and writing — original draft. Alhidayah Alhidayah: methodology and writing — original draft. Jessica Theodor Usman: methodology and writing — original draft. Julika Fajrika Nur: methodology and data curation. Muh. Nur Amir: data curation, validation, and supervision. Andi Dian Permana: conceptualization, project administration, funding acquisition, validation, and supervision. The manuscript was written through contributions of all the authors. All the authors have given approval to the final version of the manuscript.

Funding This study did not receive any funding.

Declarations

Ethics Approval We have no ethical issue to declare.

Competing Interests The authors declare no competing interests.

References

- Dipiro JT, Yee GC, Posey LM, Haines ST, Nolin TD, Ellingrod V. *Pharmacotherapy: a pathophysiologic approach*. 11th ed. New York: The McGraw-Hill Companies, Inc.; 2020.
- Ahad A, Aqil M, Kohli K, Sultana Y, Mujeeb M. Enhanced transdermal delivery of an anti-hypertensive agent via nanoethosomes: statistical optimization, characterization and pharmacokinetic assessment. *Int J Pharm*. 2013;443:26–38.
- World Health Organization. Hypertension. WHO Rep. 2021. p. 1. Available from: <https://www.who.int/news-room/fact-sheets/detail/hypertension>. Accessed 7 Feb 2022.
- Mills KT, Stefanescu A, He J. The global epidemiology of hypertension. *Nat Rev Nephrol*. 2020;16:223–37.
- Zhou B, Carrillo-Larco RM, Danaei G, Riley LM, Paciorek CJ, Stevens GA, et al. Worldwide trends in hypertension prevalence and progress in treatment and control from 1990 to 2019: a pooled analysis of 1201 population-representative studies with 104 million participants. *Lancet*. 2021;398:957–80.
- Bhosale SS, Avachat AM. Design and development of ethosomal transdermal drug delivery system of valsartan with pre-clinical assessment in Wistar albino rats. *J Liposome Res*. 2013;23:119–25.
- Permana AD, McCrudden MTC, Donnelly RF. Enhanced intradermal delivery of nanosuspensions of antifilaria drugs using dissolving microneedles: a proof of concept study. *Pharmaceutics*. 2019;11:346.
- Permana AD, Tekko IA, McCrudden MTC, Anjani QK, Ramadan D, McCarthy HO, et al. Solid lipid nanoparticle-based dissolving microneedles: a promising intradermal lymph targeting drug delivery system with potential for enhanced treatment of lymphatic filariasis. *J Control Release*. 2019;316:34–52.
- Alkilani AZ, McCrudden MTC, Donnelly RF. Transdermal drug delivery: innovative pharmaceutical developments based on disruption of the barrier properties of the stratum corneum. *Pharmaceutics*. 2015;7:438–70.
- Santinon C, de Freitas ED, da Silva MGC, Vieira MGA. Modification of valsartan drug release by incorporation into sericin/alginate blend using experimental design methodology. *Eur Polym J*. 2021;153:110506. <https://doi.org/10.1016/j.eurpolymj.2021.110506>.
- Xu WJ, Xie HJ, Cao QR, Shi LL, Cao Y, Zhu XY, et al. Enhanced dissolution and oral bioavailability of valsartan solid dispersions prepared by a freeze-drying technique using hydrophilic polymers. *Drug Deliv Taylor and Francis Ltd*. 2016;23:41–8.
- Sapkal SB, Shinde SA, Darakhe RA, Shikhande VN. Solid dispersion of valsartan for solubility improvement using β -cyclodextrin. *MOJ Bioequiv Bioavailab*. 2018;5:313–9.
- Yan YD, Sung JH, Kim KK, Kim DW, Kim JO, Lee BJ, et al. Novel valsartan-loaded solid dispersion with enhanced bioavailability and no crystalline changes. *Int J Pharm Elsevier*. 2012;422:202–10.
- Park YJ, Lee HK, Im YB, Lee W, Han HK. Improved pH-independent dissolution and oral absorption of valsartan via the preparation of solid dispersion. *Arch Pharm Res*. 2010;33:1235–40.
- Ahad A, Aqil M, Ali A. Investigation of antihypertensive activity of carbopol valsartan transdermal gel containing 1,8-cineole. *Int J Biol Macromol*. 2014;64:144–9.
- Himawan A, Djide NJN, Mardikasari SA, Utami RN, Arjuna A, Donnelly RF, et al. A novel in vitro approach to investigate the effect of food intake on release profile of valsartan in solid dispersion-floating gel in-situ delivery system. *Eur J Pharm Sci*. 2022;168:106057. <https://doi.org/10.1016/j.ejps.2021.106057>.
- Khan S, Minhas MU, Tekko IA, Donnelly RF, Thakur RRS. Evaluation of microneedles-assisted in situ depot forming poloxamer gels for sustained transdermal drug delivery. *Drug Deliv Transl Res*. 2019;9:764–82.
- Ahmed KS, Shan X, Mao J, Qiu L, Chen J. Derma roller@microneedles-mediated transdermal delivery of doxorubicin and celecoxib co-loaded liposomes for enhancing the anticancer effect. *Mater Sci Eng C Elsevier*. 2019;99:1448–58. <https://doi.org/10.1016/j.msec.2019.02.095>.
- Badran MM, Kuntsche J, Fahr A. Skin penetration enhancement by a microneedle device (Dermaroller®) in vitro: dependency on needle size and applied formulation. *Eur J Pharm Sci*. 2009;36:511–23.
- Ananda PWR, Elim D, Zaman HS, Muslimin W, Tunggeng MGR, Permana AD. Combination of transdermal patches and solid microneedles for improved transdermal delivery of primaquine. *Int J Pharm*. 2021;609:121204. <https://doi.org/10.1016/j.ijpharm.2021.121204>.
- Tobin KV, Fiegel J, Brogden NK. Thermosensitive gels used to improve microneedle-assisted transdermal delivery of naltrexone. *Polymers (Basel)*. 2021;13:1–15.
- Khattab A, Marzok S, Ibrahim M. Development of optimized mucoadhesive thermosensitive pluronic based in situ gel for controlled delivery of Latanoprost: antiglaucoma efficacy and stability approaches. *J Drug Deliv Sci Technol*. 2019;53:101134.
- Asma N, Maddeppungeng NM, Raihan M, Erdiana AP, Himawan A, Permana AD. New HPLC-UV analytical method for quantification of metronidazole: application to ex vivo ocular kinetic assessments following the administration of thermosensitive ocular in situ gel. *Microchem J*. 2022;172:106929. <https://doi.org/10.1016/j.microc.2021.106929>.
- Enggi CK, Isa HT, Sulistiawati S, Ardika KAR, Wijaya S, Asri RM, et al. Development of thermosensitive and mucoadhesive gels of cabotegravir for enhanced permeation and retention profiles in vaginal tissue: a proof of concept study. *Int J Pharm*. 2021;609:121182. <https://doi.org/10.1016/j.ijpharm.2021.121182>.
- Tuçcu-Demiröz F. Development of in situ poloxamer-chitosan hydrogels for vaginal drug delivery of benzydamine hydrochloride: textural, mucoadhesive and in vitro release properties. *Marmara Pharm J*. 2017;21:762–70.
- Soliman GM, Fetih G, Abbas AM. Thermosensitive bioadhesive gels for the vaginal delivery of sildenafil citrate: in vitro characterization and clinical evaluation in women using clomphene citrate for induction of ovulation. *Drug Dev Ind Pharm*. 2016;43:399–408.
- Zhang T, Chen S, Dou H, Liu Q, Shu G, Lin J, et al. Novel glucosamine-loaded thermosensitive hydrogels based on poloxamers for osteoarthritis therapy by intra-articular injection. *Mater Sci Eng C*. 2021;118:111352. <https://doi.org/10.1016/j.msec.2020.111352>.
- Permana AD, Nurul R, Layadi P, Himawan A, Juniarti N, Kurnia Q, et al. Thermosensitive and mucoadhesive in situ ocular gel for effective local delivery and antifungal activity of itraconazole nanocrystal in the treatment of fungal keratitis. *Int J Pharm*. 2021;602:120623.
- Din FU, Mustapha O, Kim DW, Rashid R, Park JH, Choi JY, et al. Novel dual-reverse thermosensitive solid lipid nanoparticle-loaded hydrogel for rectal administration of flurbiprofen with improved bioavailability and reduced initial burst effect. *Eur J Pharm Biopharm*. 2015;94:64–72.
- Chen J, Zhou R, Li L, Li B, Zhang X, Su J. Mechanical, rheological and release behaviors of a poloxamer 407/poloxamer 188/carbopol 940 thermosensitive composite hydrogel. *Molecules*. 2013;18:12415–25.

31. Permana AD, Utomo E, Pratama MR, Amir MN, Anjani QK, Mardikasari SA, et al. Bioadhesive-thermosensitive in situ vaginal gel of the gel flake-solid dispersion of itraconazole for enhanced antifungal activity in the treatment of vaginal candidiasis. *ACS Appl Mater Interfaces*. 2021;13:18128–41.
32. Nief RA, Hussein AA. Preparation and evaluation of meloxicam microsponges as transdermal delivery system. *Iraqi J Pharm Sci*. 2014;23:62–7.
33. Verma S, Chaudhary B. Preparation and evaluation of novel in situ gels containing acyclovir for the treatment of oral herpes simplex virus infections simultaneous estimation of mycophenolate mofetil and prednisolone view project preparation and evaluation of novel in situ gels. *Artic Sci World J*. 2014;2014:280928.
34. Fathalla ZMA, Vangala A, Longman M, Khaled KA, Hussein AK, El-Garhy OH, et al. Poloxamer-based thermoresponsive ketorolac tromethamine in situ gel preparations: design, characterisation, toxicity and transcorneal permeation studies. *Eur J Pharm Biopharm*. 2017;114:119–34.
35. Putri HE, Utami RN, Aliyah, Wahyudi E, Oktaviani WW, Mudjahid M, et al. Dissolving Microneedle Formulation of Ceftriaxone: effect of Polymer Concentrations on Characterisation and Ex Vivo Permeation Study. *J Pharm Innov* 2021. <https://doi.org/10.1007/s12247-021-09593-y>
36. Ramadan D, Permana AD, Courtenay AJ, McCrudden MTC, Tekko IA, McAlister E, et al. Development, evaluation, and pharmacokinetic assessment of polymeric microarray patches for transdermal delivery of vancomycin hydrochloride. *Mol Pharm*. 2020;17:3353–68.
37. Peleshok K, Bondar B, Kryskiw L, Kucher T, Poliak O, Logoyda L. Non-extractive spectrophotometric determination of valsartan in pure form and in pharmaceutical products by ion-pair complex formation with bromophenol blue and methyl red. *Pharmacia*. 2021;68:851–8.
38. Zhang Y, Huo M, Zhou J, Xie S. PKSolver: an add-in program for pharmacokinetic and pharmacodynamic data analysis in Microsoft Excel. *Comput Methods Programs Biomed*. 2010;99:306–14.
39. Jain D. Newer trends in in situ gelling systems for controlled ocular drug delivery. *J Anal Pharm Res*. 2016;2:1–16.
40. Mura S, Manconi M, Sinico C, Valenti D, Maria A. Penetration enhancer-containing vesicles (PEVs) as carriers for cutaneous delivery of minoxidil. *Int J Pharm*. 2009;380:72–9.
41. Zhang K, Shi X, Lin X, Yao C, Shen L, Feng Y. Poloxamer-based in situ hydrogels for controlled delivery of hydrophilic macromolecules after intramuscular injection in rats. *Drug Deliv*. 2015;22:375–82.
42. Li X, Hyun K. Rheological study of the effect of polyethylene oxide (PEO) homopolymer on the gelation of PEO-PPO-PEO triblock copolymer in aqueous solution. *Korea Aust Rheol J*. 2018;30:109–25.
43. Kim MS, Baek IH. Fabrication and evaluation of valsartan-polymer-surfactant composite nanoparticles by using the supercritical antisolvent process. *Int J Nanomedicine*. 2014;9:5167–76.
44. Alberti I, Grenier A, Kraus H, Carrara DN. Pharmaceutical development and clinical effectiveness of a novel gel technology for transdermal drug delivery. *Expert Opin Drug Deliv*. 2005;2:935–50.
45. Jarmolowska KM. The effect of poloxamer 407 on the properties of hydrophilic gels containing lactic acid complexed with chitosan. *Prog Chem Appl Chitin Its*. 2010;15:143–8.
46. Lalitha N, Sanjay PPN, Vyshak MG, Kadri U, Pharmacy AC, Lalbagh N, et al. Stability-indicating reverse phase HPLC method for the determination of cefazolin. *Trop J Pharm Res*. 2010;9:45–50.
47. Rençber S, Karavana SY, Şenyiğit ZA, Eraç B, Limoncu MH, Baloğlu E. Mucoadhesive in situ gel formulation for vaginal delivery of clotrimazole: formulation, preparation, and in vitro/in vivo evaluation. *Pharm Dev Technol*. 2017;22:551–61.
48. Aho J, Boetker JP, Baldursdottir S, Rantanen J. Rheology as a tool for evaluation of melt processability of innovative dosage forms. *Int J Pharm*. 2015;494:623–42.
49. Rarokar NR, Saoji SD, Khedekar P. Investigation of effect of extensively used polymers on thermoreversible properties of Pluronic® tri-block polymer. *J Food Pharm Sci*. 2017;5:29–39.
50. Inal O, Yapar EA. Effect of mechanical properties on the release of meloxicam from poloxamer gel bases. *Indian J Pharm Sci*. 2013;75:700–6.
51. Permana AD, Paredes AJ, Zanutto FV, Amir MN, Ismail I, Bahar MA, et al. Albendazole nanocrystal-based dissolving microneedles with improved pharmacokinetic performance for enhanced treatment of cystic echinococcosis. *ACS Appl Mater Interfaces*. 2021;13:38745–60.

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Springer Nature or its licensor (e.g. a society or other partner) holds exclusive rights to this article under a publishing agreement with the author(s) or other rightsholder(s); author self-archiving of the accepted manuscript version of this article is solely governed by the terms of such publishing agreement and applicable law.

ORIGINALITY REPORT

21 %
SIMILARITY INDEX

16 %
INTERNET SOURCES

15 %
PUBLICATIONS

4 %
STUDENT PAPERS

PRIMARY SOURCES

1 biointerfaceresearch.com 5 %
Internet Source

2 www.ncbi.nlm.nih.gov 1 %
Internet Source

3 dspace.hmlibrary.ac.in:8080 1 %
Internet Source

4 "Advanced Biopolymeric Systems for Drug Delivery", Springer Science and Business Media LLC, 2020 1 %
Publication

5 Submitted to Universitas Indonesia 1 %
Student Paper

6 www.dovepress.com 1 %
Internet Source

7 Khalid El-Say, Mutlaq Al-Subaie, Khaled Hosny, Tarek Ahmed, Bader Aljaeid. "Utilization of nanotechnology to enhance percutaneous absorption of acyclovir in the treatment of herpes simplex viral infections", International Journal of Nanomedicine, 2015 1 %

8

Submitted to Badan PPSDM Kesehatan
Kementerian Kesehatan

Student Paper

<1 %

9

link.springer.com

Internet Source

<1 %

10

Samiullah Khan, Muhammad Usman Minhas,
Ismaiel A. Tekko, Ryan F. Donnelly, Raghu Raj
Singh Thakur. "Evaluation of microneedles-
assisted in situ depot forming poloxamer gels
for sustained transdermal drug delivery",
Drug Delivery and Translational Research,
2019

Publication

<1 %

11

Latifah Rahman, Reni Sriyani Lembang,
Subehan Lallo, Sri Resky Handayani,
Usmanengsi, Andi Dian Permana.

"Bioadhesive dermal patch as promising
approach for improved antibacterial activity
of bioactive compound of Zingiber
cassumunar Roxb in ex vivo Staphylococcus
aureus skin infection model", Journal of Drug
Delivery Science and Technology, 2021

Publication

<1 %

12

Sagar S. Bhosale, Amelia M. Avachat. "Design
and development of ethosomal transdermal
drug delivery system of valsartan with

<1 %

preclinical assessment in Wistar albino rats",
Journal of Liposome Research, 2013

Publication

13

Divya Thakur, Gurpreet Kaur, Sheetu Wadhwa, Ashana Puri. "Development, Pre-clinical Investigation and Histopathological Evaluation of Metronidazole Loaded Topical Formulation for Treatment of Skin Inflammatory Disorders", Drug Delivery Letters, 2021

Publication

<1 %

14

Fakhar-ud-Din, Gul Majid Khan. "Development and characterisation of levosulpiride-loaded suppositories with improved bioavailability ", Pharmaceutical Development and Technology, 2017

Publication

<1 %

15

medcraveonline.com

Internet Source

<1 %

16

res.mdpi.com

Internet Source

<1 %

17

A.İşıl Özdöğün, Gülçin Akca, Sevda Şenel. "Development and in vitro evaluation of gel formulation of atorvastatin solid dispersions", Journal of Drug Delivery Science and Technology, 2021

Publication

<1 %

18

Qonita Kurnia Anjani, Akmal Hidayat Bin Sabri, Juan Domínguez-Robles, Natalia Moreno-Castellanos et al. "Metronidazole nanosuspension loaded dissolving microarray patches: An engineered composite pharmaceutical system for the treatment of skin and soft tissue infection", *Biomaterials Advances*, 2022

Publication

<1 %

19

thno.org
Internet Source

<1 %

20

Sarah A. El-Lakany, Nazik A. Elgindy, Maged W. Helmy, Marwa M Abu-Serie, Ahmed O. Elzoghby. "Lactoferrin-decorated vs. PEGylated zein nanospheres for combined aromatase inhibitor and herbal therapy of breast cancer", *Expert Opinion on Drug Delivery*, 2018

Publication

<1 %

21

Submitted to Nelson Mandela Metropolitan University
Student Paper

<1 %

22

Sung Hyun Im, Hoe Taek Jung, Myoung Jin Ho, Jeong Eun Lee et al. "Montelukast Nanocrystals for Transdermal Delivery with Improved Chemical Stability", *Pharmaceutics*, 2019

Publication

<1 %

23

mdpi-res.com

Internet Source

<1 %

24

sure.sunderland.ac.uk

Internet Source

<1 %

25

Abdul Ahad, Mohammed Aqil, Kanchan Kohli, Yasmin Sultana, Mohd Mujeeb, Asgar Ali. "Role of novel terpenes in transcutaneous permeation of valsartan: effectiveness and mechanism of action", Drug Development and Industrial Pharmacy, 2011

Publication

<1 %

26

Estelle Dumont, Julia Vergalli, Jelena Pajovic, Satya P Bhamidimarri et al. "Mechanistic aspects of maltotriose-conjugate translocation to the Gram-negative bacteria cytoplasm", Life Science Alliance, 2018

Publication

<1 %

27

Fatima Farrukh, Amin Abbasi, Misbah Jawed, Aysha Almas, Tazeen Jafar, Salim S. Virani, Zainab Samad. "Hypertension in Women: A South-Asian Perspective", Frontiers in Cardiovascular Medicine, 2022

Publication

<1 %

28

Priscila Rosa, Juliana dos Santos, Tássia Fontana Lehmen, Julia Weber et al. " and evaluation of a desonide gel-cream

<1 %

photostabilized with benzophenone-3 ", Drug Development and Industrial Pharmacy, 2015

Publication

29 ijpsr.com Internet Source <1 %

30 www.njpppp.com Internet Source <1 %

31 avmajournals.avma.org Internet Source <1 %

32 Shivani Verma, Puneet Utreja. "Oleic Acid Vesicles as a New Approach for Transdermal Delivery of Econazole Nitrate: Development, Characterization, and In-vivo Evaluation in Wistar Rats", Recent Advances in Anti-Infective Drug Discovery, 2021
Publication <1 %

33 ecampus.sttind.ac.id Internet Source <1 %

34 www.acarindex.com Internet Source <1 %

35 www.google.com Internet Source <1 %

36 www.walshmedicalmedia.com Internet Source <1 %

37 Ahad, A.. "Formulation and optimization of nanotransfersomes using experimental <1 %

design technique for accentuated transdermal delivery of valsartan", Nanomedicine: Nanotechnology, Biology, and Medicine, 201202

Publication

38

Basant A. Habib, Sinar Sayed, Ghada M. Elsayed. "Enhanced transdermal delivery of ondansetron using nanovesicular systems: Fabrication, characterization, optimization and ex-vivo permeation study-Box-Cox transformation practical example", European Journal of Pharmaceutical Sciences, 2018

Publication

<1 %

39

Cinthia M. Batista, Luma A. de Queiroz, Ângela V.F. Alves, Elisiane C.A. Reis et al. "Photoprotection and skin irritation effect of hydrogels containing hydroalcoholic extract of red propolis: A natural pathway against skin cancer", Heliyon, 2022

Publication

<1 %

40

Lijie Li, Dadong Guo, Junguo Guo, Jike Song, Qiuxin Wu, Damei Liu, Hongsheng Bi, Xiaofeng Xie. "Thermosensitive in-situ forming gels for ophthalmic delivery of tea polyphenols", Journal of Drug Delivery Science and Technology, 2018

Publication

<1 %

41 Mohamed M. Badran, Abdullah H. Alomrani, Aliyah Almomen, Yousef A. Bin Jordan, Amal El Sayeh Abou El Ela. "Novel Metoprolol-Loaded Chitosan-Coated Deformable Liposomes in Thermosensitive In Situ Gels for the Management of Glaucoma: A Repurposing Approach", Gels, 2022
Publication <1 %

42 Rohan Aggarwal, Monika Targhotra, Bhumika Kumar, P.K Sahoo, Meenakshi K. Chauhan. "Novel Polypseudorotaxanes Hydrogel based Nail Lacquer of Efinaconazole for Transungual Drug Delivery", Drug Delivery Letters, 2021
Publication <1 %

43 Yuanyuan Jin, Da Liu, Zhen Lu, Lubing Yang, Jiangli Chen, Xuyan Zhou, Zhidong Qiu, Ye Jin. "Preparation and Evaluation of Liposomes and Niosomes Containing Total Ginsenosides for Anti-Photoaging Therapy", Frontiers in Bioengineering and Biotechnology, 2022
Publication <1 %

44 pure.ulster.ac.uk
Internet Source <1 %

45 www.mdpi.com
Internet Source <1 %

46 www.sciencegate.app
Internet Source <1 %

47 Mohamed Badran. "Effect of terpene liposomes on the transdermal delivery of hydrophobic model drug, nimesulide: Characterization, stability and in vitro skin permeation", African Journal of Pharmacy and Pharmacology, 2012
Publication

<1 %

48 Tarek M. Ibrahim, Marwa H. Abdallah, Nagia A. El-Megrab, Hanan M. El-Nahas. "Transdermal ethosomal gel nanocarriers; a promising strategy for enhancement of anti-hypertensive effect of carvedilol", Journal of Liposome Research, 2018
Publication

<1 %

49 dspace.bsu.edu.ru
Internet Source

<1 %

50 jnanobiotechnology.biomedcentral.com
Internet Source

<1 %

51 pubmed.ncbi.nlm.nih.gov
Internet Source

<1 %

52 www.jddtonline.info
Internet Source

<1 %

53 www.nrcresearchpress.com
Internet Source

<1 %

54 www.pnrjournal.com
Internet Source

<1 %

55

www.tandfonline.com

Internet Source

<1 %

56

"Delivery Technologies for Biopharmaceuticals", Wiley, 2009

Publication

<1 %

57

Abdul Ahad, Mohd. Aqil, Asgar Ali. "Investigation of antihypertensive activity of carbopol valsartan transdermal gel containing 1,8-cineole", International Journal of Biological Macromolecules, 2014

Publication

<1 %

58

Amarjitsing Rajput, Aditi Bariya, Ahmed Allam, Sarah Othman, Shital B. Butani. "In situ nanostructured hydrogel of resveratrol for brain targeting: in vitro-in vivo characterization", Drug Delivery and Translational Research, 2018

Publication

<1 %

59

Tarek A. Ahmed, Khalid M. El-Say, Osama A. A. Ahmed, Bader M. Aljaeid. "

Superiority of TPGS-loaded micelles in the brain delivery of vinpocetine via administration of thermosensitive intranasal gel

", International Journal of Nanomedicine, 2019

Publication

<1 %

60

Abdul Ahad, Mohd. Aqil, Kanchan Kohli, Yasmin Sultana, Mohd. Mujeeb. "Enhanced transdermal delivery of an anti-hypertensive agent via nanoethosomes: Statistical optimization, characterization and pharmacokinetic assessment", International Journal of Pharmaceutics, 2013

Publication

<1 %

61

Binu Chaudhary, Surajpal Verma. "Preparation and Evaluation of Novel Gels Containing Acyclovir for the Treatment of Oral Herpes Simplex Virus Infections ", The Scientific World Journal, 2014

Publication

<1 %

62

Kevin Ita, Sharon Ashong. "Percutaneous Delivery of Antihypertensive Agents: Advances and Challenges", AAPS PharmSciTech, 2020

Publication

<1 %

63

Viliana Gugleva, Stefka Titeva, Neli Ermenlieva, Sonya Tsibranska, Slavka Tcholakova, Stanislav Rangelov, Denitsa Momekova. "Development and evaluation of doxycycline niosomal thermoresponsive in situ gel for ophthalmic delivery", International Journal of Pharmaceutics, 2020

Publication

<1 %

64

Vivien Kmietczyk, Eva Riechert, Laura Kalinski, Etienne Boileau et al. " m A-mRNA methylation regulates cardiac gene expression and cellular growth ", Life Science Alliance, 2019

Publication

<1 %

Exclude quotes On

Exclude matches < 5 words

Exclude bibliography On