



# Silver nanoparticles (AgNPs) synthesis methods as heavy-metal sensors: a review

F. Sudarman<sup>1</sup> · M. Shiddiq<sup>2</sup> · B. Armynah<sup>1</sup> · D. Tahir<sup>1</sup>

Received: 19 March 2022 / Revised: 21 December 2022 / Accepted: 30 December 2022

© The Author(s) under exclusive licence to Iranian Society of Environmentalists (IRSEN) and Science and Research Branch, Islamic Azad University 2023

## Abstract

The quick and high-accuracy location of heavy metals is one of the principal prerequisites for reducing the environmental pollution. Therefore, the rapid and precise detection of heavy metals has become a primary problem for scientists worldwide. Among the different heavy metals, arsenic, cadmium, lead, mercury, and chromium (Cr) are highly toxic. Silver nanoparticles (AgNPs) have been created for the detection of heavy metals. The use of nanomaterials is promoted because of their solid adsorption, high electron energy, and biocompatibility, which are appropriate for heavy-metal sensor applications. This review focused on synthesis AgNPs by biological, chemical, and physical methods and their capability for detection of heavy metals by colorimetric methods included the practical and basic assessment of toxic heavy metals, and they are easily implemented on location, use simple instruments, and provide simple analysis results. In this review, we have provided the promising possibilities with new prospects and challenges for high efficiency and stability of AgNPs as a multi-sensor of heavy-metal ions with high-sensitive detection in tainted water bodies.

**Keywords** AgNPs · Heavy-metal ions · Sensor colorimetric · Environmental pollution

## Introduction

The innovation in the use of nanoscience and nanomaterials in various field applications, including energy, optoelectronics, biomedicine, and biotechnology, has been reported (Zannotti et al. 2020). Nanotechnology is a part of such innovation, and it is applied in nanosized synthesis methodology. This rapidly developing and innovative technology has received interest over the last decade due to its historical backdrop of wide applications. Nanotechnology is a multi-disciplinary field with first uncovered. Characterization by nanotechnology is being prepared for control of nanoscale objects, where “nano” means one billionth of an actual unit. However, no settlement has been achieved regarding the meaning of nanotechnology (Kakakhel et al. 2021).

Nanoparticles (NPs) are natural substances used in nanotechnology (Magaye and Zhao 2012). The two types of NP sources can be inorganic or organic. AgNPs are inorganic NPs (Maaz 2018) with sizes in the 1–100 nm range. Investigations of AgNPs have focused on their unique physical, chemical, and biological properties. Their prevalence is mainly attributed to their form, composition, crystallinity, and structure of AgNPs, which is contrast with its mass structure (Syafuddin et al. 2017), (Wang et al. 2015).

Metal NPs can be synthesized by chemical or physical methods. In general, bottom-up and top-down approaches, such as chemical reduction, have been used for the preparation of metallic NPs. The advantages of chemical and physical methods include their easy execution, large quantity production, and well-controlled particle interspacing; however, they also have disadvantages, such as the remarkably high cost, including those for the equipment and operation, and high energy consumption (Lin et al. 2021). Materials that are used for the synthesis of AgNPs using this chemical method are very toxic and hazardous in nature (Panja et al. 2021). Electrochemical methods are very intriguing because of their high performance in obtaining particles, which they attain by utilizing quick and direct techniques and controlling the molecular size effectively. Through

---

Editorial responsibility: Ta Yeong Wu.

✉ D. Tahir  
dtahir@fmipa.unhas.ac.id

<sup>1</sup> Department of Physics, Hasanuddin University, Makassar 90245, Indonesia

<sup>2</sup> Research Center for Physics, Indonesia Institute of Sciences, Puspiptek, Banten 15314, Indonesia



these procedures, particles are not limited to the size and shape of a few compositions. In addition, such methods are eco-accommodating, that is, they steer away from the use of reducer specialists, which are occasionally toxic. The biological method is simple, environmentally friendly, and commercial, uses a single step method, and does not require elevated temperature, pressure, force, and harmful chemicals (Panja et al. 2021).

Over the period of years, various conventional analytical methods have been established for the detection of heavy metals at very low and ultra-low level employing different techniques such as liquid chromatography, UV–Vis spectroscopy, X-ray fluorescence spectroscopy (XFS), capillary electrophoresis (CE), microprobes (MP), anodic stripping voltammetry (ASV), atomic absorption spectroscopy (AAS), inductively coupled plasma mass spectroscopy (ICP-MS), and inductively coupled plasma optical emission spectroscopy (ICP-OES) (Yu et al. 2022). However, these analytical tools suffer from several limitations including sample preparation, cleanup, pre-concentration processes, expensive instruments, and professional personnel on the other hand, facile, inexpensive, and easy implementation for the metal detection such as electrochemical colorimetric and fluorescence detection (Buledi et al. 2020) (Aragay et al. 2011).

In recent years, nanomaterial-based sensors have shown great potential in detection of heavy metals due to their high surface reactivity, large surface area, strong adsorption capacity, and high catalytic efficiency. Various nanomaterials like metal and metal oxide nanoparticles, polymeric nanomaterials, silicon, and carbon based nanomaterials have been used to design special nanosensors for the detection of toxic heavy metals. The enhanced sensitivity and selectivity of nanosensor is initiated by their large surface-to-volume ratio, high reactivity, size-dependent properties, and high degree of functionalization (Borah et al. 2015). For surface state, covalent functionalization, organic ligand, and nanocomposite formation have large contribution to improve response selectivity and sensitivity in heavy-metal detection. The nanomaterials involved in chemical sensors have greatly enhanced their reproducibility and detection limit for selective determination of heavy metal (Kaur et al. 2015) (Buledi et al. 2020). Generally, electronic and optical properties of nanomaterials are highly considered to increase selectivity and sensitivity.

In addition, nanomaterials used in sensor fields have many advantages, such as ultra-high specific surface areas, easy functionalization, abundant active sites, and tunable electronic structure. Therefore, they are promising building blocks for constructing various sensors with excellent performances. The various types of sensors are including electrochemical sensors, fluorometric sensors, colorimetric sensors, electrochemiluminescence (ECL) sensors, photoelectrochemical sensors, and field effect transistor (FET)

sensors (Gan et al. 2018). In this review, many scientists globally were reported for colorimetric sensor silver (Ag)-based nanomaterials due to solid limited surface plasmon resonance absorption and interparticle distance, which affect to the optical properties. The colorimetric detection method has numerous advantages including efficient time and speed detection, high affectability, cost-viability, and user friendly. The surface state of NPs plays a essential role in the improvement of sensitivity of colorimetric sensors for heavy-metal particles. For example, AgNPs functionalized surface with small natural ligands to form bio-macromolecules was demonstrated specific colorimetric detection of various heavy-metal particles (Wang et al. 2015).

One of the main causes of our environment's rapid degradation is the overexploitation of natural resources for heavy metals.  $\text{Pb}^{2+}$ ,  $\text{Cr}^{3+}$ ,  $\text{Hg}^{2+}$ ,  $\text{As}^{3+}$ , and  $\text{Cu}^{2+}$  are the major heavy metals that have harmed the environment in recent years. As a result, numerous efforts have been exerted to quantify and detect heavy metals conventionally and analytically. However, advanced technologies are continuously being demanded for the detection of heavy metals in a user-friendly and sensitive manner, which resulted in the development of nano-based technology. Analytical devices, which are very sensitive, selective, and capable of working quickly, have become more effective due to the use of nanotechnology (Shrivastava et al. 2022).

Metals are naturally present in the earth's crust, but their composition and concentrations vary. Heavy metals pose a serious threat to the environment and human health. The rapid rise in heavy metals in the environment over the past ten years is attributable to the rise in mining and industrial activities. Metals can also be released from rocks by weathering, erosion, rainwater, soil, and other natural processes, which can significantly increase the release of toxic metals (Buledi et al. 2020). Mercury has deleterious effects on the human kidney, brain, and central nervous system. This element is volatile and predominantly exists as  $\text{Hg}^{2+}$  in water. The  $\text{Hg}^{2+}$  ion is highly toxic at low concentrations and can accumulate in ecosystems, in particular apex predators, causing several disorders and diseases. Meanwhile, lead (Pb) pollution has been associated with neurodevelopmental effects, and cadmium (Cd) is classified as a carcinogen. Arsenic intake causes dermal lesions, skin cancers, bladder, and lung cancers (Mensah et al. 2021, Li et al. 2013).

Mensah et al. (2021) reported efforts exerted for the improvement of the environment affected by heavy metals in water. Different inorganic NPs, including metals, metal oxides, and metal sulfides NPs, have been applied successfully as nanoadsorbents for the treatment of water with high contaminations of heavy metals, that is, at concentrations greater than  $100 \text{ mg L}^{-1}$ , achieving high adsorption capacities up to  $3449 \text{ mg g}^{-1}$ . The synthesis method, selectivity, stability, regeneration and reusability, and adsorbent

separation from solutions are critical parameters that determine the quality of inorganic nanoadsorbents. Surface-functionalized nanoadsorbents possess high selectivity and capacity for heavy-metal removal from water at very low adsorbent dosages of less than  $2 \text{ g L}^{-1}$ , which make them better than conventional adsorbents in terms of environmental remediation.

Thus, we underscore the uses of AgNPs in sensors of heavy metals (Fig. 1), such as  $\text{Pb}^{2+}$ , copper ( $\text{Cu}^{2+}$ ), manganese ( $\text{Mn}^{2+}$ ), and mercury ( $\text{Hg}^{2+}$ ). In this review, we specifically addressed the previously reported AgNPs for heavy-metal sensors with recent updates.

## Materials and methods

### AgNP synthesis methods


#### Synthesis of AgNPs using bottom-up approaches


As mentioned above, numerous types of silver nanostructures with distinctive properties have been used in various sensor applications, especially those regarding heavy metals (Lee and Jun 2019). The union of NPs has been utilized in

three distinct methodologies, including physical, chemical, and biological strategies. The physical and chemical synthesis methods, which point toward controlling the actual properties of particles, are presently utilized to create metal NPs.

The synthesis methods of metal NPs are mainly divided into top-down and bottom-up approaches (see Fig. 2) (Kalishwaralal et al. 2010). Method “top-down” is the mechanical crushing of mass metals with the resulting adjustment of the utilized colloidal NPs (Tao et al. 2006). Top-down approaches disincorporate bulk materials to generate the required nanostructures. These include physical and chemical synthesis methods. The physical synthesis of AgNP includes the evaporation–condensation approach and laser ablation technique. Both approaches can be used to synthesize large quantities of AgNPs with high purity and without the use of chemicals that release toxic substances and jeopardize the human health and environment. However, agglomeration is often a great challenge because capping agents are not used. In addition, both approaches consume high power and require relatively long synthesis duration with complex equipment, over all increase their operating cost (Lee and Jun 2019). The laser wavelength, time span of laser pulses, laser influence, ablation time duration, and effectual liquid medium with or without the surfactant are

**Fig. 1** Schematic representation of AgNP applications for heavy-metal sensors

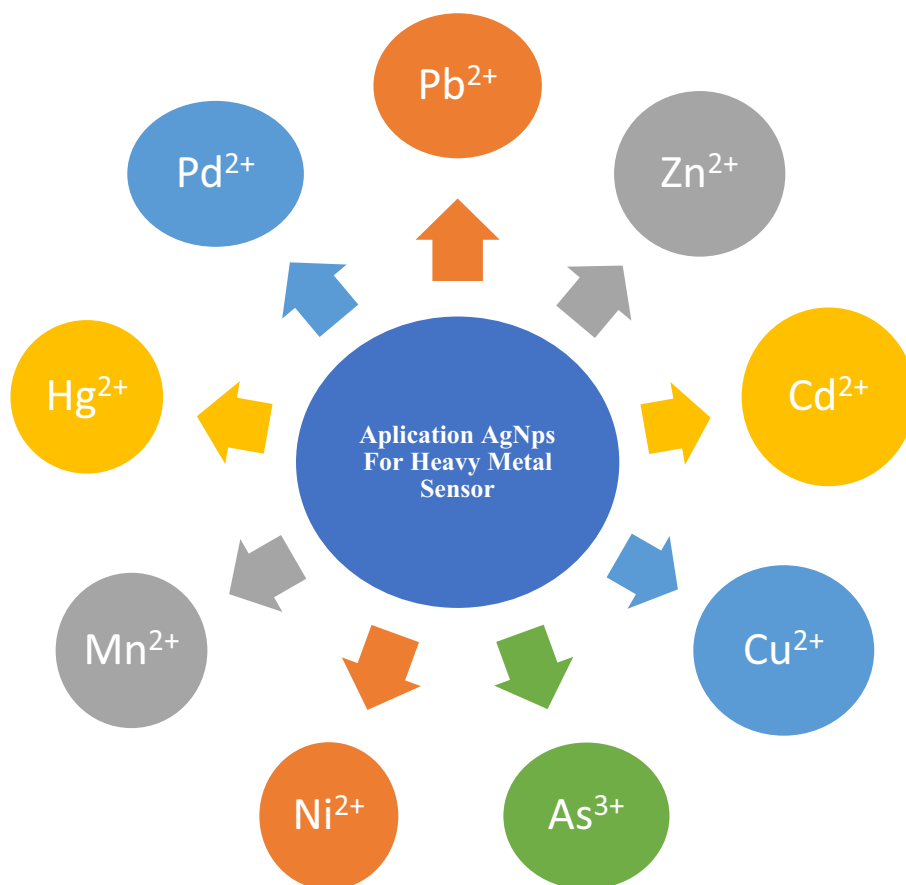

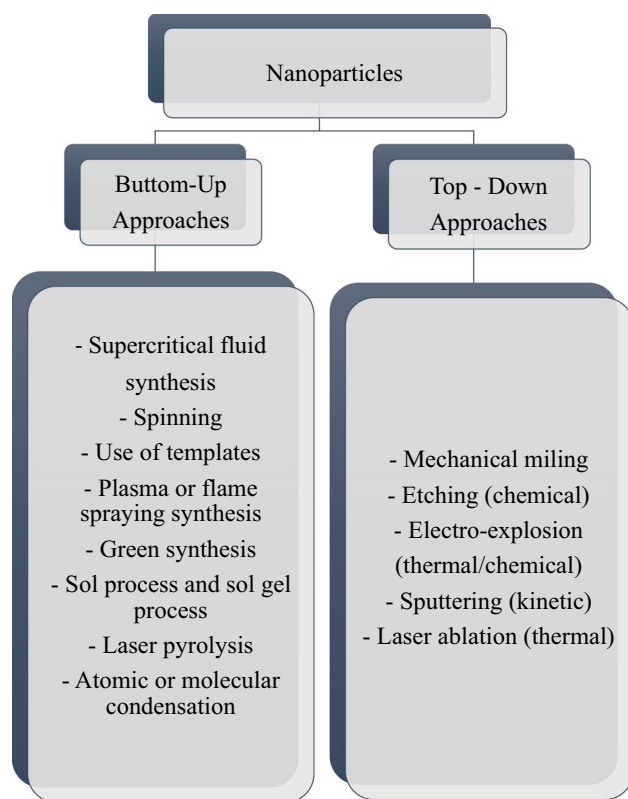

**Fig. 2** Schematic illustration of two different routes in AgNP synthesis

the major parameters that influence the synthesized particles when using the laser ablation method (Shyam et al. 2020).

The AgNP synthesis is mainly achieved through chemical methods. Sodium borohydride, hydrazine hydrate, sodium citrate, and lithium aluminum hydride are the most commonly used reducing agents. Silver atoms ( $\text{Ag}^0$ ) are formed due to the reduction of  $\text{Ag}^+$  containing complexes, which may lead to the cluster formation due to agglomeration. Colloidal Ag particles emerge from these clusters. To avoid such issue, scientists use protective or capping agents (Shyam et al. 2020).

Different chemical and physical techniques, e.g., electrochemical strategy (Singaravelan and Bangaru Sudarsan Alwar 2015), phytochemical method (Narchin et al. 2018), and laser ablation (Ma 2019), have been utilized to combine AgNPs. The area of green synthesis has been investigated to use fundamental phytochemicals, such as amides, aldehydes, alkaloids, flavonoids, phenols, ketones, carboxylic acids, and ascorbic acids (Buledi et al. 2020).

### Synthesis of AgNPs using top-down approaches

Figure 2 shows top-down methods, NPs are normally synthesized by evaporation and condensation and breakdown of bulk materials into fine particles via size reduction

using various lithographic techniques, e.g., grinding and milling (Khan et al. 2018a, b). This group includes the green synthesis method, which uses microorganisms or plants extracts. An intelligent strategy should be scaled up and climate friendly, combine great scope, and not require the use of toxic synthetic compounds. The green synthesis of NPs may be a granular perspective where the most response observed is drop. Biogenic incorporation is beneficial because of its natural reduction effect and the use of multiple physicochemical manufacturing methods. The unintentional production of large NPs free of impurities, size, and morphology has been reported by Gupta and Chauhan (2017).

In this regulatory race for AgNPs, the green biomimetic synthesis of plant-mediated AgNPs is considered the best innovation for the rapid manufacture of AgNPs, effectively meeting the extreme needs and interests of today's market and drives a decline in the business or aging of substances harmful to the environment, human well-being, and climate. Water hyacinth plant leaf extract was used for the colorimetric sensing of heavy metals (Zannotti et al. 2020); green synthesis was utilized to separate heavy metals from khat (*Catha edulis*) plant and effective in the detection of  $\text{Hg}^{2+}$  particles (Wang et al. 2015).

In addition, green synthesis principles put forward the need to evolve environmentally technologies for the fabrication of nanomaterials. The biosynthesis of NPs, which is the combination of nanotechnology and biotechnology, has gained interest. Abundant reactants and starting materials used in chemical method reactions are toxic and potentially hazardous. Biomimetic approaches have been developed due to the increasing environmental concerns over harmful chemical methods. Green methods principles forced researchers to develop strategies involving biological methods where enzymes, microorganisms, and plant extract play a vital role in NPs formation. The biologically synthesized NPs exhibit tremendous interdisciplinary applications (Shyam et al. 2020).

NPs are created physically and chemically within a significant time frame. However, late advancements showed the primary job of microorganisms and biological systems occurring with metal NPs (Fig. 3).

As depicted in Fig. 3 and more detail can be seen in Table 1, metallic NPs can be obtained from cell or cell-free extracts of a variety of biological resources. The evaluation of NP preparation against green synthesis principles (see Table 1), such as the selection of a solvent medium, eco-friendly reducing agent, and nontoxic material for NPs stabilization, is the most important consideration. Plant extract reduces metal ions within a shorter period than microbial NPs, making plant-based NPs more stable and monodispersed. Microbial synthesis is one of the methods used for nanomaterial production (Kumar et al. 2020).



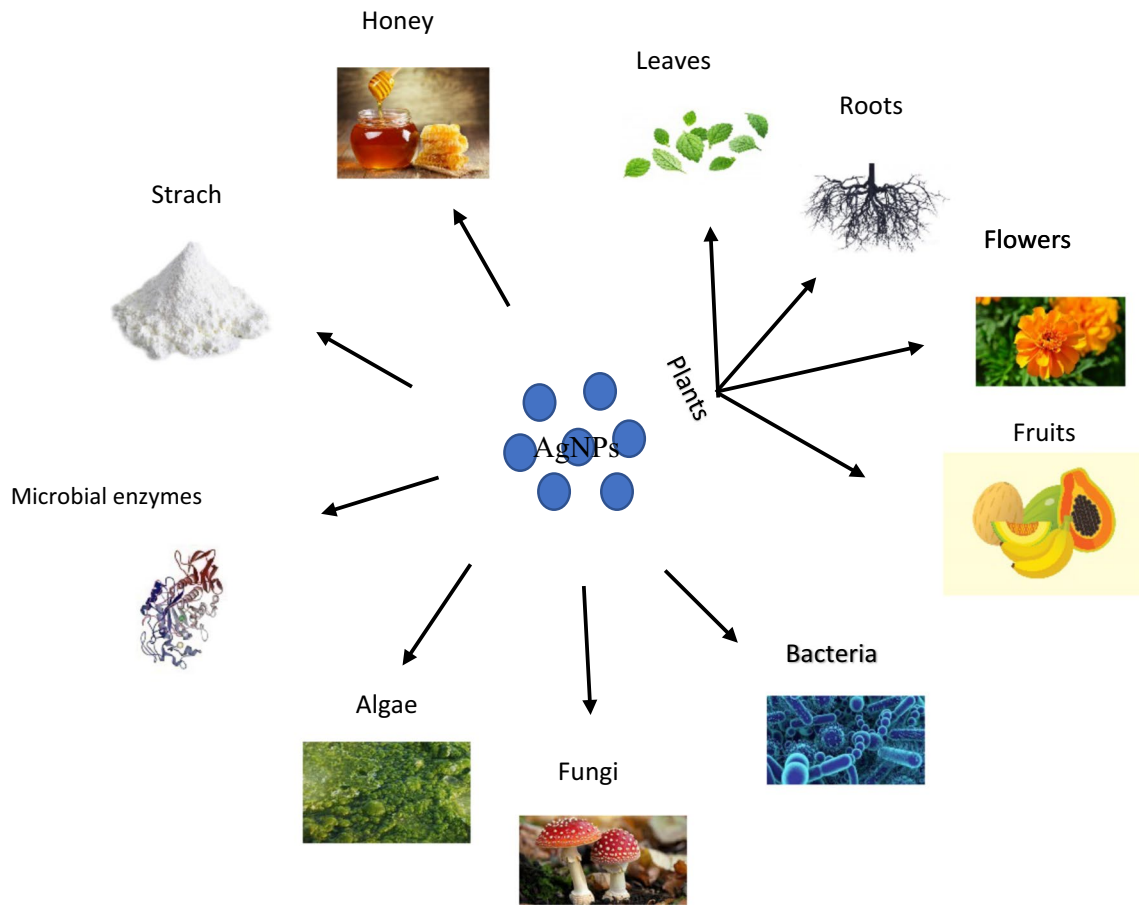


Fig. 3 Various types of green synthesis sources utilized for the arrangement of AgNPs

Table 1 Section green synthesis of AgNP detection of heavy metals

Metal NPs	Sources	Sources type	Heavy metal detection	References
AgNPs	Fruits	Watermelon ( <i>Citrullus lanatus</i> )	Hg (II)	(Firdaus et al. 2021)
		Kokum fruit extract	Hg <sup>2+</sup>	(Sangaonkar et al. 2020)
		Durenta erecta ( <i>D. erecta</i> )	Cr <sup>6+</sup>	(Ismail et al. 2018)
	Flowers	Mango ( <i>Mangifera indica</i> )	As <sup>3+</sup>	(Kolya et al. 2020)
		<i>Moringa oleifera</i>	Cr (II)	(Bindhu et al. 2020)
	Roots	<i>Bistorta amplexicaulis</i>	Hg <sup>2+</sup> Pb <sup>2+</sup>	(Ahmed et al. 2020)
	Leaves	<i>Hyacinth</i>	Hg <sup>2+</sup>	(Oluwafemi et al. 2019)
		<i>Acacia chundra</i>	Hg <sup>2+</sup>	(Anto Judy et al. 2021)
		<i>Lantana camara</i>	Hg <sup>2+</sup> Cu <sup>2+</sup> Pb <sup>2+</sup> Mn <sup>2+</sup>	(Aritonang et al. 2021)
	AgNPs	Bacteria	<i>Staphylococcus sciuri</i>	Cd
Fungi		<i>E. coli</i>	Fe <sup>3+</sup>	(Princy et al. 2022)
Algae		<i>Porphyra yezoensis</i>	Cu <sup>2+</sup>	(Xu et al. 2019)
Strach		<i>polyvinylpyrrolidone</i>	Hg (II)	(Al-Onazi and Abdel-Lateef 2022)

## Results and discussion

### Applications of AgNP in heavy-metal sensors

The chemical symbol of silver, Ag, comes from the Latin word “argentum,” which means “shiner” in proto-Indo-European. Silver is white, belongs to the noble element family, and has an atomic number of 47. AgNPs are an ideal candidate for a wide range of applications, including nanomedicine, nanobiotechnology, nanosensors, and electronic devices, due to their outstanding physicochemical properties and capability to exhibit surface plasmon resonance (SPR). Given their outstanding properties and low cost of preparation, AgNPs attracted considerable attention in the field of sensor technology from an environmental standpoint (Hyder et al. 2022). Heavy metals are delegated ecological toxins because they cause harmful impacts on living organic entities, including creatures, people, and plants. These metals persevere in the environment because they cannot be obliterated nor corrupted. The contamination by risky heavy-metal-based particles has been an expanding issue. Metal materials cause different medical conditions, such as those observed in the hematopoietic, gastrointestinal, kidney, and sensory systems (Duffus 2002).

Multiple detection technologies for the detection of heavy metals have been developed. Several analytical methods, including atomic absorption spectroscopy (AAS) (Tinas et al. 2018), have been used to monitor trace amounts of heavy metals in the environment. These methods include electrochemistry and atoms (Dali et al. 2018), voltammetry stripping (Luo et al. 2017), and ultraviolet-visible and fluorescence spectrometry (Zhao et al. 2017). These methods provide correct and accurate results, but they require a long operation time, skilled staff, expensive instruments, and proper handling. Therefore, a straightforward and delicate colorimetric method that effectively detects the target material by observing the change in color can be used to definitively address these issues (Zhai et al. 2019). Such a method can also be used in organic pesticides (Tang and Sun 2018) and biomolecules (Hyder et al. 2021). Given that metal NPs have a large surface area, excellent optical properties, and high molar absorptivity and can be customized with a variety of stabilizing and capping agents, many metal NPs, including gold, silver, and copper can be used extensively for this purpose (Hyder et al. 2022).

These days, our current circumstance is the progressive manifestation of substantial metal poisons because of current farming practices and fast industrialization (Jumina et al. 2020). Regulatory authorities will decide essential standards for the safe consumption of these heavy metals.

Table 2 provides a list of different global and national regulatory authorities who determine and regulate these standards for the safe consumption of drinking water. The list also highlights the difference in threshold limits due to geographical variation and consumption limits of different populations in terms of drinking water (Shrivastava et al. 2022).

Given their great catalytic potential and reactivity, strong adsorption potential, and large surface area, nanomaterial-based colorimetric sensors have presented considerable promise in the detection of heavy metals in recent years. Various nanomaterials, specifically metal NPs, have been employed to construct distinctive types of colorimetric sensors for sensing of heavy metals. The improved selectivity and sensitivity of colorimetric nanosensors originates from their high degree of functionalization, great volume-to-surface ratio, size-dependent features, and high reactivity (Rasheed et al. 2022).

AgNPs' localized surface plasmon resonance (LSPR) properties contributed significantly to the field of colorimetric sensing as shown in Fig. 4. Although the stability of metal NPs is a major obstacle to their use in colorimetric heavy-metal sensing, different capping and stabilizing agents have been used to functionalize the metal surface of metal NPs. These capping agents prevent NPs from aggregating and increase their activity (Hyder et al. 2022).

### Sensing of Mercury (Hg)

Mercury is a hazardous toxic material that can pollute the environment and is one of the most dangerous heavy-metal particles in metallic, inorganic, and natural forms (Wang et al. 2015). It is a common contaminant emitted from coal, gold mining companies, and volcanic emissions. Therefore, proficient procedures must be developed to enable the rapid observations of mercury in liquid frameworks (Yu and Tseng 2008).  $\text{Hg}^{2+}$  is very stable and quickly accumulates in water bodies. It can be released to the surface and groundwater due to various industrial or natural activities, such as fossil fuels (especially from thermoelectric power plants), volcanic emissions, and agriculture (Abou El-Nour et al. 2010; Sharma et al. 2009). Water-soluble  $\text{Hg}^{2+}$  particles are one of the most stable and typical inorganic mercury compounds. In shallow conditions, this element can cause complicated issues in the regenerative, gastrointestinal, and cardiovascular systems (Şahin et al. 2020).

$\text{Hg}^{2+}$  is harmful and can cause unfavorable impacts on human well-being and climate. Thus, numerous effective logical methodologies, including fluorescence spectrometry, have been created to enhance  $\text{Hg}^{2+}$  sensing. Colorimetric tests, electrochemical investigation, mass spectrometry (MS), and nuclear ingestion spectrometry. Although these strategies are sensitive and selective, they still have a few



**Table 2** Maximum permissible limits of various heavy metals according to different regulatory authorities

Heavy Metal	WHO (mg L <sup>-1</sup> )	EPA (mg L <sup>-1</sup> )	FSSAI (mg L <sup>-1</sup> )	CODEX (mg L <sup>-1</sup> )	EU (mg L <sup>-1</sup> )	FDA (mg L <sup>-1</sup> )	Associated Health Risk	Reference
Hg	0.001	0.002	0.001	0.001	–	–	Tremors Insomnia and memory loss Kidneys	(Mukherjee et al. 2021), (Shrivastava et al. 2022)
Cd	0.003	0.005	0.003	0.003	0.005	0.005	Nausea, vomiting, and diarrhea Muscle cramps Salivation Liver injury	
As	0.01	0.01	0.05	0.01	0.01	0.01	Encephalopathy Thickening of the skin Diarrhea and heart disease	
Pb	0.01	0.015	0.01	0.01	0.01	0.005	Anemia and seizures Behavioral problems Intellectual disability	
Cr	0.05	0.1	0.05	–	0.05	0.100	Depression Anxiety and schizophrenia Kidney and liver diseases	
Cu	2	1.3	1.5	–	2.00	1.000	Vomiting Hematemesis, Hypotension Melena (black “tarry” feces)	
Ni	0.07	0.04	1.5	–	0.02	0.1	Chronic bronchitis Reduced lung function Allergy	

*FSSAI* food safety and standards authority of India; *WHO* world health organization; *CODEX* codex alimentarius commission, a body under Joint FAO/WHO food standards program in Rome; *EU* European union; *USFDA* United State food and drug administration; *EPA* environmental protection agency

restrictions, such as being time-consuming and requiring the use of modern sample treatment, complex and costly instrumentation, or inapplicability in situ investigation. Accordingly, the advancement of a substitute productive, straightforward, and rapid insightful strategy for sensitive and selective recognition of Hg<sup>2+</sup> is attracting the attention of researchers (Hao et al. 2020). Synthesis nanoparticles are shown to be used to develop new color sensors to detect Hg<sup>2+</sup> ions selectively and easily in different media (Ullah et al. 2022).

AgNPs have drawn incredible attention for Hg sensor enhancement mainly because of their sensitivity, which affects micro-level Hg<sup>2+</sup> concentration fixation changes. This conduct is related to the redox science of Hg<sup>2+</sup> and Ag surface and the delicate science among metals and sulfur-containing capping agents used for AgNPs. In the two cases, the presence of Hg produces significant changes in the absorbance intensity and peak position of AgNPs. Surface influence plays the most important part in the stabilization and reactivity of AgNPs. Hence, ligand surface



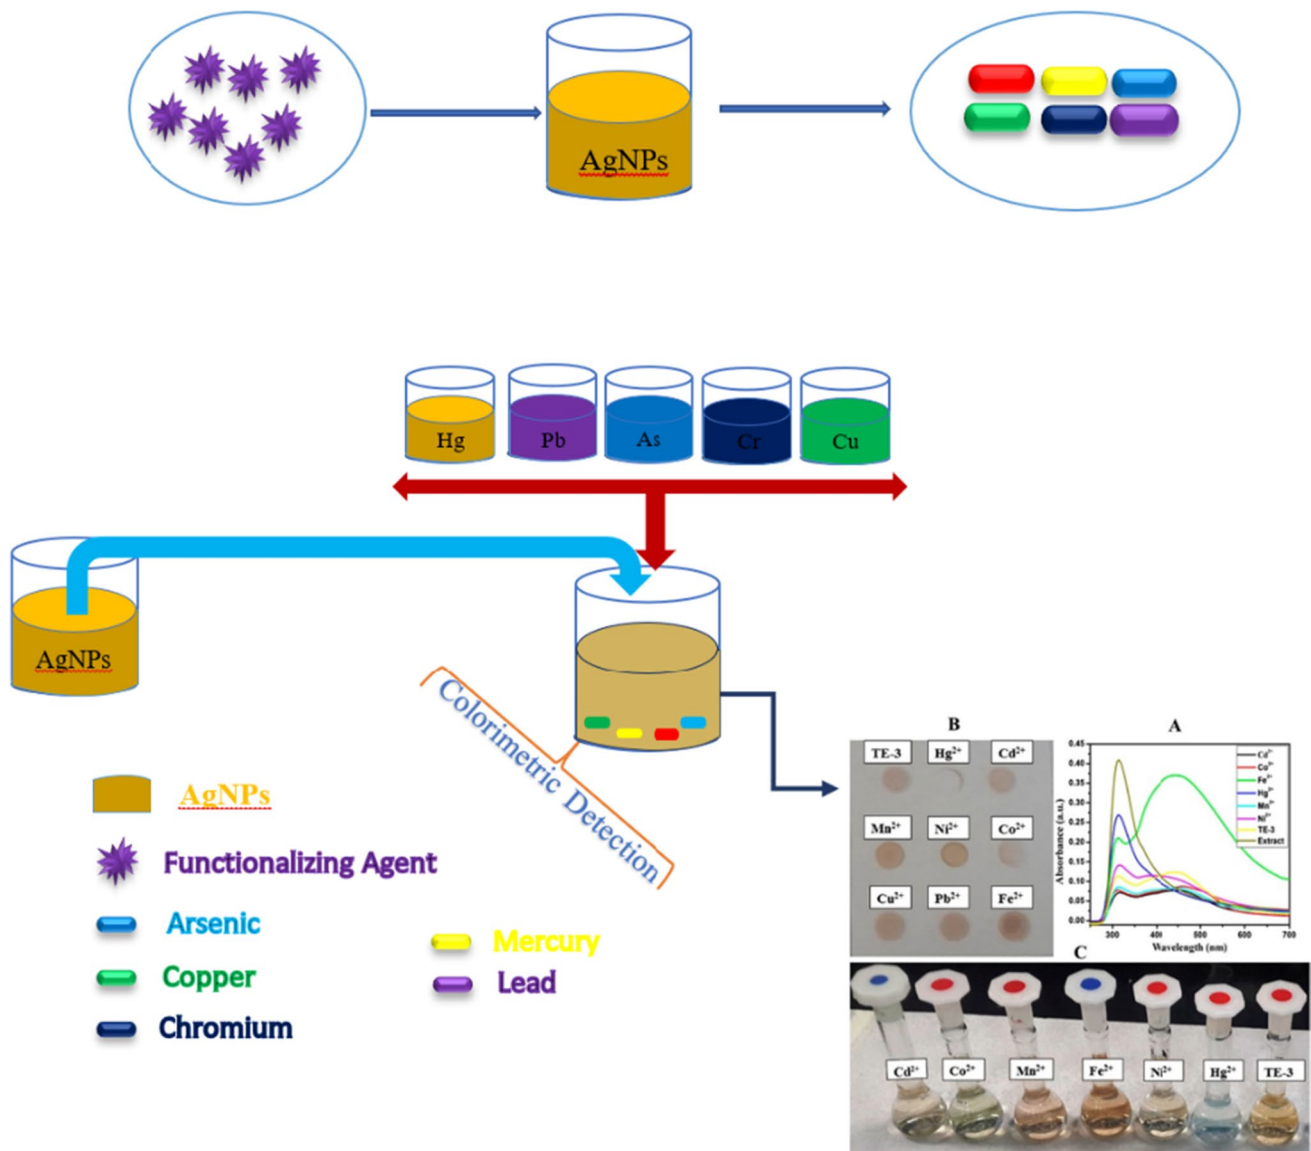


Fig. 4 Colorimetric sensing of heavy metal by AgNPs (Hyder et al. 2021; Kalam et al. 2018)

chemistry is used to tune their sensing properties (Zannotti et al. 2020).

Methyl mercury ( $\text{CH}_3\text{Hg}^+$ ) is another form of Hg that bioaccumulates in inorganic tissues, poisoning the food chain (Mensah et al. 2021). Hg readily methylates to form the extremely toxic  $\text{CH}_3\text{Hg}^+$  (Liu et al. 2022).  $\text{CH}_3\text{Hg}^+$ , as the most toxic species of Hg, accounts for 95% of organic Hg and is of particular concern due to its bio amplification factors (106 – 107) in aquatic organisms via the food chain. Among Hg species,  $\text{Hg}^{2+}$  is only lower than  $\text{CH}_3\text{Hg}^+$  in toxicity and can be converted into  $\text{CH}_3\text{Hg}^+$  under anaerobic conditions in biological systems. Hence, different Hg species must be determined in addition to the total Hg to evaluate its toxicity in the environment (Zheng et al. 2018).

Consequently, surface ligands produce various properties and limitations of NPs, which will aggregate or disaggregate and cooperate with components and particles present in their environment. Surface ligands influence the detection against metal particles, such as the altered selectivity and sensitivity of  $\text{Hg}^{2+}$ . Thus far, a limited number of studies reported the colorimetric identification of  $\text{Hg}^{2+}$  particles utilizing green synthesized unmodified AgNPs in liquid media. Numerous biomaterials from various plants, fruits, and leaves are utilized for the photoinduced green synthesis of AgNPs. A biomaterial was added as a stabilizing agent and applied in  $\text{Hg}^{2+}$  detection (Proposito et al. 2019). Citrus extracts from gum kondagogu, which are frequently used to decrease/settle the level of AgNPs, were applied as a direct colorimetric



sensor for the sensitive discovery of  $\text{Hg}^{2+}$  (Rastogi et al. 2014).

### Sensing of Manganese (Mn)

Manganese is one of the significant resources, with more than 90% being used in the steel industry. China is the largest electrolytic metal Mn maker, producing approximately 1.40 million tons every year and representing over 97.0, paying little heed to the worldwide supply. In 2018, 49 electrolytic Mn metal ventures were recorded in China, with a limit of 2.26 million tons. Mn is one of the necessary minor components in the body, with functions involved in bone transformation phenomena, lipids, amino alkanolic corrosion, and carbohydrate metabolism. The average intake of Mn is in the range of 2 and 9 mg/day (for a mean 70 kg individual). Ordinarily, the brain contains a small amount of Mn, and the insufficiency and excess amount of Mn fundamentally influence its capacity (Nie et al. 2017).

Nonetheless, exaggerated exposure to Mn may cause manganese. An inebriated individual may suffer from depression, disposition swings, enthusiastic practices, and psychosis. Consequently, several optical methods for  $\text{Mn}^{2+}$  detection have been reported: AAS, inductively coupled plasma–atomic emission spectroscopy (ICP–AES), and ICP–MS. However, the significant parts of them require refined hardware and modern strategies, making them time-consuming and inconvenient to use. In this regard, the sensitive, selective, and straightforward detection procedure for detection of  $\text{Mn}^{2+}$  remains fundamental (Hu et al. 2014).

A few scientific methods for the detection of  $\text{Mn}^{2+}$  have been reported: ICP spectroscopy, AAS, and ICP–AES. Nevertheless, these methods need complex systematic processes and expensive equipment, making them inconvenient and time-consuming (Zhou et al. 2012). Colorimetric methods, which include unprecedented effects on the applications for metal ions, have drawn attention.

To date, different colorimetric sensors have been used for functional metal NPs. AgNPs are incredibly appealing due to their optical, electrical, and synthesis properties, especially in the field of location with detection. In addition, they will occasionally be perceived with unaided eyes for certain purposes. A fundamental disadvantage of the abovementioned methods is their sensitivity; accordingly, the sensitivity of a colorimetric sensor for detection can be developed (Hu et al. 2014).

### Sensing of Lead (Pb)

The heavy-metal pollution in the air, soil, and water is a significant issue and a developing danger for the humankind and the environment. The sources of heavy-metal contamination in the environment are petroleum, paper, plastic, coal,

and color enterprises. Certain metals, including Pb, Cu, Hg, and Cd particles, show toxicity in trace amounts. Pb is the second most toxic substance because of its wide use. Pb has been applied as an additional substance in fossil fuel, paint shades, electric stockpiling batteries, building development, projectiles, shot patch, and pipes (Cheon and Park 2016).

$\text{Pb}^{2+}$  is an exceptionally toxic heavy-metal ion that can cause genuine environmental and medical issues but is universally used in industries. Broad investigations have demonstrated that people, particularly youngsters, can experience extremely durable neurological harm and brokenness when displaying low blood levels of Pb. Until this point, no protected limit for Pb exposure has been recognized. In the brain, Pb-instigated harm in the prefrontal cerebral mantle, hippocampus, and cerebellum can cause the spread of neurologic problems. At the atomic level, Pb ions meddle with the administrative activity of calcium in cellular processes and disturb an assortment of intracellular biological activities (Noh et al. 2015).

The WHO suggested the value of  $0.01 \text{ mg}\cdot\text{L}^{-1}$  as the most significant restriction of  $\text{Pb}^{2+}$  in drinking water. Low-level Pb exposure can cause neurological, conceptive, cardiovascular, and formative problems, kidney harm, muscle loss of motion, cognitive decline, and anemia (Cheon and Park 2016).  $\text{Pb}^{2+}$  is a risky metal material and a prominent eco-sphere modern pollutant. It has been pronounced as such because of the basic peril it imposes, particularly in non-industrial nations worldwide. Human bones and delicate tissues can accumulate  $\text{Pb}^{2+}$ , which results in human organ debilitations; at an excessive level, such a condition will cause the body to terminate. Thus, the quantity of such poisonous metal particles in liquid conditions must be determined. Such a step is likewise essential in most applications, such as natural observation, control of normalized water quality, and reuse of water contaminated with  $\text{Pb}^{2+}$  (Khan et al. 2018a, b).

In this way, effortless strategies for the monitoring of  $\text{Pb}^{2+}$  levels in the environment are gaining significance. A sensitive method for the regular and adequate estimation of the  $\text{Pb}^{2+}$  concentration is critical in environmental assessment. Up to this point, the spread of scientific methods, including AAS, ICP–MS, fluorescence, and electrochemical methods, has accounted for the determination of  $\text{Pb}^{2+}$  particles. However, most of these procedures require complex instrumentation and general prepared settings. Henceforth, the advancement of a precise, quick, and helpful analytical method for the detection of  $\text{Pb}^{2+}$  remains a challenge for physicists (Noh et al. 2015).

### Sensing of Copper (Cu)

Many heavy metals in the environment, climate, and living systems affect directly or indirectly the biota and humankind.



Cu is the third fundamental metal that causes changes in human bodies. However, the over-administration of Cu can harm the liver and kidney, expand imperative symptoms and respiratory rates, and damage the focal systema nervosum. Although Cu is a significant element, its concentration affects the physical body. Its bioaccumulation causes oxidative pressure and neurodegenerative infections. Thus, the WHO suggests that a close to  $2 \text{ mg L}^{-1}$  Cu concentration be permitted in beverages (Flores et al. 2017).

$\text{Cu}^{2+}$  is a cation causing sizable fundamental changes in far-reaching industrial applications, such as in biological fields.  $\text{Cu}^{2+}$  additionally acts as a reactant cofactor in numerous metalloenzymes, including superoxide dismutase and tyrosinase. The insufficiency of  $\text{Cu}^{2+}$  may cause a few perilous illnesses. A high measure of  $\text{Cu}^{2+}$  inside the body can cause extreme conditions, such as gastrointestinal confusion to liver or kidney harm. Consequently, the specific detection of  $\text{Cu}^{2+}$  is an environmental and biological concern (Iftekhhar et al. 2021).

Several developed methods have been broadly applied for the detection of  $\text{Cu}^{2+}$  particles; these methods include electrochemical sensing (Flores et al. 2017), ICP–AES (Shoae et al. 2012), and fluorescence analysis (Zhang et al. 2014). Fluorescence analysis has drawn expanding consideration because of its simplicity, minimal expense, high sensitivity, and selectivity. Moreover, these methods are inconceivably requesting and sensitive and include high working expenses, time-consuming pretreatment cycles, and considerable preparation for test sample analysis (Iftekhhar et al. 2021). Therefore, fluorescent sensors for detecting  $\text{Cu}^{2+}$  have caught the interest of researchers. Together with fluorescent probes, NPs have raised an extensive scientific interest because they need to be generally applied inside the detection field for most analyses (Xu et al. 2019).

## Sensing of Chromium (Cr)

Chromium is one of the essentially bountiful components usually present in earth, in the outside layer of rocks, soils, silt, and plants. In nature, the chromite metal [ $\text{FeCr}_2\text{O}_4$ ] has two oxidation states: the trivalent ( $\text{Cr}^{3+}$ ) and hexavalent ( $\text{Cr}^{6+}$ ) forms. The oxidation states vary in terms of their accessibility and harmfulness. Between Cr (VI) and Cr (III), the essential one is more poisonous considering its high solvency and portability in natural frameworks. Cr is expansive because of the applications in arranged enterprises, such as materials, color, calfskin, substance assembly, and metal finishing (Sharif et al. 2015).

Cr provides a quick result on physiological capacities and helps deal with the conventional digestion of different food sources, such as starch, protein, nucleic acids, and fat, and a critical ultra-follow supplement in the eating routine of people and creatures (Chamaraja et al. 2021). Low-level  $\text{Cr}^{3+}$  is

significant for ordinary physiological function. In this manner, a conspicuous part participates in lipid, protein, macromolecule, and glucose resistance digestion in humans. High convergences of Cr inside the body reach the DNA and break down tissue cells. Notwithstanding Cr's hazardous nature, different modern exercises consistently add Cr species to the environment, causing Cr contamination (Sharif et al. 2015).

$\text{Cr}^{6+}$  is a solid oxidizer that has a relationship with infections and the Cr content in human tissues and organs. Thus, it has been associated with certain medical problems, including persistent gastroenteritis, dermatitis, cancer, and septum perforation (Yokota et al. 2019). Cr ions are generally used in various economic applications, such as chrome plating, shade creation, calfskin tanning, passing on, landfill filtering, and impeccable handling.  $\text{Cr}^{6+}$  ions are prevalent in the environment and may be detected in normal water because of their vast scope of use in different industries (Kanagaraj et al. 2017).

Different novel nanotechnology-based colorimetric tests, including those dependent on label-free AgNPs (Elavarasi et al. 2014) and AgNPs capped with tartaric acid (Shrivasa et al. 2019), have been conducted for the detection of  $\text{Cr}^{6+}$  particles. However, scientific methods utilizing changed NPs have shown restricted selectivity and sensitivity in the detection of  $\text{Cr}^{6+}$  ions. For more detail about type of heavy metal detection, limit of detection (LOD) based on functionalizing agent, linear range, and particle size from various reference clearly can be seen in Table 3. The particle size of NPs was usually determines using transmission electron microscope (TEM) or scanning electron microscope (SEM), and crystallite size by quantitatively analysis of X-ray diffraction (XRD) spectra (Ilyas et al. 2019), (Ilyas et al. 2021), (Tahir et al. 2021).

## Challenges and future prospects

Over the past few decades, heavy-metal toxicity has become a serious threat to humans and the environment. Heavy metals are evident entities that have the potential to cause several dangerous health risks due to their long half-life, potential accumulation in various parts of the body, and non-biodegradability (Abdelsattar et al. 2022). Sensor-based methods for the detection of heavy/toxic metals have been developed.

AgNPs have emerged as promising nanotools for the detection of heavy metals. Their solidness, similarity to liquid media, simple surface functionalization, and scaling down has favored their application in detection and recognition, in contrast to the utilized traditional method. AgNPs give a formative stage to attainable and practical examination by conquering the typical procedures that incorporate extended conventions and refined instrumentation.

In the future, the research of nanocomposites and multifunctional NPs for heavy-metal sensors in the environment

**Table 3** Performance of AgNPs with various functionalizing agents as a sensor for the detection of heavy metals using certain characteristics and synthesis methods

Metal	Functionalizing agent	Particle size (nm)	Linear range	LOD	Synthesize method	Analysis method	Reference
Hg <sup>2+</sup>	Unmodified Ag NPs	–	25 × 10 <sup>-9</sup> –500 × 10 <sup>-9</sup> M	17 × 10 <sup>-9</sup> M	–	Colorimetric	Wang et al. (2010)
	Unmodified Ag NPs	–	10 <sup>-10</sup> × 10 <sup>-6</sup> M	2.2 × 10 <sup>-6</sup> M	Green synthesis	Colorimetric	Farhadi et al. (2012)
	Dendrimer-stabilized Ag NPs	12.1	0.01–10 ppm	–	Chemical	Colorimetric	Yuan et al. (2013)
	Citrate-Ag NPs	65.23	–	90.9 × 10 <sup>-12</sup> M	Chemical	SERS	Ren et al. (2012)
	Small gel-Ag NPs	5.0	0.50–800 × 10 <sup>-9</sup> M	0.125 × 10 <sup>-9</sup> M	–	Colorimetric	Sun et al. (2014)
	4-mercaptopyridine-Ag NPs	–	1–100 × 10 <sup>-9</sup> M	0.34 × 10 <sup>-9</sup> M	Physical	Vibrational spectroscopic	Chen et al. (2014)
	Cysteine-Ag NPs	–	–	1 × 10 <sup>-12</sup> M	Chemical	SERS	Wang et al. (2010)
	Polymethacrylic acid-Ag NPs	20	10 × 10 <sup>-9</sup> –20 × 10 <sup>-9</sup> M	< 10 × 10 <sup>-9</sup> M	Hydrothermal	Colorimetric	Liu et al. (2013)
	L-Tyrosine-Ag NPs	13	1–300 × 10 <sup>-9</sup> M	53 × 10 <sup>-9</sup> M	Green synthesis	Colorimetric	Annadhasan et al. (2014)
	Neem leaf extracts Ag NPs	20	0–140 × 10 <sup>-6</sup> M	< 1 × 10 <sup>-6</sup> M	Green synthesis	Colorimetric	Karthiga and Anthony (2013)
	Unmodified Au–Ag NPs	–	0.1–1.0 × 10 <sup>-6</sup> M	5.0 × 10 <sup>-9</sup> M	Chemical	Colorimetric	Li et al. (2014)
	Gln-His-Ag NPs	~ 10	1.0–500 × 10 <sup>-6</sup> M	0.9 × 10 <sup>-6</sup> M	Chemical	Colorimetric	Buduru et al. (2017)
	Citrate/L-cysteine AgNPs	2	–	3.0 × 10 <sup>-6</sup> (0.6 ppm)	Chemical	–	Proposito et al. (2019)
	Gelatin /AgNPs	23	0.14–0.5 mg L <sup>-1</sup>	64.9 nM	Chemical	Colorimetric	Zannotti et al. (2020)
	Unmodified AgNPs	8.6	1.25 pM–125 nM	25 nM	Chemical (drop casting)	Colorimetric	Jeevika and Shankaran (2014)
	<i>Durio zibethinus</i> /AgNPs	97.37	10–50 nm	0–33 μM	Green synthesis	Colorimetric	Sengan et al. (2018)
	AgNPs/ MBO	~ 20	0–835 ppt	9.2 pM	Chemical	Colorimetric	Bhattacharjee et al. (2018)
	AgNPs/ MBI	~ 20	0–2760 ppt	46 pM	Chemical	Colorimetric	Bhattacharjee et al. (2018)
	AgNPs/ MBT	~ 20	0–3294 ppt	92 pM	Chemical	Colorimetric	Bhattacharjee et al. (2018)
	AgNPs/ 2-aminopyrimidine-4,6-diol	18	10–50 μM	0.35 μM	Chemical	Colorimetric	Prasad et al. (2018)
	AgNPs/ starch	15.4 ± 3.9	4.5–2500 nM	4.5–2500 nM	Physical	Colorimetric	Vasileva et al. (2017)



**Table 3** (continued)

Metal	Functionalizing agent	Particle size (nm)	Linear range	LOD	Synthesize method	Analysis method	Reference
Pb <sup>2+</sup>	PVA/ AgNPs	–	0.2–1.4 ppm	0.1609 mg L <sup>-1</sup>	<i>Green synthesis</i>	Colorimetric	Taufiq et al. (2021)
	1-(2-mercaptoethyl)-1,3,5-triazinane-2,4,6-trione AgNPs	10	0.1–0.6 µg mL <sup>-1</sup>	0.06 µg mL <sup>-1</sup>	Chemical	Colorimetric	Noh et al. (2015)
	Green synthesized-AgNPs	20	0.5–25 µM	0.1 µM	<i>Green synthesis</i>	Colorimetric	Khan et al. (2018a, b)
	Paper-AgNPs/PVA	22.5	241 nM–4.8 µM	96 nM	<i>Green synthesis</i>	Colorimetric	Shrivastava et al. (2019)
	Gluc-Ag NPs	–	9.57 ± 2 nm	0.203 × 10 <sup>-6</sup> M	Chemical	Colorimetric	Choudhury and Misra (2018)
	(AgNPs/ dithizone)	14	0.5–10 µg/L	0.64 µg/L	Chemical	Colorimetric	Roto et al. (2019)
	AgNPs/ 3,4-dihydroxy-L-phenylalanine	20	65–125 µM	81 µM	<i>Green synthesis</i>	Colorimetric	Cheon and Park (2016)
	AgNPs/ L-Tyrosine	17 ± 2	16–100 nM	16 nM	<i>Green synthesis</i>	Colorimetric	Annadhasan et al. (2014)
	AgNPs/ 1-(2-mercaptoethyl)-1,3,5-triazinane-2,4,6-trione	10	1.2–7.3 µM	96.5 nM	Physical	Colorimetric	Noh et al. (2015)
Mn <sup>2+</sup>	AgNPs/ Gluconate	9.57 ± 2	0.5–2.0 µM	0.203 × 10 <sup>-6</sup> M	Chemical	Colorimetric	Choudhury and Misra (2018)
	(TMB)-(PEI)/AgNPs	–	20 nM to 1 µM	1 nM and 200 nM	Chemical	Colorimetric	Zhang et al. (2022)
	4-MBA-MA-AgNPs	–	5 × 10 <sup>-7</sup> mol/L to 1 × 10 <sup>-5</sup> mol/L	50 nM	Chemical	Colorimetric	Zhou et al. (2012)
	Clove-AgNPs	25	0.4–2.0 µM	0.2 µM	Chemical	Colorimetric	Joshi et al. (2016)
	P <sub>3</sub> O <sub>10</sub> <sup>5-</sup> -AgNPs	–	0.05–20 µM	0.1 µM	Chemical	Colorimetric	Gao et al. (2013)
	Na <sub>4</sub> P <sub>2</sub> O <sub>7</sub> -HPMC-AgNPs	15	11.8 to 12.7 µM	0.5 µM	Chemical	Colorimetric	Wu et al. (2015)
	CA-AgNPs	~ 1	0–0.8 µM	5 nM	Chemical	Colorimetric	Qi et al. (2017)
	NTTTA-AgNPs	11	0.05–10 µM	0.5 µM	Chemical	Colorimetric	Wei et al. (2018)
	AgNPs/ L-Tyrosine	8.2 ± 2	16–500 nM	16 nM	<i>Green synthesis</i>	Colorimetric	Annadhasan et al. (2014)

**Table 3** (continued)

Metal	Functionalizing agent	Particle size (nm)	Linear range	LOD	Synthesize method	Analysis method	Reference
Cu <sup>2+</sup>	4-MBA AgNPs	~10	$1 \times 10^{-7}$ – $1 \times 10^{-4}$ M	$2.5 \times 10^{-8}$ M	Chemical	Colorimetric	Zuo et al. (2011)
	PADs AgNPs	10	7.8–62.8 mM	7.8 nM	Physical	Colorimetric	Ratnarathorn et al. (2012)
	AgNPs / gelatin hydrogels	–	$1 \times 10^{-8}$ – $1 \times 10^{-4}$ M	$1 \times 10^{-7}$ M	Chemical	Colorimetric	Jeevika and Shankaran (2014)
	Trehalose –AgNPs	0.23	1.92 nM	0.817–5.66 $\mu$ M	Chemical	–	Maruthupandi and Vasimalai (2021)
	Cdots–AgNPs	$33.8 \pm 3.4$	0.005–1 $\mu$ M	4.81 nM	Physical	Colorimetric	Wei et al. (2019)
	Flow-batch/Ag NPs/ Na <sub>2</sub> S <sub>2</sub> O <sub>3</sub> /Cu <sup>2+</sup>	$25 \pm 5$	0.5–35 $\mu$ g/L	0.24 $\mu$ g/L	Chemical	Colorimetric	Peng et al. (2017)
	R-PE-AgNPs	8	0 $\mu$ M to 100.0 $\mu$ M	0.0190 $\mu$ M	Green synthesis	Colorimetric	Xu et al. (2019)
	(DNA-Ag NCs)	2	5.0–125.0 ( $\mu$ M)	0.500 $\mu$ M	Chemical	Colorimetric	Liu et al. (2012)
	AgNps 2-aminothiopheny	5.5	0.0005–50.0 ( $\mu$ M)	0.0005 $\mu$ M	Physical	Fluorescent	Tharmaraj and Pitchumani (2013)
	Chitosan-capped AgNPs	20	3.33–40.0 ( $\mu$ M)	0.0103 $\mu$ M	Chemical	Colorimetric	Zuo et al. (2011)
	DSP-AuNPs / AgNPs	–	1.0–1000 nM	0.48 nM	Chemical	Electrochemical	Cui et al. (2014)
	AgNPs/ casein-peptide	$20 \pm 2$	0.08–1.44 $\mu$ M	0.16 $\mu$ M	Physical	Colorimetric	Ghodake et al. (2018)
	AgNPs/ 3,4-dihydroxy- L-phenylalanine	20	65–125 $\mu$ M	94 $\mu$ M	Green synthesis	Colorimetric	Cheon and Park (2016)
	AgNPs/ Riboflavin	20	5–100 $\mu$ M	1.12 nM	Green synthesis	Colorimetric	Basiri et al. (2017)

will be real-time directed toward the location of numerous analytes during a solitary go with improved affectability and handiness. Furthermore, nanochips are being pushed for improvement, wherein NPs are immobilized into tiny chip-like materials and utilized for detector applications. This venture may open new vistas for the creation of a “lab to chip” strategy for the sensitive detection of metal ions in tainted water bodies. Third, the origination of a novel innovation that licenses possible recognition and evaluation of metal particles in defiled samples will help in screening and limit environmental toxicity, subsequently providing protection to humans and government assistance. A consensus among physicists, scientists, and researchers will help in the assembly and commercialization of these entertainers, which may work with the usage of various tests in the laboratory and field for metal identification.

## Conclusion

This paper investigated the synthesis and functionalization of AgNPs, which can be used as a sensor for heavy metals (Cu<sup>2+</sup>, Hg<sup>2+</sup>, Cr<sup>2+</sup>, Pb<sup>2+</sup>, Mn<sup>2+</sup>, and As<sup>2+</sup>), using different synthesis methods (chemical, physical, and biological). In conclusion, endeavors were explored to create nanomaterial-based sensors for the detection of heavy metals for further development of the sensitivity, selectivity, and execution of gadgets. Better affectability and selectivity in the detection of heavy metals are accomplished when using nanomaterials as sensors. Physical and chemical methods have the advantage of high surface-to-volume ratio of high-functionality nanomaterials used in the detection of heavy metals. On the other hand, biological method-based sensors from steady, economical, biocompatible, and nontoxic inorganic reagents



offer the best results due to their high limit of detection, low cost, and accessible applications. For advances and developments in detection of heavy-metal ions using these nanosensors were poses incredible improvement challenges.

**Author contributions** All authors contributed to the study conception and design. Literature search, data collection and analysis were performed by F.S., M.S., B.A., D.T. The first draft of the manuscript was written by F.S., and all authors commented on previous versions of the manuscript. All authors read and approved the final manuscript. Conceptualization idea, review and editing, supervision was contributed by D.T.

**Funding** The authors declare that no funds, grants, or other support were received during the preparation of this manuscript.

**Data availability** All data generated or analyzed during this study are included in this published article.

## Declarations

**Conflict of interest** The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

**Consent for publication** All authors mutually agree that the manuscript can be submitted to International Journal of Environmental Science and Technology.

## References

- Abdelsattar AS, Gouda SM, Hassan YY, Farouk WM, Makky S, Nasr A, Hakim TA, El-Shibiny A (2022) In vitro bacteriophage-mediated synthesis of silver nanoparticles for antibacterial applications and heavy metal detection. *Mater Lett* 318:132184. <https://doi.org/10.1016/j.matlet.2022.132184>
- Abou El-Nour KMM, Eftaiha A, Al-Warthan A, Ammar RAA (2010) Synthesis and applications of silver nanoparticles. *Arab J Chem* 3(3):135–140. <https://doi.org/10.1016/j.arabjc.2010.04.008>
- Ahmed F, Kabir H, Xiong H (2020) Dual colorimetric sensor for Hg<sup>2+</sup>/Pb<sup>2+</sup> and an efficient catalyst based on silver nanoparticles mediating by the root extract of *Bistorta amplexicaulis*. *Front Chem* 8:591958. <https://doi.org/10.3389/fchem.2020.591958>
- Al-Onazi WA, Abdel-Lateef MA (2022) Catalytic oxidation of *O*-phenylenediamine by silver nanoparticles for resonance Rayleigh scattering detection of mercury (II) in water samples. *Spectrochim Acta A Mol Biomol Spectrosc* 264:120258. <https://doi.org/10.1016/j.saa.2021.120258>
- Annadhasan M, Muthukumarasamyvel T, Sankar Babu VR, Rajendiran N (2014) Green synthesized silver and gold nanoparticles for colorimetric detection of Hg<sup>2+</sup>, Pb<sup>2+</sup>, and Mn<sup>2+</sup> in aqueous medium. *ACS Sustain Chem Eng* 2(4):887–896. <https://doi.org/10.1021/sc400500z>
- Anto Judy D, Sheeba Sherlin Y, Arasu MV, Al-Dhabi NA, Choi KC, Bindhu MR (2021) Environmental photochemistry in *Solanum trilobatum* mediated plasmonic nanoparticles as a probe for the detection of Cd<sup>2+</sup> ions in water. *Environ Res* 202:111918. <https://doi.org/10.1016/j.envres.2021.111918>
- Aragay G, Pons J, Merkoçi A (2011) Enhanced electrochemical detection of heavy metals at heated graphite nanoparticle-based screen-printed electrodes. *J Mater Chem* 21(12):4326. <https://doi.org/10.1039/C0JM03751F>
- Aritonang HF, Kojong T, Koleangan H, Wuntu AE (2021) Green synthesis of silver nanoparticles using *Lantana camara* fresh leaf extract for qualitative detection of Hg<sup>2+</sup>, Cu<sup>2+</sup>, Pb<sup>2+</sup>, and Mn<sup>2+</sup> in aqueous solution. *Indones J Chem* 21(4):990–1002. <https://doi.org/10.22146/ijc.64902>
- Basiri S, Mehdinia A, Jabbari A (2017) Biologically green synthesized silver nanoparticles as a facile and rapid label-free colorimetric probe for determination of Cu<sup>2+</sup> in water samples. *Spectrochim Acta A Mol Biomol Spectrosc* 171:297–304. <https://doi.org/10.1016/j.saa.2016.08.032>
- Bhattacharjee Y, Chatterjee D, Chakraborty A (2018) Mercaptobenzoheterocyclic compounds functionalized silver nanoparticle, an ultrasensitive colorimetric probe for Hg(II) detection in water with picomolar precision: a correlation between sensitivity and binding affinity. *Sens Actuators B Chem* 255:210–216. <https://doi.org/10.1016/j.snb.2017.08.066>
- Bindhu MR, Umadevi M, Esmail GA, Al-Dhabi NA, Arasu MV (2020) Green synthesis and characterization of silver nanoparticles from *Moringa oleifera* flower and assessment of antimicrobial and sensing properties. *J Photochem Photobiol B Biol* 205:111836. <https://doi.org/10.1016/j.jphotobiol.2020.111836>
- Borah SBD, Bora T, Baruah S, Dutta J (2015) Heavy metal ion sensing in water using surface plasmon resonance of metallic nanostructures. *Groundw Sustain Dev* 1(1–2):1–11. <https://doi.org/10.1016/j.gsd.2015.12.004>
- Buduru P, Reddy BCSR, Naidu NVS (2017) Functionalization of silver nanoparticles with glutamine and histidine for simple and selective detection of Hg<sup>2+</sup> ion in water samples. *Sens Actuators B Chem* 244:972–982. <https://doi.org/10.1016/j.snb.2017.01.041>
- Buledi JA, Amin S, Haider SI, Bhangar MI, Solangi AR (2020) A review on detection of heavy metals from aqueous media using nanomaterial-based sensors. *Environ Sci Pollut Res* 28:58994–59002. <https://doi.org/10.1007/s11356-020-07865-7>
- Chamaraja NA, Mahesh B, Praveen Kumar CB (2021) Colorimetric detection of chromium (VI) using peroxidase mimetic IONPS with 4-Aminoantipyrene and 3-Aminophenol as a chromogen. *Environ Nanotechnol Monit Manag* 16:100471. <https://doi.org/10.1016/j.enmm.2021.100471>
- Chen L, Qi N, Wang X, Chen L, You H, Li J (2014) Ultrasensitive surface-enhanced Raman scattering nanosensor for mercury ion detection based on functionalized silver nanoparticles. *RSC Adv* 4(29):15055–15060. <https://doi.org/10.1039/c3ra47492e>
- Cheon J, Park W (2016) Green synthesis of silver nanoparticles stabilized with mussel-inspired protein and colorimetric sensing of lead(II) and copper(II) ions. *Int J Mol Sci* 17(12):2006. <https://doi.org/10.3390/ijms17122006>
- Choudhury R, Misra TK (2018) Gluconate stabilized silver nanoparticles as a colorimetric sensor for Pb<sup>2+</sup>. *Colloids Surf A Physicochem Eng Asp* 545:179–187. <https://doi.org/10.1016/j.colsurfa.2018.02.051>
- Cui L, Wu J, Li J, Ge Y, Ju H (2014) Electrochemical detection of Cu<sup>2+</sup> through Ag nanoparticle assembly regulated by copper-catalyzed oxidation of cysteamine. *Biosens Bioelectron* 55:272–277. <https://doi.org/10.1016/j.bios.2013.11.081>
- Dali M, Zinoubi K, Chrouda A, Abderrahmane S, Cherrad S, Jaffrezic-Renault N (2018) A biosensor based on fungal soil biomass for electrochemical detection of lead (II) and cadmium (II) by differential pulse anodic stripping voltammetry. *J Electroanal Chem* 813:9–19. <https://doi.org/10.1016/j.jelechem.2018.02.009>
- Duffus JH (2002) “Heavy metals” a meaningless term? (IUPAC technical report). *Pure Appl Chem* 74(5):793–807. <https://doi.org/10.1351/pac200274050793>
- Elavarasi M, Rajeshwari A, Alex SA, Nanda Kumar D, Chandrasekaran N, Mukherjee A (2014) Simple colorimetric sensor for Cr(III) and Cr(VI) speciation using silver nanoparticles as a probe. *Anal Methods* 6(14):5161. <https://doi.org/10.1039/c4ay00877d>

- Farhadi K, Forough M, Molaei R, Hajizadeh S, Rafipour A (2012) Highly selective  $Hg^{2+}$  colorimetric sensor using green synthesized and unmodified silver nanoparticles. *Sens Actuators B Chem* 161(1):880–885. <https://doi.org/10.1016/j.snb.2011.11.052>
- Firdaus ML, Apriyoanda H, Elvinawati E, Rahmidar L, Astuti AP, Swistoro E, Sundaryono A (2021) Green route of silver nanoparticles synthesis using watermelon (*Citrullus lanatus*) fruit extract for mercury ions detection. *J Phys Conf Ser* 1731:012020. <https://doi.org/10.1088/1742-6596/1731/1/012020>
- Flores E, Pizarro J, Godoy F, Segura R, Gómez A, Agurto N, Sepúlveda P (2017) An electrochemical sensor for the determination of Cu (II) using a modified electrode with ferrocenyl crown ether compound by square wave anodic stripping voltammetry. *Sens Actuators B Chem* 251:433–439. <https://doi.org/10.1016/j.snb.2017.05.058>
- Gan X, Zhao H, Schirhagl R, Quan X (2018) Two-dimensional nanomaterial based sensors for heavy metal ions. *Microchim Acta* 185(10):478. <https://doi.org/10.1007/s00604-018-3005-1>
- Gao YX, Xin JW, Shen ZY, Pan W, Li X, Wu AG (2013) A new rapid colorimetric detection method of  $Mn^{2+}$  based on tripolyphosphate modified silver nanoparticles. *Sens Actuators B Chem* 181:288–293. <https://doi.org/10.1016/j.snb.2013.01.079>
- Ghodake GS, Shinde SK, Saratale RG, Kadam AA, Saratale GD, Syed A, Ameen F, Kim DY (2018) Colorimetric detection of  $Cu^{2+}$  based on the formation of peptide–copper complexes on silver nanoparticle surfaces. *Beilstein J Nanotechnol* 9:1414–1422. <https://doi.org/10.3762/bjnano.9.134>
- Gupta D, Chauhan P (2017) Green synthesis of silver nanoparticles involving extract of plants of different taxonomic groups. *J Nanomed Res* 5(2):00110. <https://doi.org/10.15406/jnmr.2017.05.00110>
- Hao B, Bu X, Wu J, Ding Y, Zhang L, Zhao B, Tian Y (2020) Determination of  $Hg^{2+}$  in water based on acriflavine functionalized AgNPs by SERS. *Microchem J* 155:104736. <https://doi.org/10.1016/j.microc.2020.104736>
- Hu R, Zhang L, Li H (2014) A highly sensitive and selective colorimetric sensor for the detection of  $Mn^{2+}$  based on supramolecular silver nanoparticle clusters. *New J Chem* 38(6):2237–2240. <https://doi.org/10.1039/c3nj01593a>
- Hyder A, Memon SS, Memon S, Sirajuddin Memon ZA, Rajpar DB, Shaikh SG, Buledi AJ (2021) A highly discerning p-tetranitrocalix[4]arene (p-TNC4) functionalized copper nanoparticles: a smart electrochemical sensor for the selective determination of diphenhydramine drug. *Microchem J* 163:105908. <https://doi.org/10.1016/j.microc.2020.105908>
- Hyder A, Buledi JA, Nawaz M, Rajpar DB, Shah ZUH, Orooji Y, Yola ML, Karimi-Maleh H, Lin H, Solangi AR (2022) Identification of heavy metal ions from aqueous environment through gold, silver and copper nanoparticles: An excellent colorimetric approach. *Environ Res* 205:112475. <https://doi.org/10.1016/j.envres.2021.112475>
- Iftekhhar S, Nazir F, Abbasi NM, Ahmad Khan A, Ahmed F (2021) Rumex hastatus mediated green synthesis of AgNPs: An efficient nanocatalyst and colorimetric probe for  $Cu^{2+}$ . *Colloids Surf A Physicochem Eng Asp* 628:127356. <https://doi.org/10.1016/j.colsurfa.2021.127356>
- Ilyas S, Heryanto H, Abdullah B, Tahir D (2019) X-ray diffraction analysis of nanocomposite  $Fe_3O_4$ /activated carbon by Williamson-Hall and size-strain plot methods. *Nano Struct Nano Objects* 20:100396. <https://doi.org/10.1016/j.nanos.2019.100396>
- Ilyas S, Heryanto H, Tahir D (2021) Correlation between structural and optical properties of CuO/carbon nanoparticle in supports the photocatalytic performance and attenuate the electromagnetic wave. *J Environ Chem Eng* 9(1):104670. <https://doi.org/10.1016/j.jece.2020.104670>
- Ismail M, Khan MI, Akhtar K, Khan MA, Asiri AM, Khan SB (2018) Biosynthesis of silver nanoparticles: a colorimetric optical sensor for detection of hexavalent chromium and ammonia in aqueous solution. *Physica E Low Dimens Syst Nanostruct* 103:367–376. <https://doi.org/10.1016/j.physe.2018.06.015>
- Jeevika A, Shankaran DR (2014) Visual colorimetric sensing of copper ions based on reproducible gelatin functionalized silver nanoparticles and gelatin hydrogels. *Colloids Surf A Physicochem Eng Asp* 461:240–247. <https://doi.org/10.1016/j.colsurfa.2014.08.002>
- Joshi P, Nair M, Kumar D (2016) pH-controlled sensitive and selective detection of Cr(III) and Mn(II) by using clove (*S. aromatum*) reduced and stabilized silver nanospheres. *Anal Methods* 8(6):1359–1366. <https://doi.org/10.1039/c5ay03217b>
- Jumina Priastomo Y, Setiawan HR, Mutmainah Kurniawan YS, Ohto K (2020) Simultaneous removal of lead (II), chromium (III), and copper (II) heavy metal ions through an adsorption process using C-phenylcalix [4]pyrogallolarene material. *J Environ Chem Eng* 8(4):103971. <https://doi.org/10.1016/j.jece.2020.103971>
- Kakakhel MA, Sajjad W, Wu F, Bibi N, Shah K, Yali Z, Wang W (2021) Green synthesis of silver nanoparticles and their shortcomings, animal blood a potential source for silver nanoparticles: a review. *J Hazard Mater Adv* 1:100005. <https://doi.org/10.1016/j.hazadv.2021.100005>
- Kalam A, Al-Sehemi AG, Alrumman S, Assiri M, Moustafa MFM, Yadav P, Pannipara M (2018) Colorimetric optical chemosensor of toxic metal ion ( $Hg^{2+}$ ) and biological activity using green synthesized AgNPs. *Green Chem Lett Rev* 11(4):484–491. <https://doi.org/10.1080/17518253.2018.1538431>
- Kalishwaralal K, Deepak V, Ram Kumar Pandian S, Kottaisamy M, BarathManiKanth S, Kartikeyan B, Gurunathan S (2010) Biosynthesis of silver and gold nanoparticles using *Brevibacterium casei*. *Colloids Surf B* 77(2):257–262. <https://doi.org/10.1016/j.colsurfb.2010.02.007>
- Kanagaraj R, Nam YS, Pai SJ, Han SS, Lee KB (2017) Highly selective and sensitive detection of  $Cr^{6+}$  ions using size-specific label-free gold nanoparticles. *Sens Actuators B Chem* 251:683–691. <https://doi.org/10.1016/j.snb.2017.05.089>
- Karthiga D, Anthony SP (2013) Selective colorimetric sensing of toxic metal cations by green synthesized silver nanoparticles over a wide pH range. *RSC Adv* 3(37):16765. <https://doi.org/10.1039/c3ra42308e>
- Kaur B, Srivastava R, Satpati B (2015) Ultratrace detection of toxic heavy metal ions found in water bodies using hydroxyapatite supported nanocrystalline ZSM-5 modified electrodes. *New J Chem* 39(7):5137–5149. <https://doi.org/10.1039/C4NJ02369B>
- Khan NA, Niaz A, Zaman MI, Khan FA, Nisar-ul-Haq M, Tariq M (2018a) Sensitive and selective colorimetric detection of  $Pb^{2+}$  by silver nanoparticles synthesized from *Aconitum violaceum* plant leaf extract. *Mater Res Bull* 102:330–336. <https://doi.org/10.1016/j.materresbull.2018.02.050>
- Khan Y, Qasimnasar M, Numan M, Ullah I, Shinwari ZK (2018b) Biomimetic synthesis of silver nanoparticles for breast cancer therapeutics and its mechanism. *Int J Nanotec Nanomed* 3(1):2476–2334. <https://doi.org/10.1049/iet-nbt.2016.0222>
- Kolya H, Kuila T, Kim NH, Lee JH (2020) Colorimetric/naked eye detection of arsenic ions in aqueous medium by mango flower extract: a facile and novel approach. *Appl Surf Sci* 513:145760. <https://doi.org/10.1016/j.apsusc.2020.145760>
- Kumar H, Bhardwaj K, Kuča K, Kalia A, Nepovimova E, Verma R, Kumar D (2020) Flower-based green synthesis of metallic nanoparticles: applications beyond fragrance. *Nanomaterials* 10(4):766. <https://doi.org/10.3390/nano10040766>
- Lee SH, Jun BH (2019) Silver nanoparticles: synthesis and application for nanomedicine. *Int J Mol Sci* 20(4):865. <https://doi.org/10.3390/ijms20040865>



- Li F, Wang J, Lai Y, Wu C, Sun S, He Y, Ma H (2013) Ultrasensitive and selective detection of copper (II) and mercury (II) ions by dye-coded silver nanoparticle-based SERS probes. *Biosens Bioelectron* 39(1):82–87. <https://doi.org/10.1016/j.bios.2012.06.050>
- Li L, Feng D, Fang X, Han X, Zhang Y (2014) Visual sensing of  $Hg^{2+}$  using unmodified Au@Ag core-shell nanoparticles. *J Nanostruct Chem* 4:117. <https://doi.org/10.1007/s40097-014-0117-y>
- Lin L, Pho HQ, Zong L, Li S, Pourali N, Rebrov E, Tran NN, Ostrikov K, Hessel V (2021) Microfluidic plasmas: novel technique for chemistry and chemical engineering. *Chem Eng J* 417:12935. <https://doi.org/10.1016/j.cej.2021.129355>
- Liu G, Feng DQ, Chen T, Li D, Zheng W (2012) DNA-templated formation of silver nanoclusters as a novel light-scattering sensor for label-free copper ions detection. *J Mater Chem* 22(39):20885. <https://doi.org/10.1039/c2jm35236b>
- Liu J, Ren X, Meng X, Fang Z, Tang F (2013) Sensitive and selective detection of  $Hg^{2+}$  and  $Cu^{2+}$  ions by fluorescent Ag nanoclusters synthesized via a hydrothermal method. *Nanoscale* 5(20):10022. <https://doi.org/10.1039/c3nr03329e>
- Liu Y, Weerasooriya R, Chen X (2022) The metal-organic framework supported gold nanoparticles as a highly sensitive platform for electrochemical detection of methyl mercury species in the aqueous environment. *J Hazard Mater* 431:128608. <https://doi.org/10.1016/j.jhazmat.2022.128608>
- Luo X, Huang W, Shi Q, Xu W, Luan Y, Yang Y, Wang H, Yang W (2017) Electrochemical sensor based on lead ion-imprinted polymer particles for ultra-trace determination of lead ions in different real samples. *RSC Adv* 7(26):16033–16040. <https://doi.org/10.1039/c6ra25791g>
- Yufei M (2019) Laser technology and its applications: laser ablation technique for synthesis of metal nanoparticle in liquid, Ch 4. InTech, Jakarta <https://doi.org/10.5772/intechopen.80374>
- Khan M (2018) Silver nanoparticles—fabrication, characterization and applications: silver nanoparticles: synthesis, characterization and applications, Ch 2. InTech, Jakarta <https://doi.org/10.5772/intechopen.71247>
- Magaye R, Zhao J (2012) Recent progress in studies of metallic nickel and nickel-based nanoparticles' genotoxicity and carcinogenicity. *Environ Toxicol Pharmacol* 34(3):644–650. <https://doi.org/10.1016/j.etap.2012.08.012>
- Maruthupandi M, Vasimalai N (2021) Nanomolar detection of L-cysteine and  $Cu^{2+}$  ions based on trehalose capped silver nanoparticles. *Microchem J* 161:105782. <https://doi.org/10.1016/j.microc.2020.105782>
- Mensah MB, Lewis DJ, Boadi NO, Awudza JAM (2021) Heavy metal pollution and the role of inorganic nanomaterials in environmental remediation. *R Soc Open Sci* 8(10):201485. <https://doi.org/10.1098/rsos.201485>
- Mukherjee S, Bhattacharyya S, Ghosh K, Pal S, Halder A, Naseri M, Mohammadniaei M, Sarkar S, Ghosh A, Sun Y, Bhattacharyya N (2021) Sensory development for heavy metal detection: a review on translation from conventional analysis to field-portable sensor. *Trends Food Sci Technol* 109:674–689. <https://doi.org/10.1016/j.tifs.2021.01.062>
- Narchin F, Larijani K, Rustaiyan A, Nejad Ebrahimi S, Tafvizi F (2018) Phytochemical synthesis of silver nanoparticles by two techniques using *Saturaja rechengri* Jamzad extract: identifying and comparing in vitro anti-proliferative activities. *Adv Pharm Bull* 8(2):235–244. <https://doi.org/10.15171/apb.2018.028>
- Nie Q, Wang Y, Jia L, Liu B, Liu E, Hu X, Fan J (2017) Luminescence resonance energy transfer probes based on  $NaYF_4:Yb, Er$ -Ag nanocompounds for sensitive detection of  $Mn^{2+}$  ions. *J Alloys Compd* 722:896–902. <https://doi.org/10.1016/j.jallcom.2017.06.112>
- Noh KC, Nam YS, Lee HJ, Lee KB (2015) A colorimetric probe to determine  $Pb^{2+}$  using functionalized silver nanoparticles. *Analyst* 140(24):8209–8216. <https://doi.org/10.1039/c5an01601k>
- Oluwafemi OS, Anyik JL, Zikalala NE, Sakho EHM (2019) Biosynthesis of silver nanoparticles from water hyacinth plant leaves extract for colorimetric sensing of heavy metals. *Nano Struct Nano Objects* 20:100387. <https://doi.org/10.1016/j.nanos.2019.100387>
- Panja A, Mishra AK, Dash M, Pandey NK, Singh SK, Kumar B (2021) Silver nanoparticles—a review. *Eurasian J Med Oncol* 5(2):95–102. <https://doi.org/10.14744/ejmo.2021.59602>
- Peng J, Liu G, Yuan D, Feng S, Zhou T (2017) A flow-batch manipulated Ag NPs based SPR sensor for colorimetric detection of copper ions ( $Cu^{2+}$ ) in water samples. *Talanta* 167:310–316. <https://doi.org/10.1016/j.talanta.2017.02.015>
- Prasad KS, Shruthi G, Shivamallu C (2018) Functionalized silver nanosensor for colorimetric detection of  $Hg^{2+}$  ions: facile synthesis and docking studies. *Sensors* 18(8):2698. <https://doi.org/10.3390/s18082698>
- Princy SSJ, Sherin JFJ, Vijayakumar C, Hentry C, Bindhu MR, Alarjani KM, Alghamidi NS, Hussein DS (2022) Detection of heavy metals, SERS and antibacterial activity of polyvinylpyrrolidone modified plasmonic nanoparticles. *Env Res* 210:112883. <https://doi.org/10.1016/j.envres.2022.112883>
- Proposito P, Burratti L, Bellingeri A, Protano G, Faleri C, Corsi I, Battocchio C, Iucci G, Tortora L, Secchi V, Francho S, Venditti I (2019) Bifunctionalized silver nanoparticles as  $Hg^{2+}$  plasmonic sensor in water: synthesis, characterizations, and ecosafety. *Nanomaterials* 9(10):1353. <https://doi.org/10.3390/nano9101353>
- Qi YX, Qu ZB, Wang QX, Zhang M, Shi G (2017) Nanomolar sensitive colorimetric assay for  $Mn^{2+}$  using cysteic acid-capped silver nanoparticles and theoretical investigation of its sensing mechanism. *Anal Chim Acta* 980:65–71. <https://doi.org/10.1016/j.aca.2017.05.018>
- Rasheed T, Shafi S, Ali J, Sher F, Rizwan K, Khan S (2022) Recent advances in chemically and biologically synthesized nanostructures for colorimetric detection of heavy metal. *J King Saud Univ Sci* 34(2):101745. <https://doi.org/10.1016/j.jksus.2021.101745>
- Rastogi L, Sashidhar RB, Karunasagar D, Arunachalam J (2014) Gum kondagogu reduced/stabilized silver nanoparticles as direct colorimetric sensor for the sensitive detection of  $Hg^{2+}$  in aqueous system. *Talanta* 118:111–117. <https://doi.org/10.1016/j.talanta.2013.10.012>
- Ratnarathorn N, Chailapakul O, Henry CS, Dungchai W (2012) Simple silver nanoparticle colorimetric sensing for copper by paper-based devices. *Talanta* 99:552–557. <https://doi.org/10.1016/j.talanta.2012.06.033>
- Ren W, Zhu C, Wang E (2012) Enhanced sensitivity of a direct SERS technique for  $Hg^{2+}$  detection based on the investigation of the interaction between silver nanoparticles and mercury ions. *Nanoscale* 4(19):5902–5909. <https://doi.org/10.1039/c2nr31410j>
- Roto R, Mellisani B, Kuncaka A, Mudasar M, Suratman A (2019) Colorimetric sensing of  $Pb^{2+}$  ion by using Ag nanoparticles in the presence of dithizone. *Chemosensors* 7(3):28. <https://doi.org/10.3390/chemosensors7030028>
- Şahin S, Caglayan MO, Üstundağ Z (2020) A review on nanostructure-based mercury (II) detection and monitoring focusing on aptamer and oligonucleotide biosensors. *Talanta* 220:121437. <https://doi.org/10.1016/j.talanta.2020.121437>
- Sangaonkar GM, Desai MP, Dongale TD, Pawar KD (2020) Selective interaction between phyto-mediated anionic silver nanoparticles and mercury leading to amalgam formation enables highly sensitive, colorimetric and memristor-based detection of mercury. *Sci Rep* 10(1):2037. <https://doi.org/10.1038/s41598-020-58844-4>
- Sengan M, Veeramuthu D, Veerappan A (2018) Photosynthesis of silver nanoparticles using *Durio zibethinus* aqueous extract and its



- application in catalytic reduction of nitroaromatics, degradation of hazardous dyes and selective colorimetric sensing of mercury ions. *Mater Res Bull* 100:386–393. <https://doi.org/10.1016/j.materresbull.2017.12.038>
- Sharif T, Niaz A, Najeeb M, Zaman MI, Ihsan M (2015) Isonicotinic acid hydrazide-based silver nanoparticles as simple colorimetric sensor for the detection of  $\text{Cr}^{3+}$ . *Sens Actuators B Chem* 216:402–408. <https://doi.org/10.1016/j.snb.2015.04.043>
- Sharma VK, Yngard RA, Lin Y (2009) Silver nanoparticles: green synthesis and their antimicrobial activities. *Adv Colloid Interface Sci* 145(1–2):83–96. <https://doi.org/10.1016/j.cis.2008.09.002>
- Shoae H, Roshdi M, Khanlarzadeh N, Beiraghi A (2012) Simultaneous preconcentration of copper and mercury in water samples by cloud point extraction and their determination by inductively coupled plasma atomic emission spectrometry. *Spectrochim Acta A Mol Biomol* 98:70–75. <https://doi.org/10.1016/j.saa.2012.08.027>
- Shrivastava P, Jain VK, Nagpal S (2022) Nanoparticle intervention for heavy metal detection: a review. *Environ Nanotechnol Monit Manag* 17:100667. <https://doi.org/10.1016/j.enmm.2022.100667>
- Shyam A, Chandran SS, George B, Sreelekha E (2020) Plant mediated synthesis of AgNPs and its applications: an overview. *Inorg Nano Mater Chem* 51(12):1646–1662. <https://doi.org/10.1080/24701556.2020.1852254>
- Singaravelan R, Bangaru Sudarsan Alwar S (2015) Electrochemical synthesis, characterisation and phyto-genic properties of silver nanoparticles. *Appl Nanosci* 5(8):983–991. <https://doi.org/10.1007/s13204-014-0396-0>
- Sun Z, Zhang N, Si Y, Li S, Wen J, Zhu X, Wang H (2014) High-throughput colorimetric assays for mercury(II) in blood and wastewater based on the mercury-stimulated catalytic activity of small silver nanoparticles in a temperature-switchable gelatin matrix. *ChemComm* 50(65):9196–9199. <https://doi.org/10.1039/c4cc03851g>
- Syafiuddin A, Salmiati SMR, Beng Hong Kueh A, Hadibarata T, Nur H (2017) A review of silver nanoparticles: research trends, global consumption, synthesis, properties, and future challenges. *J Chin Chem Soc* 64(7):732–756. <https://doi.org/10.1002/jccs.20170067>
- Tahir D, Heryanto H, Ilyas S, Fahri AN, Rahmat R, Rahmi MH, Taryana Y, Sukaryo SG (2021) Excellent electromagnetic wave absorption of  $\text{Co/Fe}_2\text{O}_3$  composites by additional activated carbon for tuning the optical and the magnetic properties. *J Alloys Compd* 864:158780. <https://doi.org/10.1016/j.jallcom.2021.158780>
- Tang P, Sun G (2018) Highly sensitive colorimetric paper sensor for methyl isothiocyanate (MITC): using its toxicological reaction. *Sens Actuators B Chem* 261:178–187. <https://doi.org/10.1016/j.snb.2018.01.086>
- Tao A, Sinsermsuksakul P, Yang P (2006) Polyhedral silver nanocrystals with distinct scattering signatures. *Angew Chem* 45(28):4597–4601. <https://doi.org/10.1002/anie.200601277>
- Taufiq M, Eden WT, Sumarni W, Alauhdin M (2021) Colorimetric detection of metal ions using green-synthesized silver nanoparticles. *J Phys Conf Ser* 1918:032002. <https://doi.org/10.1088/1742-6596/1918/3/032002>
- Tharmaraj V, Pitchumani K (2013) A highly selective ratiometric fluorescent chemosensor for  $\text{Cu(II)}$  based on dansyl-functionalized thiol stabilized silver nanoparticles. *J Mater Chem B* 1(14):1962–1967. <https://doi.org/10.1039/c3tb00534h>
- Tinas H, Ozbek N, Akman S (2018) Determination of lead in flour samples directly by solid sampling high resolution continuum source graphite furnace atomic absorption spectrometry. *Spectrochim Acta Part B at Spectrosc* 140:73–75. <https://doi.org/10.1016/j.sab.2017.12.002>
- Ullah I, Ali I, Ullah S, Khan A, Imran M, Shah MR, Jun L et al. (2022) Synthesis of acyclovir stabilized silver nanoparticles for selective recognition of  $\text{Hg}^{2+}$  in different media. *Int J Environ Sci Technol* 19:11279–11290. <https://doi.org/10.1007/s13762-021-03880-4>
- Vasileva P, Alexandrova T, Karadjova I (2017) Application of starch-stabilized silver nanoparticles as a colorimetric sensor for mercury (II) in 0.005 mol/L nitric acid. *J Chem* 2017:1–9. <https://doi.org/10.1155/2017/6897960>
- Wang Y, Yang F, Yang X (2010) Colorimetric detection of mercury (II) ion using unmodified silver nanoparticles and mercury-specific oligonucleotides. *ACS Appl Mater Interfaces* 2(2):339–342. <https://doi.org/10.1021/am9007243>
- Wang L, Zhang T, Li P, Huang W, Tang J, Wang P, Liu J, Yuan Q, Bai R, Li B, Zhang K, Zhao Y, Chen C (2015) Use of synchrotron radiation-analytical techniques to reveal chemical origin of silver-nanoparticle cytotoxicity. *ACS Nano* 9(6):6532–6547. <https://doi.org/10.1021/acs.nano.5b02483>
- Wei J, Chen J, Yue G, Hu L, Zhao D, Zhu J, Yang L, Huang D, Zhao P (2018) Development of a novel tridentate ligand for colorimetric detection of  $\text{Mn}^{2+}$  based on AgNPs. *Spectrochim Acta A Mol Biomol Spectrosc* 202:244–251. <https://doi.org/10.1016/j.saa.2018.05.033>
- Wei L, Chen Y, Lian Y, Huang M, Xiao L (2019) Dual mode fluorometric/colorimetric sensor for  $\text{Cu}^{2+}$  ions detection based on hybridized carbon dots and gold-silver core shell nanoparticles. *Analyst* 144:4250–4257. <https://doi.org/10.1039/C9AN00850K>
- Wu G, Dong C, Li Y, Wang Z, Gao Y, Shen Z, Wu A (2015) A novel AgNPs-based colorimetric sensor for rapid detection of  $\text{Cu}^{2+}$  or  $\text{Mn}^{2+}$  via pH control. *RSC Adv* 5(26):20595–20602. <https://doi.org/10.1039/c5ra00001g>
- Xu Y, Hou Y, Wang Y, Wang Y, Li T, Song C, Wei N, Wang Q (2019) Sensitive and selective detection of  $\text{Cu}^{2+}$  ions based on fluorescent Ag nanoparticles synthesized by *R*-phycoerythrin from marine algae *Porphyra yezoensis*. *Ecotoxicol Environ Saf* 168:356–362. <https://doi.org/10.1016/j.ecoenv.2018.10.102>
- Yokota Y, Manaka A, Tafu M, Kato T, Tomita K, Akazawa T (2019) Simple colorimetric analysis for determining hexavalent chromium with high sensitivity via homogeneous liquid-liquid extraction. *Bull Chem Soc Jpn* 92(4):807–810. <https://doi.org/10.1246/bcsj.20180351>
- Yu CJ, Tseng WL (2008) Colorimetric detection of mercury (II) in a high-salinity solution using gold nanoparticles capped with 3-mercaptopropionate acid and adenosine monophosphate. *Langmuir* 24(21):12717–12722. <https://doi.org/10.1021/la802105b>
- Yu L, Sun L, Zhang Q, Zhou Y, Zhang J, Yang B, Xu B, Xu Q (2022) Nanomaterials-based ion-imprinted electrochemical sensors for heavy metal ions detection: a review. *Biosensors* 12(12):1096. <https://doi.org/10.3390/bios12121096>
- Yuan X, Wen S, Shen M, Shi X (2013) Dendrimer-stabilized silver nanoparticles enable efficient colorimetric sensing of mercury ions in aqueous solution. *Anal Methods* 5(20):5486. <https://doi.org/10.1039/c3ay41331d>
- Zannotti M, Vicomandi V, Rossi A, Minicucci M, Ferraro S, Petetta L, Giovannetti R (2020) Tuning of hydrogen peroxide etching during the synthesis of silver nanoparticles. An application of triangular nanoplates as plasmon sensors for  $\text{Hg}^{2+}$  in aqueous solution. *J Mol Liq* 309:113238. <https://doi.org/10.1016/j.molliq.2020.113238>
- Zhai H, Bai Y, Qin J, Feng F (2019) Colorimetric and ratiometric fluorescence dual-mode sensing of glucose based on carbon quantum



- dots and potential UV/fluorescence of *O*-diaminobenzene. *Sensors* 19(3):674. <https://doi.org/10.3390/s19030674>
- Zhang N, Si Y, Sun Z, Chen L, Li R, Qiao Y, Wang H (2014) Rapid, selective, and ultrasensitive fluorimetric analysis of mercury and copper levels in blood using bimetallic gold–silver nanoclusters with “silver effect”-enhanced red fluorescence. *Anal Chem* 86(23):11714–11721. <https://doi.org/10.1021/ac503102g>
- Zhang Z, Shang C, Zhao W, Cao Y, Han J, Hu C, Liu Y (2022) 3,3',5,5'-Tetramethylbenzidine and polyetherimide decorated silver nanoparticles for colorimetric  $Mn^{2+}$  ions detection in aqueous solution. *Chem Pap* 76:7253–7260. <https://doi.org/10.1007/s11696-022-02384-w>
- Zhao Y, Xu X, Qiu L, Kang X, Wen L, Zhang B (2017) Metal–organic frameworks constructed from a new thiophene-functionalized dicarboxylate: luminescence sensing and pesticide removal. *ACS Appl Mater Interfaces* 9(17):15164–15175. <https://doi.org/10.1021/acsami.6b11797>
- Zheng H, Hong J, Luo X, Li S, Wang M, Yang B, Wang M (2018) Combination of sequential cloud point extraction and hydride generation atomic fluorescence spectrometry for preconcentration and determination of inorganic and methyl mercury in water samples. *Microchem J* 145:806–812. <https://doi.org/10.1016/j.microc.2018.11.057>
- Zhou Y, Zhao H, Li C, He P, Peng W, Yuan L, Zeng L, He Y (2012) Colorimetric detection of  $Mn^{2+}$  using silver nanoparticles cofunctionalized with 4-mercaptobenzoic acid and melamine as a probe. *Talanta* 97:331–335. <https://doi.org/10.1016/j.talanta.2012.04.041>
- Zuo Y, Zhao HW, Huang CZ, Zhang Q (2011) Sensitive and selective detection of copper ions based on the aggregation of chitosan-stabilized silver nanoparticles. *J Nanosci Nanotechnol* 11(6):5007–5011. <https://doi.org/10.1166/jnn.2011.4123>

Springer Nature or its licensor (e.g. a society or other partner) holds exclusive rights to this article under a publishing agreement with the author(s) or other rightsholder(s); author self-archiving of the accepted manuscript version of this article is solely governed by the terms of such publishing agreement and applicable law.

