

# 30.pdf

*by*

---

FILE	30.PDF (514.41K)	WORD COUNT	2882
TIME SUBMITTED	25-NOV-2020 04:18PM (UTC+0700)	CHARACTER COUNT	14947
SUBMISSION ID	1456905850		

## **STABILITY AND INDIRECT TENSILE STRENGTH OF ASBUTON MIXTURE WITH ADDITIONAL GONDORUKEM (REGINA COLOPHONIA)**

**Don R. G. Kabo**

Doctoral Student of Civil Engineering Department, Hasanuddin University, Makassar

**M. W. Tjaronge**

Profesor, Civil Engineering Department, Hasanuddin University, Makassar

**Abdul Rachman Djamaluddin**

Associate Profesor, Civil Engineering Department, Hasanuddin University, Makassar

**Sumarni Hamid Aly**

Associate Profesor, Civil Engineering Department, Hasanuddin University, Makassar

### **ABSTRACT**

Indonesian natural rock asphalt is known as Asbuton (Buton asphalt) i.e. rock asphalt from Buton Island containing bitumen of approximately 10% to 30%. Semi extraction type of Asbuton product is available as known as modified Buton asphalt (MBA). Research and development have been conducted to obtain better quality of MBA based asphalt concrete. The utilization of Gondorukem (Regina Colophonia) is expected can increase several parameters such as Marshall stability and indirect tensile strength (ITS) of asphalt concrete. The national and regional road infrastructure development in Indonesia can be sustained by used MBA as binder and Gondorukem as additive in pavement material.

The aim of this study is to investigate the properties of asphalt concrete wearing course (AC-13WC) mixture using MBA as binder and Gondorukem as additive. The result of Marshall stability and ITS tests showed the sufficient of Marshall stability and ITS can be established by proper aggregate interlocking and adhesive which developed due to the utilization of MBA and Gondorukem in AC-13WC mixture.

**Keywords:** Modified Buton asphalt (MBA), Gondorukem, AC-13WC mixture, Marshall stability, Indirect tensile strength (ITS)

**Cite this Article:** Don R. G. Kabo, M. W. Tjaronge, Abdul Rachman Djamaluddin, Sumarni Hamid Aly, Stability and Indirect Tensile Strength of Asbuton Mixture with Additional Gondorukem (Regina Colophonia). *International Journal of Civil Engineering and Technology* 10(9), 2019, pp. 166-173.

<http://www.iaeme.com/IJCIET/issues.asp?JType=IJCIET&VType=10&IType=9>

### 3

## 1. INTRODUCTION

Hot mix asphalt mixtures (HMA) is particulate composite material composed of aggregates, asphalt binder and air voids. Asphalt concrete mixtures vary significantly as a result of using different binder-aggregate combinations, aggregate gradations, and binder modification techniques [1, 2].

There is approximately 61 million tons of solid bitumen or natural rock asphalt resources in the Kabungka and Lawele districts of Buton regency in Indonesia. Utilizing local materials such as Asbuton products for road-infrastructure development has played an important role in improving sustainable development in Indonesia in recent decades [3]. Buton natural asphalt or Buton asphalt (Asbuton) consists of approximately 10% - 30% bitumen and 70% minerals. Thus, the utilization of Asbuton products is strongly encouraged in the development of road-infrastructure. During the last few decades, Asbuton with a granular shape has been investigated for use in road construction in asphalt concrete (AC) production. Asbuton can be refined to separate bitumen from the minerals and used extracted bitumen of Asbuton and petroleum bitumen to produce MBA. In recent years, there has been a growing interest in incorporating MBA as a main binder to produce asphalt concrete [4, 5, 6, 7, 13 and 8]

It is well known the utilization of rubber as additive has positive effect on the mechanical properties of asphalt concrete [9, 10]. Gondorukem is a sap processing product of pine tree where Gondorukem is a material absorbs quickly heat or fire. The use of gondorukem rubber as an additive is expected can increase asphalt pavement layer resistance to damage caused by water and weather.

It is important to incorporate performance testing along with the empirical testing during the mixture design and quality control testing of asphalt concrete mixture. Marshall test is an empirical laboratory test that widely used to measure the stability of compacted asphalt concrete specimen [11]. As the wheel passes, tensile stress arises in the pavement structure. The tensile strength is conventionally used in pavement engineering practice as key parameter in the prediction or estimation the performance with related to the mechanical behavior of pavement structures [11]. M.R. Islam, et al [12] carried out ITS test to evaluate the influence of short-term laboratory aging (on loose mixture), long-term laboratory oven aging and field aging on the tensile strength of asphalt concrete. C. S. Du, [11] carried out ITS test to evaluate the cement influence on the tensile strength of asphalt emulsion mixture.

The present research is part of ongoing project that intends to study the suitability of MBA as binder and Gondorukem as additive in production of asphalt mixture. This paper reported the test results on the Marshall stability and ITS of the AC-WC mixture.

## 2. MATERIALS AND METHODS

### 2.1. Gondorukem (Regina Colophonia)

Gondorukem (Regina Colophonia) is a general term for the sap processing products of pine trees. The term Gondorukem originated from the use of sap as a patch of a leaking wooden ship. The world's Gondorukem industry began about 100 years ago. In the United States there was an industry in 1830. In Indonesia the Gondorukem industry began around 1938, with its first factory in Takengon (Aceh). Gondorukem is a cheap and easy material which is a natural resin obtained and distilled from pine resin and is a clear yellow to yellowish solid. The quality of the sap will determine the quality and yield of the resulting Gondorukem. Pine tree sap contains 70 -75% Gondorukem and 20-25% turpentine, respectively.

With the development of industrial technology, Gondorukem is used as additive, printing ink, chewing gum, tire industry and many more (Gondorukem and Turpentine Processing

Handbook - Industrial Division of Perum Perhutani). Table 1 shows some properties of Gondorukem.

**Table 1.** Some properties of Gondorukem (SNI 01-5009.12.2001)

No.	Parameter	Standard			
		X	WW	WG	N
1	Soft point of ring and ball method	≥78°C	≥78°C	≥76°C	≥74°C
2	Test colour with lovibond	as per example	as per example	as per example	as per example
3	Drops	≤ 0.02%	≤ 0.05%	≤ 0.07%	≤ 0.10%
4	Acid value	160 – 190			
5	Sponification value	170 – 220			
6	Iodine value	5 -25			
7	Ash content	≤ 0.01%	≤ 0.04%	≤ 0.05%	≤ 0.08%
8	Volatile oil content	≤ 2%	≤ 2%	≤ 2.5%	≤ 3%
Information :					
X ( <i>Rex</i> ) = The clearest color					
WW ( <i>Water White</i> ) = Clear colors like water					
WG ( <i>Window Glass</i> ) = Clear colors like window glass					
N ( <i>Nancy</i> ) = Yellow color - brownish brown					

## 2.2 Modified Buton Asphalt (MBA)

Table 2 shows properties of MBA. Commercial MBA was used as a prominent binder in this research. Properties of MBA are mostly similar to the petroleum bitumen.

**Table 2.** Properties of MBA

No.	Properties	Testing result
1	Penetration before weight loss (mm)	78.6
2	Softening point (°C)	52
3	ductility in 25°	114
4	Flash point (°C)	280
5	Specific gravity	1.12
6	Weight loss	0.5
7	Penetration after weight loss (mm)	86

## 2.3. Properties of Coarse Aggregate and Filler

All material used were collected from Jeneberang river in Gowa. Two fractions of coarse aggregates derived from crushed river stone were used: one with aggregate diameter 5 - 10 mm and the other with crushed stone diameter 10 - 20 mm. Stone dust collected from the same stone crushed plant was used as filler. Some properties of coarse aggregates and filler are shown in Table 3 and Table 4, respectively.

**Table 3.** Properties of coarse aggregate


Properties	(Crushed stone)	
	Diameter 5 - 10 (mm)	10 - 20 (mm)
Water absorption, %	2.07	2.08
Bulk specific gravity	2.62	2.63
Saturated surface dry specific gravity	2.68	2.68
Apparent specific gravity	2.77	2.78
Flakiness index, %	20.10	9.38
Abrasion aggregate, %	25.72	24.36

**Table 4.** Properties of filler

Water absorption, %	2.28	
Sand equivalent, %	69.57	
Bulk specific gravity 2.59	Saturated surface dry specific gravity 2.65	Apparent specific gravity 2.76

## 2.4. Mixtures Design

The combined aggregate gradation is shown in Fig. 1. The combined aggregate gradation was kept constant for all mixtures. The mixtures were all prepared in the laboratory. Based on the preliminary experiment the optimum content of asphalt MBA was obtained at 6.25% of the total weight of the mixture. Table 5 shows the mixture by weight of AC-WC mixture without Gondorukem and with 2.5, 5.0, 7.5 and 10% Gondorukem. The weight of the Gondorukem used is based on the weight of the asphalt. Gondorukem, MBA, aggregates and filler were mixed and compacted into the cylindrical mold with capacity of 1,200 gram and diameter of 101.6 mm. The specimens were compacted with 75 blows each face by using Marshall compactor. Mixing and compaction process were carried out at temperature of 150 C.

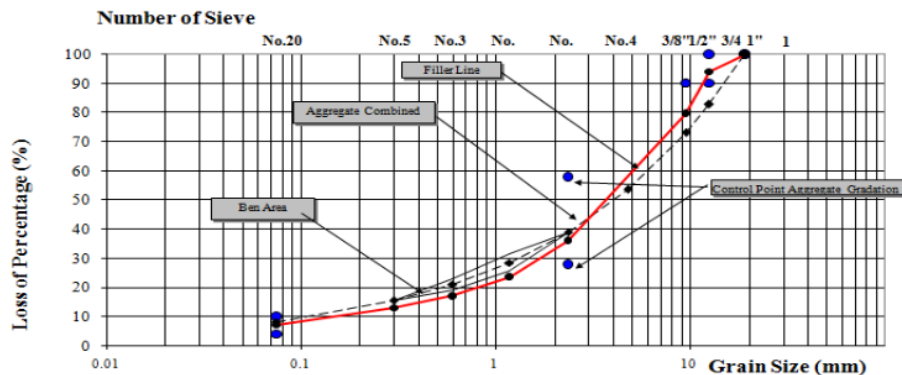


**Figure 1.** Combined Aggregates Gradation

**Table 5.** Asphalt mixture with and without Gondorukem (for 1,200 grams)

No	Description			Unit	Gondorukem content (%)				
					0.0	2.5	5.0	7.5	10.0
A	Gondorukem weight			gr	0.00	1.87	3.75	5.62	7.50
B	Modified Buton Asphalt (MBA) (6.25%)			gr	75.00	73.12	71.25	69.38	67.50
C	Aggregate combined gradation				Aggregate weight according to sieve size				
	Sieve	% loss	% restrained						
1	3/4"	100.00	0.00	gr	-	-	-	-	-
2	1/2"	96.00	4.00	gr	45.03	45.03	45.03	45.03	45.03
3	3/8"	86.93	9.07	gr	102.03	102.03	102.03	102.03	102.03
4	No. 4	63.90	23.03	gr	259.04	259.04	259.04	259.04	259.04
5	No. 8	43.56	20.34	gr	228.79	228.79	228.79	228.79	228.79
6	No. 16	28.62	14.94	gr	168.10	168.10	168.10	168.10	168.10
7	No. 30	20.76	7.87	gr	88.50	88.50	88.50	88.50	88.50
8	No. 50	15.60	5.16	gr	58.05	58.05	58.05	58.05	58.05
9	No. 100	10.79	4.80	gr	54.02	54.02	54.02	54.02	54.02
10	No. 200	8.3	2.37	gr	26.65	26.65	26.65	26.65	26.65
11	PAN	6.06	0.00	gr	94.79	94.79	94.79	94.79	94.79
	Total		100.00	gr	1,125	1,125	1,125	1,125	1,125
D	Test piece weight (A + B + C)			gr	1,200	1,200	1,200	1,200	1,200

### 3.5. Marshall Stability and Indirect Tensile Strength


The Marshall stability test was conducted on AC-WC mixture with and without Gondorukem specimens according to SNI 06-2489-1991 [12]. Figure 2 shows the Marshall stability test equipment.

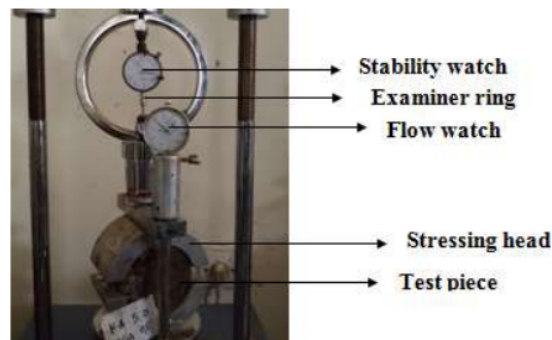

**Figure 2.** Marshall stability test equipment

ITS test was conducted on asphalt with and without Gondorukem specimens according to ASTM D6931-12 [13]. Figure 3 show ITS equipment.

4  
Stability and Indirect Tensile Strength of Asbuton Mixture with Additional Gondorukem  
(Regina Colophonia)

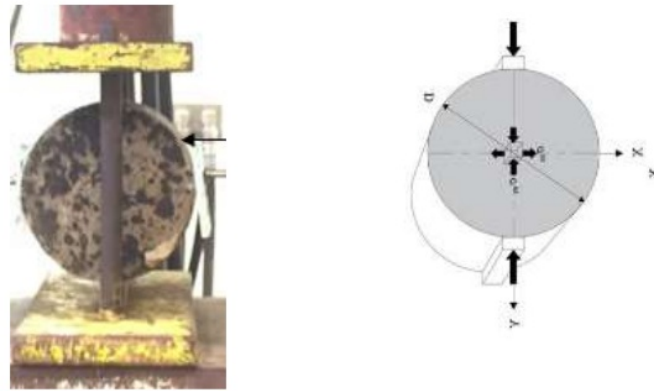

7  
Figure 3. Indirect tensile strength (ITS) equipment

### 3. RESULTS AND DISCUSSION

#### 3.1. Stability of AC-WC Mixture with and without Gondorukem

Fig. 4 shows the relationship between Gondorukem content with stability value. Three nominally identical companion specimens were produced for each AC-WC mixture under investigation to ensure repeatability of result. Each value in the Table 7 is average of three similar specimens. After compaction, the stability of the AC-WC mixture can be established due to the proper coalesces of MBA with Gondorukem so that there is an increase in the grip strength of the binder that covers the aggregate. Figure 4 indicates that the Marshall stability of AC-WC mixture increases initially, reaches a maximum value at 7.5% of Gondorukem content with corresponding with stability value of 2,884.52 kg and then decreases with increasing of Gondorukem content. This result shows that the excessive Gondorukem cannot coalesce with MBA and led to decrease the adhesive binder and particle aggregates.

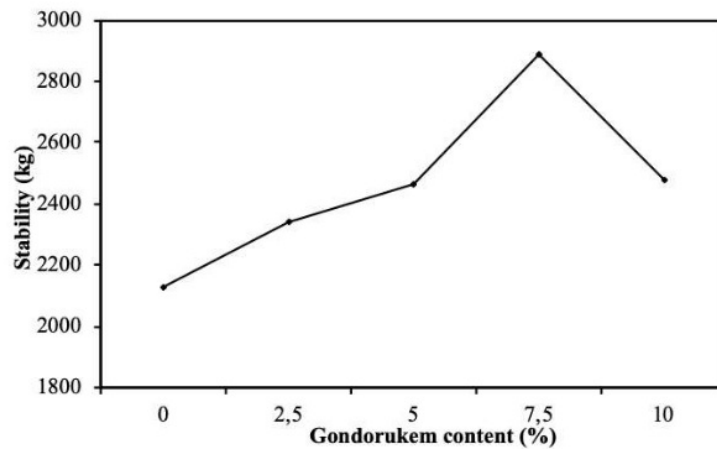


Figure 4. Relationship between Gondorukem content with stability value

### 3.2. Indirect Tensile Strength (ITS)

A series of ITS tests were performed on AC-WC with different Gondorukem content. ITS test for each mixture is repeated three times in order to verify experimental result.

Visual observation on every specimen was carried out prior to ITS test. Visual observation result on compacted specimens shows that no piling of bituminous material and filler at the lower end of the specimens. Also no bleeding occurred. These results indicate that all materials are well mixed and the compaction process allowing particles aggregate to be bound.

Fig. 5 shows relationship between Gondorukem content with ITS value. ITS of mixture without Gondorukem and mixture with 2.5%, 5%, 7.5% and 10.0% Gondorukem were 0.598 MPa, 0.678 MPa, 0.807 MPa, 0.807 MPa and 0.697 MPa and 0.1013, respectively. ITS percentages increases were 13.37%, 34.94%, 34.94% and 16.55% with 2.5%, 5%, 7.5% and 10.0% Gondorukem, respectively, compared with the corresponding value on the without Gondorukem.

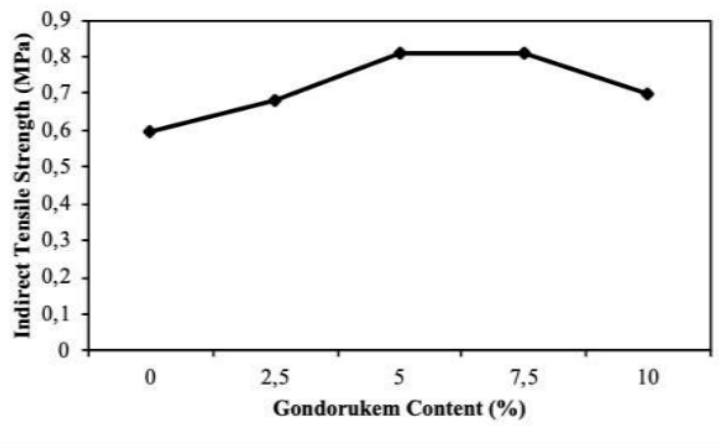


Figure 5. Relationship between Gondorukem content with ITS value

When MBA containing petroleum bitumen and Gondorukem were blended to produce a mixture, the chemical components of MBA and Gondorukem bitumen have a rearrangement, and a layer of membrane is formed to cover aggregate. As a result, AC-WC mixture containing MBA and Gondorukem had the sufficient stability with resistance to deformation and the sufficient strength to withstand the tensile load.

### 4. CONCLUSIONS

1. The utilization of Gondorukem with content from 2.5% to 10.0% increased the stability from 9% to 36% in comparison with the mixture without Gondorukem.
2. The increase in ITS was from 13.37% to 34.94% by the utilization of Gondorukem with content from 2.5% to 7.5%.

## REFERENCES

- [1] Birgisson B. *et al.* (2007). Determination and prediction of crack patterns in hot mix asphalt (HMA) mixtures. *Science Direct, Construction and Building Materials* : 664 -673.
- [2] Tayfur S., Ozen H., & Aksoy A. (2007). Investigation of rutting performance of asphalt mixtures, containing polymer modifiers. *Construction and Building Material*: 328– 337.
- [3] Suryana. A. 2003. Inventory on Solid Bitumen Sediment Using ‘Outcrop Drilling’ in Southern Buton Region, Buton Regency, Province Southeast Sulawesi, Colloquium on Result Activities of Mineral Resources Inventory. - DIM, the TA.2003, Directorate Mineral (Bandung, in Indonesian) in Tjaronge. M.W and Rita Irmawaty (2013). "Influence of Water Immersion on Physical Properties of Porous Asphalt Containing Liquid Asbuton as Bituminous Asphalt Binder". *Proceedings of 3rd International conference and Sustainable Construction Material and Technologies-SCTM, Kyoto, Japan.*
- [4] Furqon A., Properties of bituminous mixes using Indonesian natural rock asphalt, *Proceedings of 13<sup>th</sup> conference of the road engineering association of Asia and Australia (REAAA), 2005, 9–15.*
- [5] A. Gaus, Tjaronge, M.W, N. Ali, and R. Djamaluddin., (2014). Experimental Study on Characteristics of Asphalt Concrete Bearing Coarse (AC BC) Mixture Using Buton Granular Asphalt (BGA); *International Journal of Applied Engineering Research, Volume 9, Number 22 : 18037-18045.*
- [6] A. Gaus, Tjaronge, M.W., N. Ali, and R. Djamaluddin. Compressive strength of asphalt concrete binder course (AC-BC) mixture using Buton granular asphalt (BGA), *The 5<sup>th</sup> International Conference of Euro Asia Civil Engineering Forum (EACEF-5), Procedia Engineering 125 (2015) 657-662.*
- [7] Kemas Ahmad Z., Madi H., Mohamed H. A., Comparing the Performance of Granular and Extracted Binder from Buton Rock Asphalt, *Int. J. Pavement Res. Technol., 7(1) (2014).*
- [8] F. Chaeruddin, M.W. Tjaronge, M. Ramli, J. Patanduk, "Experimental study on permeable asphalt pavement used domato stone (quartzite dolomite) as course aggregate for surface layer of road pavement", *Advanced Materials Research, Vol. 935, pp. 255-258, 2014.*
- [9] Lee S.J, Amirkhanian S.N, Putman B.J and Kim K.W., Laboratory Study of the Effect of Compaction on the Volumetric and Rutting Properties of CRM Asphalt Mixture, *Journal of Materials in Civil Engineering ASCE 0899-1561 (2007) 19:12 (1079).*
- [10] Navarro F.M and Games C.R., Influence of Crumb on the Indirect Tensile Strength and Stiffness Modulus of Hot Bituminous Mixes, *Journal of Materials in Civil Engineering ASCE (2012) 10.1061/(ASCE) MT.1943-5533.0000436*
- [11] Stephen B., *The Shell Bitumen Handbook, University of Nottingham, May 2015.*
- [12] Md Rashadul Islam, Mohammad Imran Hossain and Rafiqul A. Tarefder, A study of asphalt aging using Indirect Tensile Strength test, *Construction and Building Materials, Volume 95, 1 October 2015, Pages 218–223.*
- [13] Shaowen Du, Interaction mechanism of cement and asphalt emulsion in asphalt emulsion mixtures, *Materials and Structures (2014) 47:1149–1159.*

---

% **11**

SIMILARITY INDEX

%

INTERNET SOURCES

% **11**

PUBLICATIONS

%

STUDENT PAPERS

---

## PRIMARY SOURCES

- 
- 1** M Tumpu, M W Tjaronge, A R Djameluddin, A A Amiruddin, La One. "Effect of limestone and buton granular asphalt (BGA) on density of asphalt concrete wearing course (AC-WC) mixture", IOP Conference Series: Earth and Environmental Science, 2020 %**2**  
Publication
- 
- 2** Gaus, Abdul, Tjaronge M.W., Nur Ali, and Rudy Djameluddin. "Compressive Strength of Asphalt Concrete Binder Course (AC-BC) Mixture Using Buton Granular Asphalt (BGA)", Procedia Engineering, 2015. %**2**  
Publication
- 
- 3** Birgisson, B.. "Determination and prediction of crack patterns in hot mix asphalt (HMA) mixtures", Engineering Fracture Mechanics, 200802 %**1**  
Publication
- 
- 4** Ouming Xu, Zhenjun Wang, Rui Wang. "Effects of aggregate gradations and binder contents on engineering properties of cement emulsified %**1**

## asphalt mixtures", Construction and Building Materials, 2017

Publication

---

5

ALI, N., L. SAMANG, M. W. TJARONGE, and A. RAHMAN DJAMALUDDIN. "INFLUENCE OF SEA WATER ON THE MECHANICAL PROPERTIES OF POROUS ASPHALT CONTAINING LIQUID ASBUTON", Asian And Pacific Coasts 2011, 2011.

Publication

---

% 1

6

Islam, Md Rashadul, Mohammad Imran Hossain, and Rafiqul A. Tarefder. "A study of asphalt aging using Indirect Tensile Strength test", Construction and Building Materials, 2015.

Publication

---

% 1

7

Teresa López-Montero, João Crucho, Luís Picado-Santos, Rodrigo Miró. "Effect of nanomaterials on ageing and moisture damage using the indirect tensile strength test", Construction and Building Materials, 2018

Publication

---

<% 1

8

Chairuddin, Firdaus, M.W. Tjaronge, Muhammad Ramli, and Johannes Patanduk. "Experimental Study on Permeable Asphalt Pavement Used Domato Stone (Quartzite Dolomite) as Course Agregate for Surface Layer of Road Pavement", Advanced Materials

<% 1

## Research, 2014.

Publication

---

9

Ahmed I. Nassar, Mahmoud Khashaa Mohammed, Nicholas Thom, Tony Parry. "Mechanical, durability and microstructure properties of Cold Asphalt Emulsion Mixtures with different types of filler", Construction and Building Materials, 2016

Publication

---

<% 1

10

RILEM Bookseries, 2016.

Publication

---

<% 1

11

La One, M W Tjaronge, R Irmawaty, M Hustim. "Effect of buton's granular asphalt gradation on marshall stability of cold emulsified asphalt mixtures under wet condition", IOP Conference Series: Earth and Environmental Science, 2020

Publication

---

<% 1

12

M. Arabani, F. Moghadas Nejad, A.R. Azarhoosh. "Laboratory evaluation of recycled waste concrete into asphalt mixtures", International Journal of Pavement Engineering, 2013

Publication

---

<% 1

13

Perviz Ahmedzade, Mehmet Yilmaz. "Effect of polyester resin additive on the properties of asphalt binders and mixtures", Construction and Building Materials, 2008

<% 1

14

Carlos J. Slebi-Acevedo, Pedro Lastra-González, Daniel Castro-Fresno, Moises Bueno. "An experimental laboratory study of fiber-reinforced asphalt mortars with polyolefin-aramid and polyacrylonitrile fibers", Construction and Building Materials, 2020

Publication

<% 1

15

"ICSCEA 2019", Springer Science and Business Media LLC, 2020

Publication

<% 1

---

EXCLUDE QUOTES ON  
EXCLUDE BIBLIOGRAPHY ON

EXCLUDE MATCHES < 5 WORDS