

IJE_Volume_35_Issue_1_Pages_1 02-111.pdf

by

Submission date: 21-Oct-2022 12:46PM (UTC+0700)

Submission ID: 1931306625

File name: IJE_Volume_35_Issue_1_Pages_102-111.pdf (1.13M)

Word count: 5585

Character count: 27954



Precast Concrete Column Beam Connection Using Dowels Due to Cyclic Load

H. A. Tumengkol*, R. Irmawaty, H. Parung, A. Amiruddin

Department of Civil engineering, Universitas Hasanuddin Indonesia

PAPER INFO

Paper history:

Received 21 August 2021

Received in revised form 22 September 2021

Accepted 05 October 2021

Keywords:

Column Beam Connection

Cyclic Load

Dowels Due

Earthquake-resistant Buildings

Precast Concrete

A B S T R A C T

The beam-column connection plays an important role in the building structure, especially when the load is cyclic. The main problem that must be solved is the beam and column connection panels. The purpose of this study was to analyze the characteristics of the hysteresis loop of the displacement load relationship with the control displacement of the precast beam-column connection due to cyclic loading. The research method used is the experimental method with a measurable object design test and a special testing method. The results of this study indicate that normal concrete has a compressive strength of 26.43 MPa, while grouted concrete has a compressive strength of 36.97 MPa. The findings of this study also show that the bond stress grouted concrete increases by 102.4% from normal concrete for D13 diameter screw reinforcement, while for D16 diameter, the adhesive stress increases by 51.63%. The findings of this study also show that in the ultimate condition, the load obtained the tensile load is 13.58 kN with a displacement of 87.528 mm, while the compressive load is 12.62 kN with a displacement of 88.30 mm. This study concludes that the behavior of precast beam-column joints with dowels is stronger in resisting cyclic loads.

doi: 10.5829/ije.2022.35.01a.09

NOMENCLATURE

v	Horizontal components of velocity (m/s)
C_c	Cunningham correction factor
C_k	Discrete lattice velocity in direction (k)
C_s	Speed of sound in Lattice scale
d_p	Particle diameter (μm)
f_k	Equilibrium distribution function
g	Gravity (m/s^2)
$\phi y = \Delta y$	Displacement at melting L (test object height)
$\phi u = \Delta u$	Ultimate current shift L (test object height)
P_u	Beban ultimate
P_y	Tegangan leleh baja
ϕy	Perpindahan t
$S = \rho^p / \rho^g$	Particle Specific density
U	Horizontal components of velocity (m/s)
V	Vertical components of velocity (m/s)
U_i, U_j	Random numbers between 0 and 1
Greek Symbols	
ρ	Density (kg/m^3)
τ	Lattice relaxation time
$\tau_p = \frac{\rho^p c_p (d_p)^2}{18\mu}$	Particle relaxation time (s)
Δt	Lattice time step
ν	Kinematic viscosity (m^2/s)
λ	Gas mean free path (μm)
Subscripts	
p	Particle
g	Gas

1. INTRODUCTION

Structural design is very important to pay attention to the column beam connection elements as the main point to withstand cyclic loads. Cyclic loads can be caused by earthquakes. The part of the building structure that is

susceptible to cyclic loading is at the connection of the beam and column panels [1]. This is due to the specific nature of the radiated energy and the occurrence of very large shear forces, especially at the beam-column connection. These shear forces can frustrate the joint panel core either because the shear capacity is exceeded

*Corresponding Author Email: tumengkolherman@yahoo.co.id (H. A. Tumengkol)

or because the reinforcement bonds in the joint are damaged.

The beam-column connection is a vital component in a building structure. This section is very important because it has a major role in transferring the forces in one element to other elements in the structure [2-3]. Due to the influence of lateral forces such as cyclic loads, these beam-column joints experience greater shear and horizontal forces than adjacent beam and column elements [4-6]. The flow of force through the beam-column joint can be disrupted if this connection is not able to provide adequate shear strength. If the shear capacity at this interface is insufficient, cracks can occur, and eventually, structural failure occurs.

The connection of precast concrete beam-columns is one solution to anticipate the failure of the building structure. Precast concrete is a component or structural element that is not cast at the place where the element is installed, but is cast in a place where the casting process and maintenance are carried out properly according to existing methods [7-8]. Precast concrete has many advantages compared to conventional concrete, including being able to speed up project execution time [5]. The many advantages of precast concrete make its use increased in recent years.

Hysteresis characteristics of load-displacement relationship loop with control displacement of precast beam-column joints due to cyclic loading [9-11] are the problem that arises is the difficulty of mapping the load-displacement characteristics of the beam of building precast column beams due to cyclic loading [12-14]. Precast beam-column joints, which are specific to the area of connection of precast parts. The construction will then be given a cyclic loading. The purpose of this study was to analyze the hysteresis characteristics of the load-displacement relationship with the controlled displacement of the precast beam-column connection due to cyclic loading. This study is intended to examine the behavior of beam-column joints for each model made. The results of this study can be a recommendation or input to construction implements regarding the behavior and concept of connection planning in precast concrete.

2. SPECIMENS AND TESTING METHOD

2.1. Test Object Design For the beam-column connection specimen, there are 3 models, namely monolith beam and column, grout connection with 2 pegs and grout connection with 4 pegs. (Figures 1, 2 and 3).

For columns measuring 30 cm x 30 cm with a length (ln) of 295 cm. As for the beam measuring 20 cm x 30 cm with a length of 145 cm.

The test was carried out at the Structure and Materials Laboratory, Faculty of Engineering, Hasanuddin University. Cyclic testing equipment used with an

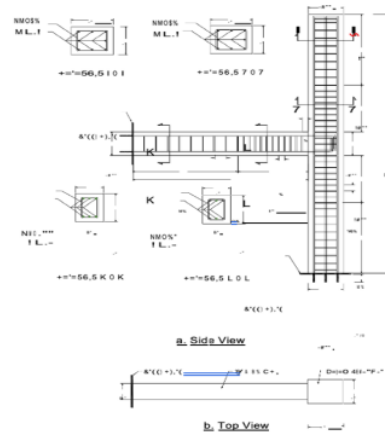


Figure 1. Monolith column beam test object (BN)

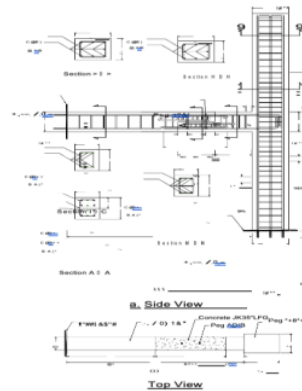


Figure 2. Test object for connection of 2 pegs (BG-1)

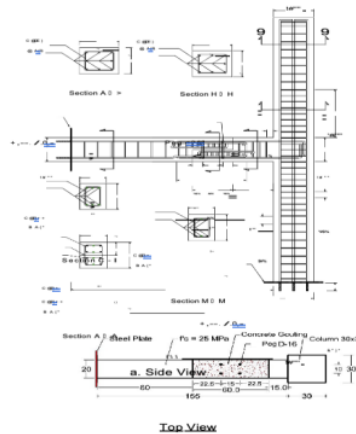


Figure 3. Test object 4 stake connection (BG-2)

actuator capable of 1500 kN with a maximum displacement of ± 20 cm.

The setup for testing the BN, BG-1, and BG-2 specimens is shown in Figure 4.

In addition, at the bottom, a plate with a thickness of 2 cm is installed and mounted on a strong floor with a thickness of 1.5 m through a rod measuring 1.5” (38 mm).

2. 2. Testing Method

1. Strain Gauge in Reinforcement and Concrete

For the strain gauge installed on steel reinforcement to determine whether the reinforcement has experienced yielding and on the concrete to determine whether the concrete has reached its ultimate condition.

For strain gauge reinforcement type FLK-6-11-5L installed on horizontal reinforcement and transverse reinforcement (see Figure 5).

2. LVDT

To measure displacement of the beam-column joint test object, a linear variable displacement transducer (LVDT) was installed.

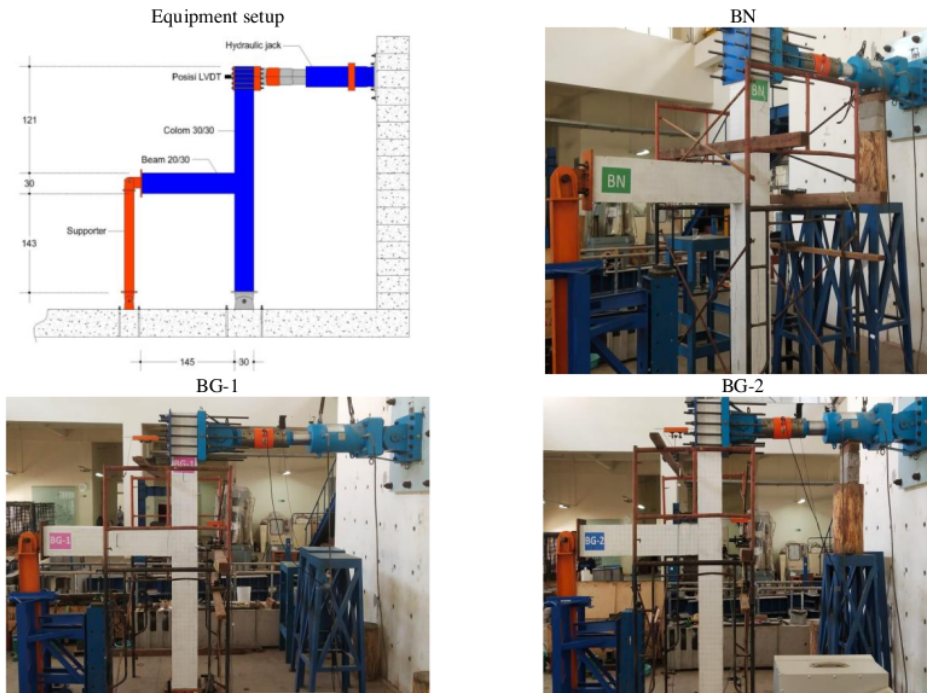


Figure 4. Cyclic testing equipment setup

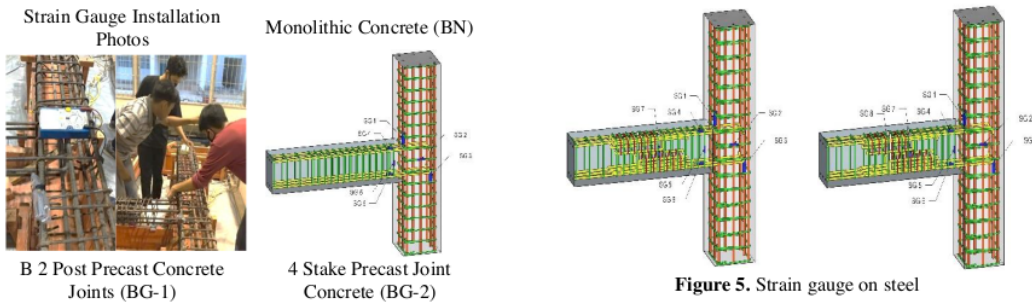


Figure 5. Strain gauge on steel

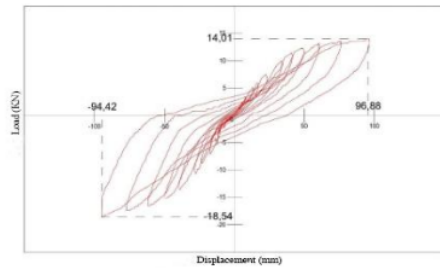


Figure 9. Relationship of load – displacement due to cyclic load on the test object BG-1

the ultimate compressive load is 16.41 kN with a displacement of 98.90 mm. The load at the first yield is 13.11 kN with a displacement of 47 mm. For the first crack, the load is 4.30 kN and the displacement is 9.91 mm (see Figure 10).

Load Capacity of Monolith Beam-Column Joints and Precast Beam-Column Joints with Pegs

From Table 1, it can be concluded that the load capacity at the time of the first crack for precast beam-column joints is greater than the load capacity of monolith beam-column joints. The load capacity of precast 4-post beam-column joints is greater than the load capacity of 2-post precast joints.

The same applies to load capacity at the time of the first yield. For the load capacity of the precast beam-column connection of 2 pegs more than the precast beam-column connection of 4 pegs and monolith (Figure 10 and Table 2 show the ultimate load capacity for monolithic and precast beam-column connections using dowels.

In the ultimate condition, the load capacity of precast beam-column joints with dowels is more than the load capacity of monolith beam-column connections. At the compression load, the load capacity of the precast beam-column connection with 2 posts increased by 13.9% and for the precast beam-column connection with 4 posts increased by 30% compared to the load capacity of the

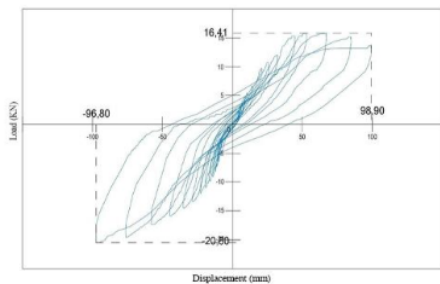


Figure 10. Load-displacement relationship due to cyclic load on the BG-2 test object

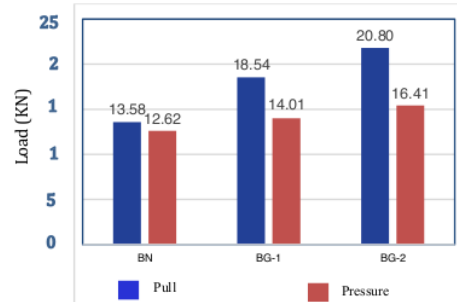


Figure 11. Ultimate load of SBK BN, BG-1, and BG-2 specimens

TABLE 2. The increase in the P_u value of precast SBK against monolithic SBK

Load	BG – 1	BG – 2
Pressure	13.9 %	30 %
Pull	36,5 %	53,2 %

monolith beam-column connection. At the tensile load, the load capacity for the precast beam-column connection with 2 posts increased by 36.5% and for the precast beam-column connection with 4 posts, it increased by 53.2% compared to the load capacity of the monolith beam-column connection.

In general, the increase in load capacity at the precast beam-column connection is due to the area being grouted with a strength of 36.97 Mpa, which is greater than the compressive strength of the concrete used in these elements. The greatest strength in the area causes the connection to become stiffer so that the load capacity increases [15-18].

3. 2. Crack Pattern Figures 12(a), 13(a), and 14(a) are images of the initial crack pattern at a drift of 0.5% for monolithic connections and precast 2 (two) and 4 (four) posts. More cracks occurred in monolith joints compared to BG-2 precast (4 pegs) and BG-1 precast (2 pegs) joints. For cracks as a whole occur in the beam area. Figures 5(b), 6(b), and 7(b) are images of the fracture pattern of monolith joints and precast joints at a drift of 0.75%. For cracks that occur more tightly in the beam area for monolithic connections (BN) when compared to 2-post precast connections (BG-1) and 4-post precast connections (BG-2). In the column, especially the lower column, the cracks that occur are more for the BG-1 and BG-2 precast joints when compared to the monolith (BN) connection [19-22].

Figures 12c, 13c, and 14c are crack patterns for monolithic and precast beam-column joints at 1% drift. In this condition, the crack pattern is almost the same as

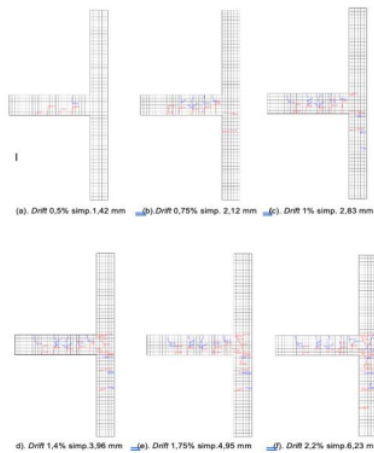


Figure 12. Pattern of monolithic beam-column (BN) joint cracks

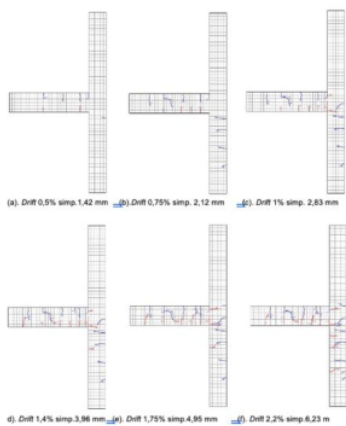


Figure 13. Crack pattern of 2-post precast beam-column connection (BG-1)

the crack pattern that occurs at a drift of 0.75% with an increase in the number of cracks.

Figures 10(d), 11(d), and 12(d) show the crack patterns for beam-column joints at 1.4% drift. Cracks are more common in the beam area for monolithic beam-column (BN) connections and precast beam-column joints BG-1 and BG-2.

In the 36th column, cracks have started to increase but only occur at the bottom of the column. Especially in the monolith beam-column connection, cracks have occurred at the beam-column meeting area.

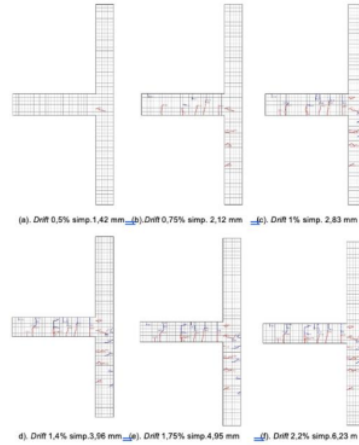


Figure 14. Crack pattern of 4-post precast beam-column connection (BG-2)

3

Figures 12(e), 13(e), and 13(f) show the crack pattern for beam-column joints with a drift of 1.75%. The crack pattern was almost the same with a 1.4% drift and an increasing number of cracks. In this condition, cracks have occurred in the area where the beam-column meets for the precast connection of 2 posts (BG-1) and 4 posts (BG-2).

Figures 12(f), 13(f), and 14(f) are crack pattern images for joints at 2.2% drift. The crack pattern model is the same as the crack pattern at 1.75% drift with more cracks.

3. 3. Ductility of Beam-column Joints

This section discusses the behavior of beam-column joints in relation to ductility. Ductility is related to the displacement that occurs in the ultimate condition, namely the condition when the structure collapses and the displacement that occurs in the first yield condition of the reinforcement.

The displacement at the ultimate condition and yielding condition in the reinforcement is obtained from the load hysteretic curve – displacement when given a cyclic load [23]. Parameters related to ductility are displacements, especially in the first yield condition of the reinforcement (Δ_y) and in the ultimate condition, namely structural failure (Δ_u). To calculate displacement ductility, displacement parameters are used, while curvature ductility uses curvature value parameters or cross-sectional curvature and load values due to cyclic loads.

24

3. 4. Displacement Ductility

Table 3 shows the displacement values at the first yield condition of the

reinforcement and at the ultimate condition. The values of Δ_y and Δ_u can be seen in the Backbone curve.

In yield conditions, the displacements that occur at the monolithic beam-column connection (BN), the precast 2-pin beam-column connection (BG-1), and the 4-post precast beam-column connection (BG-2) are 37.44 mm, 42.66 mm, and 47 mm, respectively. The ductility value is calculated based on the ratio of the displacement value in the ultimate condition to the yield condition. From Table 3, the ductility values for the BN, BG-1, and BG-2 specimens are obtained, 2.34, 2.21 and 2.06, respectively.

From Figure 15, it can be seen that the ductility value of the BN test object is 2.34, while the BG-1 test object is 2.21 and the BG-2 test object is 2.06. Based on this value, it can be concluded that the monolithic beam-column connection (BN) has a higher ductility value than the precast beam-column connection using dowels (BG-1 and BG-2).

For the ductility value of the precast beam-column connection of 2 pegs, it is 0.94 times the ductility value of the monolithic beam-column connection or reduced by 5.56%. Meanwhile, in the precast beam-column connection with 4 pegs, the ductility value is 0.88 times or reduced by 12%. For the precast beam-column connection with 2 pegs, the ductility value is greater than the precast beam-column connection with 4 posts.

The ductility of precast beam-column joints using dowels is smaller than the ductility of monolithic beam-column joints due to the presence of grouting in the beam connection area which makes the cross-section stiffer due to the greater compressive strength of the concrete in that area [24-25].

TABLE 3. Displacement in yield and ultimate conditions

SBK Test Object	First Yield	Ultimate	Ductility
	Δ_y (mm)	Δ_u (mm)	
BN	37.44	87.58	2.34
BG-1	42.66	94.42	2.21
BG-2	47	96.80	2.06

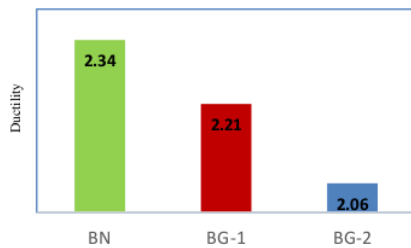


Figure 15. Ductility values for BN, BG-1, BG-2. Specimens

3. 1. 2. Classification of Ductility of Beam-column Joints Table 4 shows the classification of ductility according to ASCE 41-17.

ASCE 41-17 divides ductility according to 3 categories, namely low ductility, moderate ductility, and high ductility. For low ductility, it has a value of less than 2, while medium ductility has a value between 2 to 4. For high ductility, it has a value of more than 4 [26-27].

From Table 4, for monolithic beam-column connection (BN) and precast beam-column connection (BG-1 and BG-2), the ductility values are 2.34, 2.21, and 2.06, respectively. Based on these values, it can be concluded that the specimens for monolithic and precast beam-column joints are categorized as structural elements with moderate ductility values.

3. 5. Curvature The curvature ductility is calculated based on the load and displacement relationship (drift). Generally, the load is normalized to the load at yielding conditions, while the displacement can be converted to the value of curvature (curvature), drift (in units of %), or chord rotation (rotation).

Normalized load and curvature values for BN, BG-1, and BG-2 specimens are presented in Table 5. Note:

$$* \phi_y = \frac{\Delta y (\text{Displacement at melting})}{L (\text{test object height})}$$

$$** \phi_u = \frac{\Delta u (\text{Ultimate current shift})}{L (\text{test object height})}$$

For BN specimens, the curvature value of the melting condition is 0.013 and in the ultimate condition is 0.031. In the BG-1 test object, the curvature value is 0.015 for

TABLE 4. Classification of test object ductility according to ASCE 41-17

Test Object	Ductility	Category	ASCE 41-17
BN	2.34	Moderate ductility	< 2, low ductility
BG-1	2.21	Moderate ductility	2 to 4, moderate ductility
BG-2	2.06	Moderate ductility	> 4, high ductility

TABLE 5. Load and curvature for BN, BG-1, BG-2. specimens

SBK Test Object	P_y (kN)	P_u (kN)	P_u/P_y	Δ_y (mm)	ϕ_y^*	Δ_u (mm)	ϕ_u^{**}
BN	11.00	13.58	1.23	37.44	0.013	87.58	0.031
BG-1	12.89	18.54	1.43	42.66	0.015	94.42	0.033
BG-2	13.11	20.80	1.59	47	0.016	96.80	0.034

the melting condition and 0.033 for the ultimate condition. While in BG-2, the curvature value of the melting condition is 0.016 and in the ultimate condition is 0.034.

Figure 16, shows the curvature ductility for the specimens BN, BG-1, BG-2.

In the melting condition, the curvature ductility for the specimens BN, BG-1, and BG-2 were 0.013, 0.015, and 0.016, respectively. From this value, it can be seen that the curvature ductility value for precast beam-column joints using dowels is more than the curvature ductility value for monolith beam-column connections or an increase of 15.38% (BG-1 against BN) and 20% (BG-2). Against BN).

Based on ASCE 41-17 (Tables 10-11), the required ductility value under life safety (LS) conditions is 0.01. The curvature ductility values for the specimens BN, BG-1, and BG-2 are more than the values required in ASCE 41-17. This means that beam-column connections, both monolithic and precast using dowels, have good performance in carrying earthquake loads under moderate seismic conditions (medium earthquakes).

In the collapse prevention (CP) condition, the curvature ductility value required in ASCE 41-17 is 0.015, while the curvature ductility value for BN, BG-1, and BG-2 is more than the required value. It can be concluded that beam-column connections, both monolithic and precast, have excellent performance in carrying earthquake loads under severe seismic conditions (strong earthquakes).

From the results of the discussion in the previous section, it can be explained that the empirical findings are as follows:

Precast beam-column joints with dowels have a greater load capacity than monolithic beam-column joints. For precast SBK 2 pegs increased 11.01% - 36.52% and SBK 4 pegs increased 30.03% - 53.2% due to compressive and tensile loads.

The ductility value for monolithic SBK is greater than that of precast SBK with pegs, but the curvature ductility of precast SBK is still higher than normal SBK. SBK monolith and precast have good performance at moderate and strong earthquake levels, according to ASCE 41-17.

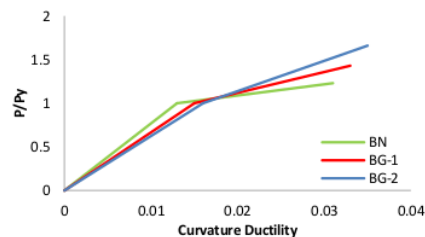


Figure 16. Bending ductility of BN, BG-1, BG-2

The stiffness degradation for precast SBK with 2 pins (5.23%) and 4 posts (4.90%) is smaller than monolith SBK (5.36%), stating that precast SBK with pegs is stiffer compared to SBK monolith.

Precast beam-column joints using dowels have a higher energy dissipation value than monolith beam-column joints, an increase of 3.42% for SBK 2 pegs and 7.94% for SBK 4 pegs.

For the connection of precast concrete column beams with dowels, it has good performance in terms of strength, ductility, stiffness, and energy dissipation. The connection of precast concrete column beams using 2 pegs is good enough to be applied at work, this is also to facilitate implementation in the field.

4. CONCLUSION

This study concludes that the hysteresis characteristics of the load-displacement relationship with displacement control of precast beam-column joints are very good for cyclic loads. The fact that the results of laboratory tests have shown that the capacity of monolithic beam-column (BN) connections is at a compressive load of 12.62 kN, while the load for 2 precast SBK increases by 11.01% - 36.52% to a load value of 18.54 kN with a deviation of 94.42 mm, and for 4 post precast, SBK increased by 30.03% - 53.2% of ultimate tensile load is 20.80 kN and the displacement is 96.80 mm compared to the load capacity of SBK monolith. This study concludes that by using 2 and 4 pins in the beam-column connection, the results are better. This study also concluded that the ductility value of SBK precast 2 pegs was 2.21 smaller than the actual SBK monolith ductility value of 2.34 or decreased by 5.56%. Meanwhile, in precast SBK 4 pegs the ductility value was 2.06 or decreased by 8.55%. Thus, this study concludes that the use of posts with 2 and 4 posts can reduce the ductility value.

5. REFERENCES

- Breccolotti, M., Gentile, S., Tommasini, M., Materazzi, A.L., Bonfigli, M.F., Pasqualini, B., Colone, V., Giansesini, M., "Beam-column joints in continuous RC frames: Comparison between cast-in-situ and precast solutions," *Engineering Structures*, Vol. 127, (2016), 129-144. doi: 10.1016/j.engstruct.2016.08.018.
- Ma, F., Deng, M., Yang, Y., "Experimental study on internal precast beam-column ultra-high-performance concrete connection and shear capacity of its joint," *Journal of Building Engineering*, (2021), 103204. doi: https://doi.org/10.1016/j.job.2021.103204.
- Wu, B., Peng, C.W., Zhao, X.Y., "Cyclic loading tests of semi-precast circular steel tubular columns incorporating precast segments containing demolished concrete lumps," *Engineering Structures*, Vol. 211, (2020), 110438. doi: https://doi.org/10.1016/j.engstruct.2020.110438.

4. Xie, L., Wu, J., Zhang, J., Liu, C., "Experimental study of mechanical properties of beam-column joint of a replaceable energy-dissipation connector-precast concrete frame," *Journal of Building Engineering*, Vol. 43, (2021), 102588. doi: <https://doi.org/10.1016/j.jobe.2021.102588>.
5. Yan, Q., Chen, T., Xie, Z., "Seismic experimental study on a precast concrete beam-column connection with grout sleeves," *Engineering Structures*, Vol. 155, (2018), 330-344. doi: <https://doi.org/10.1016/j.engstruct.2017.09.027>
6. Cai, X., Pan, Z., Zhu, Y., Gong N., Wang, Y., "Experimental and numerical investigations of self-centering post-tensioned precast beam-to-column connections with steel top and seat angles," *Engineering Structures*, Vol. 226, (2021), 111397. doi: <https://doi.org/10.1016/j.engstruct.2020.111397>.
7. Kataoka, M.N., Ferreira, M.A., de Cresce E.D., Ana, L.H., "Nonlinear FE analysis of slab-beam-column connection in precast concrete structures," *Engineering Structures*, Vol. 143, (2017), 306-315. doi: <https://doi.org/10.1016/j.engstruct.2017.04.028>.
8. Zhang, J., Ding, C., Rong, X., Yang, H., Li, Y., "Development and experimental investigation of hybrid precast concrete beam-column joints" *Engineering Structures*, Vol. 219, (2020), 110922. doi: <https://doi.org/10.1016/j.engstruct.2020.110922>.
9. Li, Z., Qi, Y., Teng, J., "Experimental investigation of prefabricated beam-to-column steel joints for precast concrete structures under cyclic loading," *Engineering Structures*, Vol. 209, (2020), 110217. doi: <https://doi.org/10.1016/j.engstruct.2020.110217>.
10. Wang, H., Marino, E.M., Pan, P., Liu, H., Nie, X., "Experimental study of a novel precast prestressed reinforced concrete beam-to-column joint," *Engineering Structures*, Vol. 156, (2018), 68-81. doi: <https://doi.org/10.1016/j.engstruct.2017.11.011>.
11. Kang, S.B., Tan, K.H., "Behaviour of precast concrete beam-column sub-assemblages subject to column removal," *Engineering Structures*, Vol. 93, (2015), 85-96. doi: <https://doi.org/10.1016/j.engstruct.2015.03.027>.
12. Hu, G., Huang, W., Xie, H., "Mechanical behavior of a replaceable energy dissipation device for precast concrete beam-column connections," *Journal of Constructional Steel Research*, Vol. 164, (2020), 105816. doi: <https://doi.org/10.1016/j.jcsr.2019.105816>.
13. Singhal, S., Chourasia, A., Kajale, Y., "Cyclic behaviour of precast reinforced concrete beam-columns connected with headed bars," *Journal of Building Engineering*, Vol. 42, (2021), 103078. doi: <https://doi.org/10.1016/j.jobe.2021.103078>.
14. Yang, J., Guo, T., Chai, S., "Experimental and numerical investigation on seismic behaviours of beam-column joints of precast prestressed concrete frame under given corrosion levels," *Structures*, Vol. 27, (2020), 1209-1221. doi: <https://doi.org/10.1016/j.istruc.2020.07.007>.
15. Ghayeb, H.H., Razak, H.A., Sulong, N.H.R., "Development and testing of hybrid precast concrete beam-to-column connections under cyclic loading," *Construction and Building Materials*, Vol. 151, (2017), 258-278. doi: <https://doi.org/10.1016/j.conbuildmat.2017.06.073>.
16. Do, T. A., Chen, H. L., Leon, G., Nguyen, T.H., "A combined finite difference and finite element model for temperature and stress predictions of cast-in-place cap beam on precast columns," *Construction and Building Materials*, Vol. 217, (2019), 172-184. doi: <https://doi.org/10.1016/j.conbuildmat.2019.05.019>.
17. Li, D., Wu, C., Zhou, Y., Luo, W., Lie, W., "A precast beam-column connection using metallic damper as connector: Experiment and application," *Journal of Constructional Steel Research*, Vol. 181, (2021), 106628. doi: <https://doi.org/10.1016/j.jcsr.2021.106628>.
18. Nzabonimpa, J.D., Hong, W.K., Kim, J., "Experimental and non-linear numerical investigation of the novel detachable mechanical joints with laminated plates for composite precast beam-column joint," *Composite Structures*, Vol. 185, (2018), 286-303. doi: <https://doi.org/10.1016/j.compstruct.2017.11.024>.
19. Wang, H., Marino, E.M., Pan, P., "Design, testing and finite element analysis of an improved precast prestressed beam-to-column joint," *Engineering Structures*, Vol. 199, (2019), 109661, doi: <https://doi.org/10.1016/j.engstruct.2019.109661>.
20. Gou, S., Ding, R., Fan, J., Nie, X., Zhang, J., "Seismic performance of a novel precast concrete beam-column connection using low-shrinkage engineered cementitious composites," *Construction and Building Materials*, Vol. 192, (2018), 643-656. doi: <https://doi.org/10.1016/j.conbuildmat.2018.10.103>.
21. Guerrero, H., Rodriguez, V., Escobar, J.A., Alcocer, S.M., Bennetts, F., Suarez, M., "Experimental tests of precast reinforced concrete beam-column connections," *Soil Dynamics and Earthquake Engineering*, Vol. 125, (2019), 105743. doi: <https://doi.org/10.1016/j.soildyn.2019.105743>.
22. Li, S. Q., Yu, T. L., Chen, Y. S. "Comparison of macroseismic intensity scales by considering empirical observations of structural seismic damage", *Earthquake Spectra*, Vol. 37, No. 1, (2021), 449-485. DOI: 10.1177/8755293020944174.
23. Li, S. Q., Yu, T. L., Jia, J. F. "Empirical seismic vulnerability and damage of bottom frame seismic wall masonry structure: A case study in Dujiangyan (China) region", *International Journal of Engineering, Transactions C: Aspects*, Vol. 32, No. 9, (2019), 1260-1268. DOI: 10.5829/ije.2019.32.09c.05
24. ACI Committee 318-89, "Building Code Requirements for Reinforce Concrete (ACI 318-89)," Illinois, (1989)
25. Li, S. Q., Yu, T. L., Jia, J. F. "Investigation and analysis of empirical field seismic damage to bottom frame seismic wall masonry structure", *International Journal of Engineering, Transactions B: Applications*, Vol. 32, No. 8, (2019), 1082-1089. DOI: 10.5829/ije.2019.32.08b.04.
26. ACI, "Recommendations for Design of Beam-Column Connections in Monolithic Reinforced Concrete Structures," ACI 352R-02, American Concret Institute, Farmington Hills, MI., (2002).
27. ASTM, "Concrete and Material, Annual Book of ASTM Standart," Vol. 04 No.02, (1993) Philadelphia

Persian Abstract

چکیده

اتصال تیر و ستون نقش مهمی در ساختار ساختمان ایفا می کند ، به ویژه هنگامی که بار چرخه ای است . مشکل اصلی که باید حل شود ، پائل های اتصال تیر و ستون است . هدف از این مطالعه تجزیه و تحلیل ویژگی های حلقه پسماند رابطه بار جابجایی با جابجایی کنترل اتصال تیر و ستون پیش ساخته به دلیل بازگذاری چرخه ای بود . روش تحقیق مورد استفاده روش آزمایشی با آزمون طراحی شیء قابل اندازه گیری و روش آزمایش ویژه است . نتایج این مطالعه نشان می دهد که بتن معمولی دارای مقاومت فشاری ۲۶.۴۳ مگاپاسکال است ، در حالی که بتن دوغابدار دارای مقاومت فشاری ۳۶.۹۷ مگاپاسکال است . یافته های این مطالعه همچنین نشان می دهد که بتن دوغاب تنش پیوند ۱۰۲.۴ درصد از بتن معمولی برای تقویت پیچ با قطر D13 افزایش می یابد ، در حالی که برای قطر D16 ، تنش چسبندگی به میزان ۵۱.۶۳ درصد افزایش می یابد . یافته های این مطالعه همچنین نشان می دهد که در شرایط نهایی ، بار به دست آمده در بار کششی ۱۳۸/۵۸ کیلو نیوتن با جابجایی ۵۸/۸۷ میلی متر است ، در حالی که بار فشاری ۱۲/۶۲ کیلو نیوتن با جابجایی ۸۸/۳۰ میلی متر است . این مطالعه نتیجه می گیرد که رفتار اتصالات تیر و ستون پیش ساخته با رولپلاک در مقاومت در برابر بارهای چرخه ای قوی تر است .

ORIGINALITY REPORT

16%

SIMILARITY INDEX

%

INTERNET SOURCES

16%

PUBLICATIONS

%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|---|----|
| 1 | H Tumengkol, R Irmawaty, H Parung dan, A Amiruddin. "Provisions for seismic detailing of column-beam connections according to SNI 2847:2019", IOP Conference Series: Earth and Environmental Science, 2021
Publication | 2% |
| 2 | H. Hassanzadeh Afrouzi, M. Farhadi, A. Abouei Mehrizi. "Numerical simulation of microparticles transport in a concentric annulus by Lattice Boltzmann Method", Advanced Powder Technology, 2013
Publication | 1% |
| 3 | Advances in Structural Engineering, 2015.
Publication | 1% |
| 4 | R. Vidjeapriya, K. P. Jaya. "Experimental Study on Two Simple Mechanical Precast Beam-Column Connections under Reverse Cyclic Loading", Journal of Performance of Constructed Facilities, 2013
Publication | 1% |
-

5

Weichen Xue, Xinyu Hu, Lingjie Dai, Bin Zhu.
"Cyclic behavior of semi-rigid precast concrete
beam-to-column subassemblages with rapid
assembly connections", Journal of Building
Engineering, 2021

Publication

1 %

6

Lee, J.Y.. "Strength deterioration of reinforced
concrete beam-column joints subjected to
cyclic loading", Engineering Structures, 200909

Publication

1 %

7

Le-Trung, K.. "Experimental study of RC
beamcolumn joints strengthened using CFRP
composites", Composites Part B, 201001

Publication

<1 %

8

Marco Breccolotti, Santino Gentile, Mauro
Tommasini, Annibale Luigi Materazzi et al.
"Beam-column joints in continuous RC
frames: Comparison between cast-in-situ and
precast solutions", Engineering Structures,
2016

Publication

<1 %

9

Yue Zhang, Dongsheng Li. "Seismic behavior
and design of repairable precast RC beam-
concrete-filled square steel tube column joints
with energy-dissipating bolts", Journal of
Building Engineering, 2021

Publication

<1 %

10

Hatta, Takeshi, Ayako Kawakami, Noriye Tsukiji, Noboru Ayetani, Toshihiro Araki, and Mitsuhiro Shimizu. "FAMILY STRUCTURE OF JAPANESE JUVENILE DELINQUENTS: EVIDENCE FROM THE RESULTS OF THE DOLL LOCATION TEST", Social Behavior and Personality An International Journal, 1993.

Publication

<1 %

11

Shubham Singhal, Ajay Chourasia, Yogesh Kajale. "Cyclic behaviour of precast reinforced concrete beam-columns connected with headed bars", Journal of Building Engineering, 2021

Publication

<1 %

12

"Strain-Hardening Cement-Based Composites", Springer Science and Business Media LLC, 2018

Publication

<1 %

13

Chao Tong, Jing Wu, Chunyu Li, Jianping Han, Zhiqiang Li. "Experimental investigation of a single-yielding precast concrete beam-column connection with replaceable energy-dissipation connector", Soil Dynamics and Earthquake Engineering, 2021

Publication

<1 %

14

Fudong Ma, Mingke Deng, Yong Yang. "Experimental study on internal precast beam-column ultra-high-performance

<1 %

concrete connection and shear capacity of its joint", Journal of Building Engineering, 2021

Publication

15

Kai-Siong Woon, Farzad Hejazi. "Vertical Cyclic Performance of Precast Frame with Hook-end U-shaped High-damping Rubber Joint", KSCE Journal of Civil Engineering, 2019

Publication

16

Tuan T. Ngo, Thong M. Pham, Hong Hao. "Effects of steel fibres and prestress levels on behaviour of newly proposed exterior dry joints using SFRC and CFRP bolts", Engineering Structures, 2020

Publication

17

Shicai Chen, Weiming Yan, Jie Gao. "Experimental Investigation on the Seismic Performance of Large-Scale Interior Beam-Column Joints with Composite Slab", Advances in Structural Engineering, 2016

Publication

18

Bin Du, Wanliang Jiang, Zheng He, Zhe Qi, Chaojie Zhang. "Development of a modified low-cycle fatigue model for semi-rigid connections in precast concrete frames", Journal of Building Engineering, 2022

Publication

19

Rudy Djameluddin, Pieter Lourens Frans, Rita Irmawati. "Flexural Capacity of the Concrete

<1 %

<1 %

<1 %

<1 %

<1 %

Beams Reinforced by Steel Truss System",
MATEC Web of Conferences, 2017

Publication

20

Samya Abd El-Hameed, Mohamed Eladawy,
Mohamed H. Agamy, Hesham Haggag.
"Experimental and numerical investigation on
the performance of adhesive steel-dowels
used in precast reinforced concrete
elements", Structures, 2022

Publication

<1 %

21

Weichen Xue, Xinyu Hu, Jiazheng Song.
"Experimental study on seismic behavior of
precast concrete beam-column joints using
UHPC-based connections", Structures, 2021

Publication

<1 %

22

Chen, Shi Cai, Wei Ming Yan, Xiao Ming Tian,
and Jie Gao. "Experimental and Numerical
Investigation on the Seismic Behavior of
Large-Scale Beam to Column Exterior Joints
with Composite Slab", Advanced Materials
Research, 2011.

Publication

<1 %

23

Lu Tingting, Zhou Hao, Liang Xingwen.
"Research on the mechanical properties of
the joint of the beam-column subassembly",
Structures, 2022

Publication

<1 %

24

A. Said, M. Nehdi. "Rehabilitation of RC frame joints using local steel bracing", Structure and Infrastructure Engineering, 2008

Publication

<1 %

25

M. Ye, J. Jiang, H.M. Chen, H.Y. Zhou, D.D. Song. "Seismic behavior of an innovative hybrid beam-column connection for precast concrete structures", Engineering Structures, 2021

Publication

<1 %

26

Maya Sian Caycedo Garcia, Gustavo Henrique Siqueira, Luiz Carlos Marcos Vieira Junior, Isaias Vizotto. "Evaluation of structural capacity of triangular and hexagonal reinforced concrete free-form shells", Engineering Structures, 2019

Publication

<1 %

27

Qian Zhang, Shuo Wang, Marco Meloni, Jian Feng, Jian Xu, Jianguo Cai. "Experimental study on seismic behavior of precast beam - column connections under cyclic loading", Structural Concrete, 2020

Publication

<1 %

28

Wei Huang, Gaoxing Hu, Xinwei Miao, Zhenhui Fan. "Seismic performance analysis of a novel demountable precast concrete beam-column connection with multi-slit devices", Journal of Building Engineering, 2021

<1 %

29

Abdul Ghani, Kay Dora, and Nor Hayati Abdul Hamid. "Comparing the Seismic Performance of Beam-Column Joints with and without SFRC when Subjected to Cyclic Loading", *Advanced Materials Research*, 2012.

Publication

30

Cailong Ma, Hongbin Jiang, Zhenyu Wang. "Experimental investigation of precast RC interior beam-column-slab joints with grouted spiral-confined lap connection", *Engineering Structures*, 2019

Publication

31

Chen, C.C.. "Behavior and strength of steel reinforced concrete beam-column joints with two-side force inputs", *Journal of Constructional Steel Research*, 200903

Publication

32

Chenglong Wu, Jiming Liu, Wenya Tan, Pengfei Wang. "Seismic behavior of composite interior joints of prefabricated H-shaped steel reinforced concrete column - steel beam", *Structures*, 2020

Publication

33

Congxiao Wu, Dingbin Li, Xuesong Deng, Cheng Yang, Xin Xu. "Experimental study on precast concrete moment - resisting frame system with sector lead viscoelastic

<1 %

<1 %

<1 %

<1 %

<1 %

dampers", Structural Control and Health Monitoring, 2021

Publication

34

HakJong Chang, Insub Choi, JunHee Kim, Sung Yub Hong. "Experimental investigation on seismic performance of two types of member-panel zone unified joints for precast concrete moment-resisting frame", Journal of Building Engineering, 2021

Publication

<1 %

35

J.D. Nzabonimpa, Won-Kee Hong, Jisoon Kim. "Experimental and non-linear numerical investigation of the novel detachable mechanical joints with laminated plates for composite precast beam-column joint", Composite Structures, 2018

Publication

<1 %

36

Jia-Jun Fan, Gang Wu, De-Cheng Feng, Yi-Hua Zeng, Yong Lu. "Seismic performance of a novel self-sustaining beam-column connection for precast concrete moment-resisting frames", Engineering Structures, 2020

Publication

<1 %

37

Mazzolani, . "New Generation of Steel Structures", Seismic Design of Steel Structures, 2013.

Publication

<1 %

38

Ying Guo, Kangshuai Wang, Duan Huang, Xueqin Jiang. "High efficiency continuous-variable quantum key distribution based on QC-LDPC codes", Chinese Optics Letters, 2019

Publication

<1 %

39

Zuohua Li, Yihe Qi, Jun Teng. "Experimental investigation of prefabricated beam-to-column steel joints for precast concrete structures under cyclic loading", Engineering Structures, 2020

Publication

<1 %

40

Gaoxing Hu, Wei Huang, Haiqiao Xie. "Mechanical behavior of a replaceable energy dissipation device for precast concrete beam-column connections", Journal of Constructional Steel Research, 2020

Publication

<1 %

41

Hua Huang, Ming Li, Wei Zhang, Yujie Yuan. "Seismic behavior of a friction-type artificial plastic hinge for the precast beam-column connection", Archives of Civil and Mechanical Engineering, 2022

Publication

<1 %

42

Jianxin Zhang, Chuanlin Ding, Xian Rong, Hongwei Yang, Yanyan Li. "Development and experimental investigation of hybrid precast concrete beam-column joints", Engineering Structures, 2020

<1 %

43

Jiaqiang Chen. "Study on the joint mechanical properties of steel structure buildings", International Journal of Building Pathology and Adaptation, 2020

Publication

<1 %

44

Wei Huang, Gaoxing Hu, Jiarui Zhang. "Experimental study on the seismic performance of new precast concrete beam-column joints with replaceable connection", Structures, 2022

Publication

<1 %

Exclude quotes On

Exclude matches < 5 words

Exclude bibliography On