

Characteristics of Bio Pellet

by Andi Detti Yunianti

Submission date: 02-Feb-2023 03:09PM (UTC+0700)

Submission ID: 2004678433

File name: itin_characteristics_of_Bio_Pellet_Andi_Detti_Yunianti_final.pdf (2.97M)

Word count: 7876

Character count: 39969



Characteristics of Bio Pellets from Spent Coffee Grounds and Pinewood Charcoal Based on Composition and Grinding Method

Nopia CAHYANI¹ · Andi Detti YUNIANI^{1,†} · SUHASMAN¹ · Kidung Tirtayasa Putra PANGESTU¹ · Gustan PARI²

ABSTRACT

One type of biomass that has promising potential for bio pellet production is spent coffee grounds (SCGs). However, previous studies have shown that SCGs in bio pellets cause a lot of smoke. Therefore, they need to be mixed with a material that has a higher calorific value to produce better quality pellets. One material that can be used is pine wood because it has a natural resin content that can increase the calorific value. The aim of this study was to examine the quality of bio pellets produced with SCGs and pine wood charcoal at different particle sizes. The charcoal was ground using either a hammer mill (HM) or a ball mill (BM). Pine wood charcoal was mixed with SCGs at ratios of SCGs to pine wood charcoal of 4:6 and 6:4 by weight, respectively, and the adhesive used a tapioca with a composition ratio 5% of the raw material. The bio pellets were produced using a manual pellet press. The quality of the bio pellets was assessed based on Indonesian National Standard (SNI) 8021-2014, and the physical observations include flame length, burning rate, and compressive strength. The average water content, ash content, and calorific value of the bio pellets were in accordance with SNI 8021-2014, but the density and ash content values were below the standard values. The BM variation of bio pellets had a higher compressive strength than the HM variation, and the 4:6 BM variation had the longest burning time compared with 4:6 HM.

Keywords: bio pellet, spent coffee grounds, charcoal, pine wood, hammer mill, ball mill

1. INTRODUCTION

Fuel is required to produce energy, and its supply is a major problem today. Every year, the consumption increases along with the increasing population in worldwide (Budiawan *et al.*, 2014). As a developing country, Indonesia has many resources that have great potential for development as renewable fuels for daily needs (Pratiwi, 2020). One energy source that is both abundant

and renewable is biomass. Biomass is organic material obtained from the photosynthetic process, both in the form of products and waste (Putri and Andasuryani, 2017). Using biomass as fuel has the advantage of reducing carbon dioxide levels in the atmosphere because biomass produces carbon neutral from combustion, so it is more easily absorbed by plants (carbon neutral; Jang, 2022; Mustamu *et al.*, 2018) and also several studies reported that wood-based fuels are the best for reducing

Date Received August 24, 2022, Date Revised September 21, 2022, Date Accepted December 14, 2022

¹ Forestry Faculty, Hasanuddin University, Makassar 90245, Indonesia

² Research Center for Biomass and Bioproducts, National Research and Innovation Agency, Bogor 16911, Indonesia

[†] Corresponding author: Andi Detti YUNIANI (e-mail: dettiyunianti70@yahoo.com, <https://orcid.org/0000-0002-7087-9589>)

© Copyright 2023 The Korean Society of Wood Science & Technology. This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/4.0/>) which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

air pollutant products during combustion and calculating average annual greenhouse gas emissions by tree species and products for charcoal (Jeoung *et al.*, 2020). In addition, the use of biomass can minimize environmental impacts of energy production by replacing fossil fuels and thus reducing greenhouse gas emissions, carbon sequestration, climate change mitigation, waste management, energy production (Heo and Choi, 2018; Wu *et al.*, 2021). Biomass can be obtained from various sources, including agricultural waste and wood waste, but it tends to have high moisture content and poor flammability (Kansai *et al.*, 2018; Lee *et al.*, 2019), the biomass based on wood consists of cellulose, hemicellulose, and lignin (Hwang *et al.*, 2021). Bio pellet technology offers a solution to improve the quality of biomass for burning (Mustamu *et al.*, 2018; Pratiwi, 2020).

Bio pellets are created by processing biomass in combination with adhesives in a pressing system. The technology is simple, and it can relatively quickly produce bio pellets with a diameter of 6–12 mm and a length of 10–20 mm (Fikri and Sartika, 2018; Mustamu *et al.*, 2018). The pelletization of biomass provides consistent quality, high energy content, and uniform size and shapes of solid energy (Lee and Kim, 2020).

One type of biomass that is abundant in Indonesia is spent coffee grounds (SCGs). Coffee consumption in Indonesia is increasing by an average of more than 7% every year, and with the higher coffee consumption, a greater amount of coffee waste is generated from cafes and households (Limantara *et al.*, 2019). However, SCGs contain aromatic and aliphatic compounds and high levels of nitrogen and sulfur (Yang *et al.*, 2018), which cause SCGs to produce a lot of smoke when they are burned (Khusna and Susanto, 2015). Therefore, modifications are necessary to increase the potential of SCGs as a fuel source by mixing it with other materials that are sustainable and have a high calorific value such as using wood, the wood itself is one of the renewable eco-environmental resources (Ahn *et al.*, 2021; Ghani

and Lee, 2021; Hadi *et al.*, 2022; Han and Lee, 2021; Jang, 2022; Park *et al.*, 2020a, 2020b). The Intergovernmental Panel on Climate Change (IPCC) recognizes wood as a representative carbon-neutral material and advocates using wood as an essential material for building a carbon-neutral society (Brunet-Navarro *et al.*, 2018; Jang, 2022). Wood that contains a high calorific value according to Martinez *et al.* (2019) is pine wood, it contains resin which can affect to increase the calorific value. However, in this study the pine wood would burn into charcoal, according to Jeoung *et al.* (2020) the wood charcoal causes the higher of fixed carbon.

In addition to the materials used, particle size is another factor that affects the pressing and burning process. A larger particle size causes larger cavities in bio pellets because a larger particle makes the adhesive will be more difficult to stick. Owing to the larger cavities, more oxygen can enter into the pellets, allowing the oxidation reaction to occur more rapidly (Lisowski *et al.*, 2019) and Ju *et al.* (2020) reported that a carbonized biomass below 100 mesh had the lowest ash content and the highest heating value, carbon content, and fixed carbon content. Reducing particle size is an important part of pre-processing associated with the use of biomass in energy production and other industries. The design and the technology used for size reduction process very important for the consideration in bio-energy making process (Lee and Eom, 2021). The technology for making powders or particles is continually advancing. One type of technology that is currently being promoted in various countries is the use of ball milling. Ball milling in the manufacture of bio-char is carried out to produce better characteristics and functionality of the product (Kumar *et al.*, 2020). Recent studies have shown that ball milling can increase the surface area and volume of pores in biochar, as well as enable a reduction in the particle size (Lyu *et al.*, 2017; Naghdi *et al.*, 2017).

The aim of this study was to investigate the characteristics of bio pellets made from a mixture of SCGs

and pine wood charcoal mixed at different ratios. The quality of the bio pellets was assessed according to Indonesian National Standard (SNI) 8021-2014 (Badan Standardisasi Nasional, 2014), which includes tests for moisture content, ash content, density, carbon content, calorific value, and volatile matter content (Mustamu *et al.*, 2018; Peudada *et al.*, 2020).

2. MATERIALS and METHODS

2.1. Tools and materials

This study used matchsticks and a drum to burn the pieces of pine wood, and the main equipment included a hammer mill (HM) to grind pine wood charcoal to obtain micro-sized particles and a ball mill (BM) to grind micro-size pine wood charcoal to obtain nano-sized particles.

The HM grinder was a type of disk mill that basically grinds material using a rotating disc on a stationary surface (Nandiyanto *et al.*, 2020). The BM grinder was a mixer milling type based on vibration ball-milling (vibration type). In vibration ball-milling, a cylinder containing a ball and the material to be milled vibrated at high frequencies and small amplitudes (Kumar *et al.*, 2020; Xing *et al.*, 2016).

The tools used for analysis were a peroxide bomb calorimeter to determine the heating value of pellets, a furnace for determining ash content, volatile matter test equipment, an analytical balance, a desiccator, a measuring cup, a caliper, and an oven. The main materials were pine wood and SCGs. The pellet formula also included tapioca starch as an adhesive.

Samples of SCGs were dried in an oven for 24 hours at 105°C, while pieces of pine wood were burned to produce charcoal. The burning process was conducted by putting the pine wood into a drum and burning it on a fireplace for 30 minutes. The resultant pine wood charcoal was ground using an HM grinder, and the pine

wood charcoal powder was then sieved and trapped at 125 µm. The charcoal ground by HM is shown in Fig. 1. A portion of the BM pine wood charcoal powder was sieved at 60 µm and then ground again by BM for 30 minutes. The BM pine wood charcoal powder is shown in Fig. 1.

Tapioca flour at a weight of 5% of the raw material per pellet unit was mixed with hot water to a concentration ratio of 1:20 between adhesive and water. The mixture was stirred until it produced a gel. HM or BM SCGs to pine wood charcoal were respectively mixed at a ratio of 6:4 or 4:6 to produce four types of pellets.

2.2. Pellet production

2.2.1. Material preparation

Samples of SCGs were dried in an oven for 24 hours at 105°C, while pieces of pine wood were burned to produce charcoal. The burning process was conducted by putting the pine wood into a drum and burning it on a fireplace for 30 minutes. The resultant pine wood charcoal was ground using an HM grinder, and the pine



Fig. 1. Pine wood charcoal powder from BM grinder. BM: ball mill.

wood charcoal powder was then sieved and trapped at 125 µm. The charcoal ground by HM is shown in Fig. 2. A portion of the HM pine wood charcoal powder was sieved at 60 µm and then ground again by BM for 30 minutes. The BM pine wood charcoal powder is shown in Fig. 1.

2.2.2. Mixing process

Tapioca flour at a weight of 5% of the raw material per pellet unit was mixed with hot water to a concentration ratio of 1:20 between adhesive and water. The mixture was stirred until it produced a gel. HM or BM SCGs to pine wood charcoal were respectively mixed at a ratio of 6:4 or 4:6 to produce four types of pellets.

2.2.3. Production

Homogeneous briquettes, each weighing 2 g, were placed in a manual pellet press (Fig. 3) for the molding process. Afterward, the pellets were dried in an oven at 120°C for 24 hours.



Fig. 2. Pine wood charcoal powder from HM grinder. HM: hammer mill.

2.2.4. Bio pellet characteristics

The bio pellet characteristics were tested based on SNI 8021-2014 to evaluate density, moisture content, ash content, volatile matter content, fixed carbon, and calorific value which follows to previous research by Mustamu *et al.* (2018). Additional characteristics were done based on physical analysis of the bio pellets to determine their compressive strength (Mustamu *et al.*, 2018), flame duration (Tongcumpou *et al.*, 2019), combustion rate (Afif Almu *et al.*, 2014), and physical appearance (Rusdianto, 2018).

2.2.4.1. Quality test of bio pellets

The density of the pellets was determined by measuring the weight of the briquette sample and dividing it by the sample volume. The briquette density is expressed by the formula:

$$\rho = \frac{M}{V} \quad (1)$$

where ρ = density (g/cm³); M = mass (g); and V =



Fig. 3. Manual pellet press.

volume of cylinder (cm³).

Determination of the moisture content (MC) was carried out by placing 1 g of the sample in an oven at a temperature of 103 ± 2°C for 24 hours until the weight was constant. The sample was then cooled in a desiccator for 15 minutes and weighed according to SNI 8021-2014, using the following formula:

$$MC(\%) = \frac{w - d}{d} \times 100\% \quad (2)$$

where w = weight before drying in the oven (g), and d = weight after drying in the oven (g).

Ash content was determined by placing 1 g of the sample on a porcelain plate of known weight in a muffle furnace at 600°C–900°C for 5 to 6 hours. The sample was cooled in a desiccator and then weighed. The ash content of the sample was calculated according to SNI 8021-2014, using the following formula:

$$\text{Ash Content}(\%) = \frac{w - d}{y} \times 100\% \quad (3)$$

where y = weight of pellet (g), w = weight of ash (pellet after ash) (g), and d = weight of porcelain cup (g).

Volatile matter was measured by placing a porcelain cup containing ± 1 g of the sample into the muffle furnace, heating it at 900°C for 7 minutes, and then putting it in a desiccator to cool for 1 hour. After that, the porcelain dish was weighed, and the amount of volatile substances was calculated according to SNI 8021-2014, using the formula:

$$\text{Volatile matter}(\%) = \frac{\text{Loss in weight due to removal of volatile matter}}{\text{Weight of coal sample taken}} \times 100\% \quad (4)$$

The fixed carbon fraction of the material does not

include the moisture, volatile matter, and ash content. The fixed carbon content was calculated according to SNI 8021-2014 with the formula:

$$\text{Fixed carbon}(\%) = 100 - (\text{Moisture content} + \text{volatile matter} + \text{ash content})\% \quad (5)$$

One gram of the sample was placed in a silica cup, which was put into a peroxide bomb calorimeter tube. The calorific value was calculated according to SNI 8021-2014 with the formula:

$$\text{Calorific value} = \frac{\text{Heat produced (in kJ)}}{\text{Mass of fuel (in kg)}} \times 100 \quad (6)$$

2.2.4.2. Physical analysis

The flame duration test was carried out following to previous study by Tongcumpou *et al.* (2019), the bio pellets burned on an alcohol burner and a tripod, and the length of ignition time was calculated using a stopwatch.

For calculating the combustion rate, the weight mass of the pellets before burnt divided to the weight mass of pellet after burnt. The combustion rate was calculated using the formula according to Afif Almu *et al.* (2014) and Oyelaran *et al.* (2018):

$$\text{Combustion rate} = \frac{w - d}{t} \quad (7)$$

where w = the weight of pellets before burnt (g), d = the weight of pellets after burnt (g), and t = total time taken (minute).

The compressive strength test was carried out on the Universal Testing Machine (UTM) and was calculated using the formula (Mustamu *et al.*, 2018):

$$P = \frac{Mb}{A} \times 100\% \quad (8)$$

where P = compressive strength of pellets (kgf/cm^2); Mb = load received by pellet until it breaks (kgf); and A = pellet surface area (cm^2).

The physical appearance of the bio pellet was carried out based on research from Rusdianto (2018), by looking at the color, diameter, and smell of each variation.

3.2.5. Data analysis

The treatment used in this study was the difference in the ratios of the pine wood charcoal powder to SCGs, 4:6 and 6:4. Another treatment was the different methods used to grind the pine wood charcoal, HM and BM. Each treatment was carried out three times. Data in this study were analyzed by using independent sample t -tests. Bio pellets were compared in terms of the different ratios of components, as well as the different grinding methods used for pine wood charcoal.

3. RESULTS and DISCUSSION

The bio pellets made with SCGs and pine wood charcoal were tested for the parameters included in SNI 8021-2014: density, moisture content, ash content, volatile matter content, fixed carbon, and calorific value. Physical analysis of bio pellets consisted of evaluating their compressive strength, burning time, burning rate, and physical appearance.

3.1. Quality of bio pellets

3.1.1. Moisture content

Bio pellets can absorb water or moisture the moisture content was calculated to determine the nature of the absorption of moisture, which can affect the other chemical test values of the bio pellet. Measurement of moisture content was carried out after the bio pellets were compressed and dried in oven for 24 hours (Muzakir et al., 2017; Putri and Andasuryani, 2017). The results of the moisture content test can be seen in

Fig. 4.

Based on the test result, the moisture content differed significantly between variations in HM and BM (two-tailed p -value ≤ 0.005). Fig. 4 shows that the BM bio pellet has a higher moisture content than the HM variation bio pellet, likely because the charcoal particles produced by BM have a smaller size. According to Priyanto et al. (2018) and Ruslan (2020), the moisture content value of a pellet is influenced by its density and pores density; the finer the particle size, the higher the moisture content value. Thus, the finer the particle size, the more moisture will be absorbed.

The test results show that the moisture content percentages of the 6:4 pine wood charcoal-SCGs combinations were significantly different from those of the 4:6 combinations (two-tailed p -value < 0.005). Fig. 4 shows that the 6:4 combinations had a higher moisture content value than the 4:6 combinations. This finding is in line with the research of Jeguirim et al. (2014), who reported that the moisture content in pure SCGs bio pellets was 11.78%, while the moisture content value in pine wood pellets was only 7.90% and that of pellets made from a mixture of SCGs and pine was 6.65%. The high moisture content in SCGs occurs because the moisture content in coffee grounds before brewing is around 42% (Colantoni et al., 2021). In the research of Atabani et al.

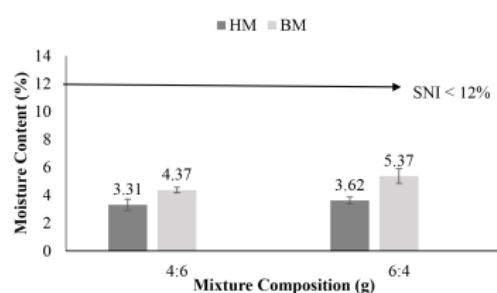


Fig. 4. The diagram of the moisture content with the ratio between SCGs to pine wood charcoal. HM: hammer mill, BM: ball mill, SNI: Indonesian National Standard, SCGs: spent coffee grounds.

(2018), the moisture content in SCGs after drying at a temperature of 105°C was found to be 55%. The high moisture content value greatly affects the chemical and mechanical test values of bio pellets (Cubero-Abarca *et al.*, 2014; Rusdianto, 2018). The high moisture content can also reduce the quality of bio pellets, for example, through the growth of microorganisms, and cause pellets to be difficult to ignite and to produce a lot of smoke (Putri and Andasuryani, 2017; Tun *et al.*, 2020).

According to SNI, good-quality bio pellets have a moisture content value $\leq 12\%$. Therefore, all variations of bio pellets in this study had a moisture content value in accordance with SNI 8021-2014.

3.1.2. Density 6

Density reflected the ratio between mass and volume of briquettes. The high- and low-density values were influenced by pressure at the time of pressing, particle size, and the homogeneity of the bio pellet constituent materials (Damayanti *et al.*, 2017; Priyanto *et al.*, 2018). The results of the density test are presented in Fig. 5.

The density was significantly different between the bio pellets made with HM and BM (two-tailed ρ -value < 0.005). Fig. 5 shows that the density of BM pellets was higher than that of HM pellets, indicating that the BM particles were smaller than the HM particles. The

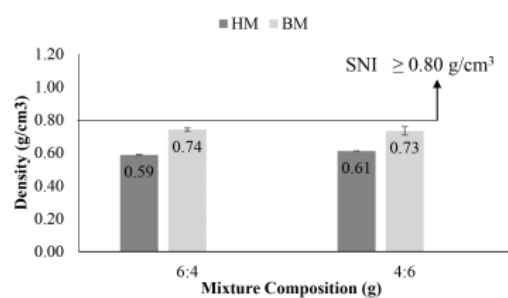


Fig. 5. The diagram of the density with the ratio between SCGs to pine wood charcoal. HM: hammer mill, BM: ball mill, SNI: Indonesian National Standard, SCGs: spent coffee grounds.

density of the material is influenced by its specific gravity, which is determined in part by the particle size of the material. Coarser or larger particles in the bio pellet lead to a lower specific gravity, and thus a lower density (Damayanti *et al.*, 2017). This pattern accords with a previous study by Priyanto *et al.* (2018), who reported that the smaller the particle size, the higher the density value. This association is explained by small particle sizes resulting in stronger bonds between charcoal particles.

With regard to the variation in the ratios of pine wood charcoal and SCGs, the test results were non-significant (two-tailed ρ -value ≥ 0.005). This outcome indicates that the material used to create the bio pellets had no effect on their density. The density was only affected by the pressure during the compression process and the particle size of the materials used (Prabawa and Miyono, 2017). Based on SNI 8021-2014, a good bio pellet density is $\geq 0.80 \text{ g/cm}^3$, and none of the variations of bio pellets in this study met this standard.

3.1.3. Ash content 48

Ash is what remains following the combustion of bio pellets. It does not have carbon elements or calorific value, and its main components are calcium, potassium, magnesium, and silica. The silica content in biomass has an unfavorable effect on the calorific value and carbon content value; that is, the smaller the ash content value, the higher the calorific value and carbon content value of the biomass (Iskandar *et al.*, 2019; Muzakir *et al.*, 2017; Putri and Andasuryani, 2017). The ash content of the bio pellets can be seen in Fig. 6.

The results (ρ -value ≤ 0.005) indicated that the ash content was significantly different between HM and BM charcoal, and the variation introduced based on different combinations of SCGs and pine wood charcoal did not have a significant effect to the ash content. According to Colantoni *et al.* (2021) the ash content reflected to the calorific value, a higher percentage of ashes implies

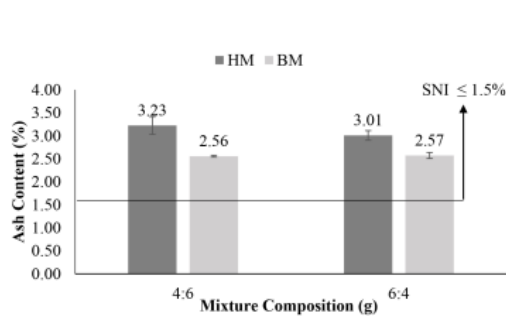


Fig. 6. The diagram of the ash content with the ratio between SCGs to pine wood charcoal. HM: hammer mill, BM: ball mill, SNI: Indonesian National Standard, SCGs: spent coffee grounds.

13 a greater quantity of unburnt products and consequently a lower calorific value (Fig. 7). The high value of ash content of this study caused by the mixture of SCGs, Limousy *et al.* (2013) found that the ash content of SCG₁ was high because contain several element including potassium (3.5 mg/g), phosphorus (1.5 mg/g), magnesium (1.3 mg/g), and calcium (0.8 mg/g, Jeguirim *et al.*, 2014; M₂₅ etto *et al.*, 2011).

Based on SNI 8021-2014, the ash content of the bio pellets in this study exceeds the standard ($\leq 1.5\%$). Therefore, the 63 bio pellets of each variation in this study do not meet the quality standard for ash content according to SNI.

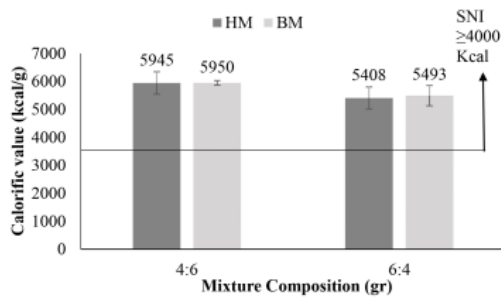


Fig. 7. Diagram of the calorific value with the ratio between SCGs to pine wood charcoal. HM: hammer mill, BM: ball mill, SNI: Indonesian National Standard, SCGs: spent coffee grounds.

15
3.1.4. Volatile matter

Volatile matter is associated with the amount of smoke that is produced during combustion. The level of volatile substances in the components of bio pellets affects the carbon content of the bio pellets. The greater the volatile matter, the lower the value of the carbon content, which causes the intensity of the fire of the bio pellet to decrease and also affects the calorific value (Iskandar *et al.*, 2019). The value of volatile matter is influenced by the organic compounds in the materials used, including carbon, hydrogen, and oxygen (Ajimotokan ⁵⁶, 2019; Kawale and Kishore, 2020). The value of the volatile matter in bio pellets can be seen in Fig. 8.

Based on the test results comparing HM and BM, the volatile matter values were not significantly different between the two types (two-tailed p -value ≥ 0.005). Meanwhile, the p -value for the comparison of the different ratios of pine wood charcoal to SCGs showed significant differences between 4:6 and 6:4 (two-tailed p -value ≤ 0.005). As illustrated in Fig. 8, the more of SCGs mixture, the higher the value of the volatile matter. According to Ajimotokan *et al.* (2019) the volatile matter of charcoal particles was lower when compared to the other raw materials. This could be due to its production process (carbonization), wherein a degree of devolatilization could have occurred. Even so, the vola-

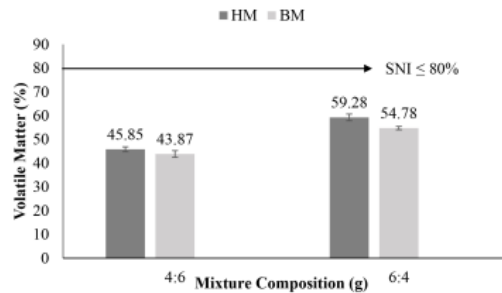


Fig. 8. Diagram of volatile matter with the ratio between SCGs to pine wood charcoal. HM: hammer mill, BM: ball mill, SNI: Indonesian National Standard, SCGs: spent coffee grounds.

tile matter content of the bio pellets in this study met the standard of SNI 8021-2014, which was $\leq 80\%$.

3.1.5. Fixed carbon content

The carbon content, or fixed carbon, is the carbon fraction (C) contained in materials; it is what remains after the water, ash, and volatile substances are removed. The carbon content in bio pellets is strongly influenced by the ash content and volatile matter content (Iskandar *et al.*, 2019; Putri and Andasuryani, 2017). Based on the test results of fixed carbon value of the bio pellets presented in Fig. 9.

According to Sunardi *et al.* (2019), the increase of fixed carbon is influenced by the amount of volatile matter and the ash content. The higher the volatile matter and the ash content, the lower the fixed carbon. The test results for fixed carbon values based on HM and BM showed no significant difference (two-tailed p -value ≥ 0.005). In contrast, 4:6 and 6:4 mixed combinations were significantly different (two-tailed p -value ≤ 0.005).

Fig. 9 shows that the fixed carbon value increases with the amount of the pine wood charcoal in the mixture, which could have been because pine wood had a higher lignin content than SCGs. According to Jeguirim *et al.* (2014), a high lignin content in the raw material for making bio pellets is associated with a high value of

fixed carbon. A high level of fixed carbon indicates that a fuel tends to burn more slowly than a fuel with a lower level of fixed carbon (Martinez *et al.*, 2019). The fixed carbon in this study was in accordance with SNI, its $\geq 14\%$.

3.1.6. Calorific value

The calorific value is determined by the combustion of the activated carbon or fixed carbon (Patandung, 2014). The calorific value is the main parameter in determining the quality of bio pellets (Iskandar *et al.*, 2019). The higher the calorific value, the better the quality of the pellets (Budiawan *et al.*, 2014). The calorific value of the bio pellets created in this study can be seen in Fig. 7.

The calorific values associated with the different treatments did not differ significantly (two-tailed p -value < 0.005). However, all bio pellets regardless of variation met SNI 8021-2014, which was $\geq 4,000$ kcal/g. The low calorific value of each variation (Fig. 7) was not in accordance with the findings reported by Kale *et al.* (2019), indicating that a lower moisture content (Fig. 4) is associated with a higher calorific value because bio pellets with a higher moisture content have a lower calorific value owing to non-combustibility.

3.2. Physical analysis of bio pellets

The quality of bio pellets was also observed physically. In addition to detecting possible damage to the bio pellets, the physical analysis also included evaluation of the flame duration and combustion rate of the bio pellets. The results are presented in Table 1.

3.2.1. Flame duration

Flame duration is one of the parameters or factors to be considered in the manufacture of solid fuels. The longer the burning time to ashes (burnt-out), the better the quality and vice versa (Ashar *et al.*, 2020). The test

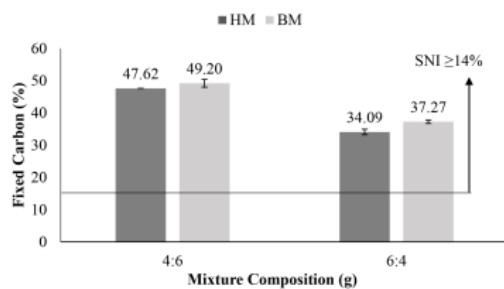


Fig. 9. The diagram of fixed carbon with the ratio between SCGs to pine wood charcoal. HM: hammer mill, BM: ball mill, SNI: Indonesian National Standard, SCGs: spent coffee grounds.

Table 1. Visual observations of the bio pellets with the ratio between SCGs and pine wood charcoal

Testing	HM		BM	
	4:6	6:4	4:6	6:4
Flame duration (minute)	24.30	23.01	29.10	26.06
Combustion rate (g/minute)	0.0407	0.0375	0.0379	0.0427
Compressive strength (kgf/cm ²)	1.3309	0.9760	2.9005	2.3960

SCGs: spent coffee grounds, HM: hammer mill, BM: ball mill.

60 results of this study showed that the bio pellets did not have significant differences (two-tailed p -value < 0.005) based on treatment with respect to the burning time of bio pellets.

Table 1 shows that the flame duration associated with the pine wood charcoal ground with the BM grinder was longer than that 54 luced with the HM grinder. This finding indicates that the smaller the particle size, the longer the duration required for a bio pellet to burn out. Smaller particle sizes are associated with denser material of the pellets, which extends the burning time of the bio pellet (Ashar *et al.*, 2020). A larger particle size causes larger cavities within pellets because the adhesive does not stick as well as with smaller particles. Oxygen can easily enter the cavities, which causes the oxidation reaction to occur faster.

In addition, a comparison between pellets with different ratios of pine wood charcoal powder to SCGs showed that pellets with a ratio of 6:4 had a longer flame duration than those with a ratio of 4:6. According to Jamilatun (2008), flame duration is influenced by the calorific value (Fig. 7); specifically, the higher the calorific value, the longer the bio pellet can burn. This can be explained by the fact that pine wood contains natural resin (Martinez *et al.*, 2019).

3.2.2. Combustion rate

The combustion rate was assessed to determine the feasibility of the bio pellets as an effective fuel (Afif Almu *et al.*, 2014). A smaller burning rate indicates a

longer burning time due to the lower mass of bio pellet that burns for each increment of time.

As shown in Table 1, all bio pellets in this study had almost the same combustion rate regardless of treatment. The combustion rate was influenced by the amount of the volatile matter (Fig. 8), with higher combustion rates being associated with higher amounts of volatile matter (Jamilatun, 2008). Pine wood naturally contains a volatile compound called turpentine (spirits of turpentine), which caused high volatilization in the bio pellets in this study.

16

3.2.3. Compressive strength

Compressive strength is the ability of a material to have durability, defined as the strength to withstand external pressure that could cause the material to break or crumble (Mustamu *et al.*, 2018). Compressive strength tests are carried out to determine the resistance of bio pellets to possible damage caused by storage, transportation, or handling (Brunerová *et al.*, 2018). The results of the compressive strength testing in this study are presented in Table 1.

The test results showed that all variations of the bio pellets in this study were essentially the same in terms of compressive strength, with no significant differences based on treatment (two-tailed p -value < 0.005). However, Table 1 shows that the compressive strength value in the BM variation was greater than the HM variation, which can be explained by the BM particle size being smaller than the HM particle size. Previous studies by Hendra (2012) and Mustamu *et al.* (2018) revealed that

compressive strength is inversely related to particle size, and a particle composition that tends to be smoother and more uniform strengthens bonding between particles. In addition, Priyanto *et al.* (2018) reported that a higher compressive strength is associated with a higher combustion rate.

According to Lisowski *et al.* (2019), as lower moisture content is linked to higher compressive strength. The moisture content values in this study are presented in Fig. 4. The high moisture content affects the low compressive strength of the 6:4 mixture composition. This is because SCGs can absorb moisture easily, according to Cubero-Abarca *et al.* (2014) and Fasina (2008) that SCGs moisture content ranging from 3% to 5%.

3.2.4. Physical appearance

Fig. 10 shows the physical appearance of the bio pellets. They have a cylindrical shape with a diameter of 1.2 cm and a length ranging from 1.2 to 1.4 cm. The aroma of coffee is more pronounced in the 6:4 SCGs to pine wood charcoal mixture in each variation of the bio pellet.

Physically, the pellets with the 6:4 had a slightly brownish color. In each variation of pellets with HM

pine wood charcoal, the pores in the pellet were more clearly visible than in those with BM; however, in the pellets with HM, the bio pellets were more difficult to compact in 6:4 mixture, which made uneven surfaces. According to Priyanto *et al.* (2018), a larger particle size makes bonding more difficult because of the presence of empty voids. As for variations in BM, the briquet dough is easier to compact, but there are more cracks on the surface of the bio pellet [Fig. 10(A) and (B)]. This could be due to the less of adhesive composition used in this study. If more adhesive compositions are used, then the composition of the particles will likely be better, more regular, and denser.

4. CONCLUSIONS

From the results of the study, the following conclusions were obtained:

1. The characteristics moisture content, volatile matter, fixed carbon, and calorific value of bio pellets composed of 4:6 and 6:4 pine wood charcoal to SCGs were in accordance with the standards. However, the ash content and density of bio pellets in this study were not in accordance with SNI.

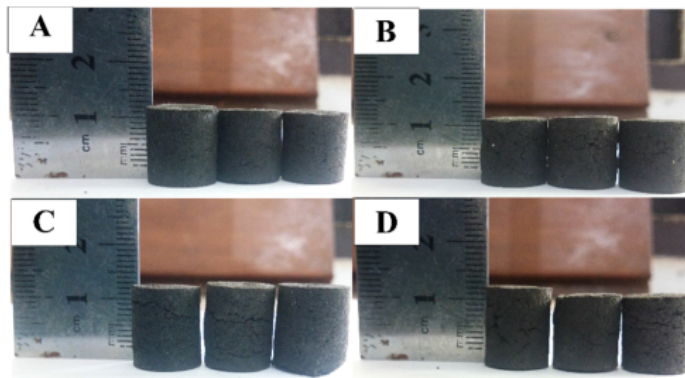


Fig. 10. The physical appearance of the bio pellets with the ratio between SCGs to pine wood charcoal: (A) BM 4:6, (B) BM 6:4, (C) HM 4:6, and (D) HM 6:4. SCGs: spent coffee grounds, HM: hammer mill, BM: ball mill

2. Composition of 4:6 SCGs to pine wood charcoal provided a longer flame duration, higher compressive strength, and a more compact physical appearance with smoother surfaces compared with the composition of 6:4. However, the combustion rates of both compositions were almost the same.

3. The bio pellets that were produced with pine wood charcoal that underwent BM compared with HM had higher density and moisture content, and lower ash content and volatile matter due to the different particle sizes.

2 CONFLICT of INTEREST

No potential conflict of interest relevant to this article was reported.

11 ACKNOWLEDGMENT

The authors would like to thank the anonymous reviewers for their valuable comments and suggestions to improve the quality of the paper. The work was supported by Tanoto Foundation, 2021.

REFERENCES

- Afif Almu, M., Syahrul, S., Padang, Y.A. 2014. Analisa nilai kalor dan laju pembakaran pada briket campuran biji nyamplung (*Calophyllum inophyllum*) dan abu sekam padi. *Dinamika Teknik Mesin: Jurnal Keilmuan dan Terapan Teknik Mesin* 4(2): 117-122.
- Ahn, K.S., Pang, S.J., Oh, J.K. 2021. Prediction of withdrawal resistance of single screw on Korean wood products. *Journal of the Korean Wood Science and Technology* 49(1): 93-102.
- Ajimotokan, H.A., Ehindero, A.O., Ajao, K.S., Adeleke, A.A., Ikubanni, P.P., Shuaib-Babata, Y.L. 2019. Combustion characteristics of fuel briquettes made from charcoal particles and sawdust agglomerates. *Scientific African* 6: e00202.
- Ashar, M., Sahara, S., Hernawati, H. 2020. Pengaruh komposisi dan ukuran partikel terhadap kualitas briket kulit durian dan tempurung kelapa. *Jurnal Fisika dan Terapannya* 7(1): 33-43.
- Atabani, A.E., Mercimek, S.M., Arvindnarayan, S., Shobana, S., Kumar, G., Cadir, M., Al-Muhateb, A.H. 2018. Valorization of spent coffee grounds recycling as a potential alternative fuel resource in Turkey: An experimental study. *Journal of the Air & Waste Management Association* 68(3): 196-214.
- Badan Standardisasi Nasional. 2014. Pelet Kayu. SNI 8021:2014. Badan Standardisasi Nasional, Jakarta, Indonesia.
- Brunerová, A., Müller, M., Šleger, V., Ambarita, H., Valášek, P. 2018. Bio-pellet fuel from oil palm empty fruit bunches (EFB): Using European standards for quality testing. *Sustainability* 10(12): 4443.
- Brunet-Navarro, P., Jochheim, H., Kroiher, F., Muys, B. 2018. Effect of cascade use on the carbon balance of the German and European wood sectors. *Journal of Cleaner Production* 170: 137-146.
- Budiawan, L., Hendrawan, Y., Susilo, B. 2014. Pembuatan dan karakterisasi briket bioarang dengan variasi komposisi kulit kopi. *Jurnal Bioproses Komoditas Tropis* 2(2): 152-160.
- Colantoni, A., Paris, E., Bianchini, L., Ferri, S., Marcantonio, V., Carnevale, M., Palma, A., Civitarese, V., Gallucci, F. 2021. Spent coffee ground characterization, pelletization test and emissions assessment in the combustion process. *Scientific Reports* 11(1): 5119.
- Cubero-Abarca, R., Moya, R., Valaret, J., Tomazello Filho, M. 2014. Use of coffee (*Coffea arabica*) pulp for the production of briquettes and pellets for heat generation. *Ciência e Agrotecnologia* 38(5): 461-470.
- Damayanti, R., Lusiana, N., Prasetyo, J. 2017. Studi pengaruh ukuran partikel dan penambahan perekat tapioka terhadap karakteristik biopellet dari kulit coklat (*Theobroma cacao* L.) sebagai bahan bakar

- alternatif terbarukan. Teknotak: Jurnal Industri Teknologi Pertanian 11(1): 51-60.
- Fasina, O.O. 2008. Physical properties of peanut hull pellets. *Bioresource Technology* 99(5): 1259-1266.
- Fikri, E., Sartika, C. 2018. Study on the use and composition of bio-charcoal briquettes made of organic waste. *Journal of Ecological Engineering* 19(2): 81-88.
- Ghani, R.S.M., Lee, M.D. 2021. Challenges of wood modification process for plantation eucalyptus: A review of Australian setting. *Journal of the Korean Wood Science and Technology* 49(2): 191-209.
- Hadi, Y.S., Herliyana, E.N., Pari, G., Pari, R., Abdillah, I.B. 2022. Furfurylation effects on discoloration and physical-mechanical properties of wood from tropical plantation forests. *Journal of the Korean Wood Science and Technology* 50(1): 46-58.
- Han, Y., Lee, S.M. 2021. Investigation on the awareness and preference for wood to promote the value of wood: II. Awareness of wood cultural resources. *Journal of the Korean Wood Science and Technology* 49(6): 643-657.
- Hendra, D. 2012. Rekayasa pembuatan mesin pelet kayu dan pengujian hasilnya. *Jurnal Penelitian Hasil Hutan* 30(2): 144-154.
- Heo, S.J., Choi, J.W. 2018. Biofuel utilization and implications in ASEAN based on case analysis of developed countries. *Journal of the Korean Wood Science and Technology* 46(5): 577-596.
- Hwang, U.T., Bae, J., Lee, T., Hwang, S.Y., Kim, J.C., Park, J., Choi, I.G., Kwak, H.W., Hwang, S.W., Yeo, H. 2021. Analysis of carbonization behavior of hydrochar produced by hydrothermal carbonization of lignin and development of a prediction model for carbonization degree using near-infrared spectroscopy. *Journal of the Korean Wood Science and Technology* 49(3): 213-225.
- Iskandar, N., Nugroho, S., Feliyana, M.F. 2019. Uji kualitas produk briket arang tempurung kelapa berdasarkan standar mutu SNI. *Momentum* 15(2): 103-108.
- Jamilatun, S. 2008. Sifat-sifat penyalaaan dan pembakaran briket biomassa, briket batubara dan arang kayu. *Jurnal Rekayasa Proses* 2(2): 37-40.
- Jang, E.S. 2022. Experimental investigation of the sound absorption capability of wood pellets as an eco-friendly material. *Journal of the Korean Wood Science and Technology* 50(2): 126-133.
- Jeguirim, M., Limousy, L., Dutournie, P. 2014. Pyrolysis kinetics and physicochemical properties of agro-pellets produced from spent ground coffee blended with conventional biomass. *Chemical Engineering Research and Design* 92(10): 1876-1882.
- Jeoung, T.Y., Yang, S.M., Kang, S.G. 2020. Study on fuel specificity and harmful air pollutants factor of agglomerated wood charcoal. *Journal of the Korean Wood Science and Technology* 48(2): 253-266.
- Ju, Y.M., Lee, H.W., Kim, A., Jeong, H., Chea, K.S., Lee, J., Ahn, B.J., Lee, S.M. 2020. Characteristics of carbonized biomass produced in a manufacturing process of wood charcoal briquettes using an open hearth kiln. *Journal of the Korean Wood Science and Technology* 48(2): 181-195.
- Kale, J., Mula, Y.R., Iskandar, T., Abrina, S.P. 2019. Optimalisasi proses pembuatan briket arang bambu dengan menggunakan perekat organik. In: Malang, Indonesia, Prosiding Seminar Nasional Teknologi Industri, Lingkungan dan Infrastruktur, pp. 1-7.
- Kansai, N., Chaisuwan, N., Supakata, N. 2018. Carbonized briquettes as a tool for adding value to waste from rain tree (*Samanea saman*) and coffee ground/tea waste. *Engineering Journal* 22(6): 47-63.
- Kawale, H.D., Kishore, N. 2020. Comparative study on pyrolysis of *Delonix regia*, pinewood sawdust and their co-feed for plausible bio-fuels production. *Energy* 203: 117921.
- Khusna, D., Susanto, J. 2015. Pemanfaata limbah padat kopi sebagai bahan bakar alternatif dalam bentuk

- briket berbasis biomass (studi kasus di PT. Santos Jaya Abadi Instan Coffee). In: Surabaya, Indonesia, Prosiding Seminar Nasional Sains dan Teknologi Terapan III, pp. 247-260.
- Kumar, M., Xiong, X., Wan, Z., Sun, Y., Tsang, D.C.W., Gupta, J., Gao, B., Cao, X., Tang, J., Ok, Y.S. 2020. Ball milling as a mechanochemical technology for fabrication of novel biochar nanomaterials. *Biore-source Technology* 312: 123613.
- Lee, H.W., Eom, C.D. 2021. Preprocessing *Miscanthus sacchariflorus* with combination system of cone grinder and air classifier. *Journal of the Korean Wood Science and Technology* 49(4): 328-335.
- Lee, H.W., Kim, S.B. 2020. Study on the estimation of proper compression ratios for Korean domestic wood species by single pellet press. *Journal of the Korean Wood Science and Technology* 48(4): 450-457.
- Lee, J., Sarmah, A.K., Kwon, E.E. 2019. Production and Formation of Biochar. In: *Biochar from Biomass and Waste: Fundamentals and Applications*, Ed. by Ok, Y.S., Tsang, D.C.W., Bolan, N. and Novak, J.M. Elsevier, Amsterdam, Netherlands.
- Limantara, J., Tedjokoeseomo, P.E.D., Rizqy, M.T. 2019. Penggunaan ampas kopi sebagai material alternatif pada produk interior. *Jurnal Intra* 7(2): 846-849.
- Limousy, L., Jeguirim, M., Dutournié, P., Kraiem, N., Lajili, M., Said, R. 2013. Gaseous products and particulate matter emissions of biomass residential boiler fired with spent coffee grounds pellets. *Fuel* 107: 323-329.
- Lisowski, A., Olendzi, D., Świętochowski, A., Dąbrowska, M., Mieszkalski, L., Ostrowska-Ligeza, E., Stasiak, M., Klonowski, J., Piątek, M. 2019. Spent coffee grounds compaction process: Its effects on the strength properties of biofuel pellets. *Renewable Energy* 142: 173-183.
- Lyu, H., Gao, B., He, F., Ding, C., Tang, J., Crittenden, J.C. 2017. Ball-milled carbon nanomaterials for energy and environmental applications. *ACS Sustainable Chemistry and Engineering* 5(11): 9568-9585.
- Martinez, C.L.M., Sermyagina, E., de Cassia Oliveira Carneiro, A., Vakkilainen, E., Cardoso, M. 2019. Production and characterization of coffee-pine wood residue briquettes as an alternative fuel for local firing systems in Brazil. *Biomass and Bioenergy* 123: 70-77.
- Mussatto, S.I., Machado, E.M.S., Martins, S., Teixeira, J.A. 2011. Production, composition, and application of coffee and its industrial residues. *Food and Bioprocess Technology* 4(5): 661-672.
- Mustamu, S., Hermawan, D., Pari, G. 2018. Karakteristik biopellet dari limbah padat kayu putih dan gondorukem. *Jurnal Penelitian Hasil Hutan* 36(3): 191-204.
- Muzakir, M.T., Nizar, M., Yulianti, C.S. 2017. Pemanfaatan kulit buah kakao menjadi briket arang menggunakan kanji sebagai perekat. *Serambi Engineering* 2(3): 124-129.
- Naghdi, M., Taheran, M., Brar, S.K., Rouissi, T., Verma, M., Surampalli, R.Y., Valero, J.R. 2017. A green method for production of nanobiochar by ball milling-optimization and characterization. *Journal of Cleaner Production* 164: 1394-1405.
- Nandiyanto, A.B.D., Ragadhita, R., Sukmafitri, A., Bilad, M.R., Aziz, M., Yunas, J. 2020. Mechanical impact in disk mill for producing controlled rice husk particle size by changing impactor shapes and disk rotation speeds. *Sains Malaysiana* 49(12): 2927-2940.
- Oyelaran, O.A., Olorunfemi, B.J., Sanusi, O.M., Fagbemigun, A.O., Balogun, O. 2018. Investigating the performance and combustion characteristics of composite bio-coal briquette. *Journal of Materials and Engineering Structures* 5(2): 173-184.
- Park, S., Han, Y., Son, D.W. 2020a. Flame retardancy of wood products by spreading concentration and impregnation time of flame retardant. *Journal of the*

- Korean Wood Science and Technology 48(4): 417-430.
- Park, Y., Jeon, W.S., Yoon, S.M., Lee, H.M., Hwang, W.J. 2020b. Evaluation of cell-wall microstructure and anti-swelling effectiveness of heat-treated larch wood. *Journal of the Korean Wood Science and Technology* 48(6): 780-790.
- Patandung, P. 2014. Pengaruh jumlah tepung kanji pada pembuatan briket arang tempurung pala. *Jurnal Penelitian Teknologi Industri* 6(2): 95-102.
- Peudada, A., Mawardi, I., Ariefin, A. 2020. Pengaruh lubang laluan countersink dan counterbore terhadap karakteristik pellet kayu kelapa sawit dengan penambahan karbon arang tempurung. *Jurnal Mesin Sains Terapan* 4(1): 6-11.
- Prabawa, I.D.G.P., Miyono, M. 2017. Mutu biopellet dari campuran cangkang buah karet dan bambu ater (*Gigantochloa atter*). *Jurnal Riset Industri Hasil Hutan* 9(2): 99-110.
- Pratiwi, V.D. 2020. Effect of burning temperature on the quality of alternatif bio-energy from coffee waste. *Jurnal Teknik Energi Elektrik, Teknik Telekomunikasi, & Teknik Elektronika* 8(3): 615-626.
- Priyanto, A., Hantarum, H., Sudarno, S. 2018. Pengaruh variasi ukuran partikel briket terhadap kerapatan, kadar air, dan laju pembakaran pada briket kayu sengon. In: *Prosiding Seminar Nasional Sains dan Teknologi Terapan*, pp. 541-546.
- Putri, R.E., Andasuryani, A. 2017. Studi mutu briket arang dengan bahan baku limbah biomassa. *Jurnal Teknologi Pertanian Andalas* 21(2): 143-151.
- Rusdianto, A.S. 2018. Physico-chemical properties of biopellet from coffee shell. *Research Journal of Chemical and Environmental Sciences* 6(3): 40-43.
- Ruslan, R. 2020. Pengaruh ukuran partikel terhadap karakteristik briket berbasis sekam padi dan tempurung kelapa. *Jurnal Ilmu Fisika: Teori Dan Aplikasinya* 1(2): 59-65.
- Sunardi, S. Djuanda, D., Mandra, M.A.S. 2019. Characteristics of charcoal briquettes from agricultural waste with compaction pressure and particle size variation as alternative fuel. *International Energy Journal* 19(3): 139-148.
- Tongcumpou, C., Usapein, P., Tuntiwiwattanapun, N. 2019. Complete utilization of wet spent coffee grounds waste as a novel feedstock for antioxidant, biodiesel, and bio-char production. *Industrial Crops and Products* 138: 111484.
- Tun, M.M., Raclavská, H., Juchelková, D., Růžicková, J., Šafář, M., Štrbová, K., Gikas, P. 2020. Spent coffee ground as renewable energy source: Evaluation of the drying processes. *Journal of Environmental Management* 275: 111204.
- Wu, P., Wang, Z., Bolan, N.S., Wang, H., Wang, Y., Chen, W. 2021. Visualizing the development trend and research frontiers of biochar in 2020: A scientometric perspective. *Biochar* 3(4): 419-436.
- Xing, T., Mateti, S., Li, L.H., Ma, F., Du, A., Gogotsi, Y., Chen, Y. 2016. Gas protection of two-dimensional nanomaterials from high-energy impacts. *Scientific Reports* 6(1): 35532.
- Yang, I., Han, G.S., Oh, S.W. 2018. Larch pellets fabricated with coffee waste and the commercializing potential of the pellets. *Journal of the Korean Wood Science and Technology* 46(1): 48-59.

Characteristics of Bio Pellet

ORIGINALITY REPORT

18%

SIMILARITY INDEX

13%

INTERNET SOURCES

13%

PUBLICATIONS

4%

STUDENT PAPERS

PRIMARY SOURCES

1	coek.info Internet Source	1%
2	www.chikd.org Internet Source	1%
3	idoc.pub Internet Source	1%
4	eprints.unm.ac.id Internet Source	1%
5	mro.massey.ac.nz Internet Source	1%
6	www.iieta.org Internet Source	1%
7	Yusuf Sudo Hadi, Deded Sarip Nawawi, Imam Busyra Abdillah, Gustan Pari, Rohmah Pari. "Evaluation of Discoloration and Subterranean Termite Resistance of Four Furfurylated Tropical Wood Species after One-Year Outdoor Exposure", Forests, 2021 Publication	1%
8	etd.auburn.edu Internet Source	1%

9	www.koreascience.or.kr Internet Source	1 %
10	Dina Asmaul Chusniyah, Reno Pratiwi, Benyamin, Suliestiyah. "The Development of Sustainable Energy Briquettes Using Coconut Dregs Charcoal and Tapioca Flour as Adhesives", IOP Conference Series: Earth and Environmental Science, 2022 Publication	<1 %
11	scientiairanica.sharif.edu Internet Source	<1 %
12	Romauli Tampubolon, Evi Sribudiani, Sonia Somadona, Yusup Amin, Sukma Surya Kusumah. "Characteristics of Particleboard from Sorghum and Nypa Fruit Skin Fiber Bonded with Citric Acid-Sucrose Adhesive", Jurnal Sylva Lestari, 2022 Publication	<1 %
13	www.nature.com Internet Source	<1 %
14	Honghong Lyu, Zebin Yu, Bin Gao, Feng He, Jun Huang, Jingchun Tang, Boxiong Shen. "Ball-milled biochar for alternative carbon electrode", Environmental Science and Pollution Research, 2019 Publication	<1 %
15	core.ac.uk Internet Source	<1 %

- | | | |
|----|--|------|
| 16 | mdpi-res.com
Internet Source | <1 % |
| 17 | unsworks.unsw.edu.au
Internet Source | <1 % |
| 18 | www.atlantis-press.com
Internet Source | <1 % |
| 19 | Submitted to University of the West Indies
Student Paper | <1 % |
| 20 | Simon Kizito, Joseph Jjagwe, Bruno Ssewaya, Lillian Nekesa, Peter Tumutegyereize, Ahamada Zziwa, Allan John Komakech. "Biofuel characteristics of non-charred briquettes from dried fecal sludge blended with food market waste: Suggesting a waste-to-biofuel enterprise as a win-win strategy to solve energy and sanitation problems in slums settlements", Waste Management, 2021
Publication | <1 % |
| 21 | Submitted to Waljat College of Applied Sciences
Student Paper | <1 % |
| 22 | springerplus.springeropen.com
Internet Source | <1 % |
| 23 | Emmanuel Ogo Onche, Oluwaseun Kehinde Oyewole, Salifu Tahiru Azeko, John David Obayemi, Nima Rahbar, Winston Oluwole Soboyejo. "Compressive Deformation and | <1 % |

the Failure of Functionally Graded Bamboo Structures: Implications for Bioinspired Design", Elsevier BV, 2022

Publication

24 portal.koreascience.or.kr <1 %
Internet Source

25 S Wibowo, K Arief, T K Waluyo. <1 %
"Characteristics of wood pellets from over-dry sawdust waste", IOP Conference Series: Earth and Environmental Science, 2021
Publication

26 Submitted to Universitas Brawijaya <1 %
Student Paper

27 www.its.ac.id <1 %
Internet Source

28 Submitted to Deptford Township High School <1 %
Student Paper

29 Submitted to Georgia Institute of Technology <1 %
Student Paper

30 Taek Yong JEOUNG, Seung Min YANG, Seog Goo KANG. "Study on Fuel Specificity and Harmful Air Pollutants Factor of Agglomerated Wood Charcoal", Journal of the Korean Wood Science and Technology, 2020
Publication

31

Internet Source

<1 %

32

Hyoung-Woo LEE, Soon-Bae KIM. "Study on the Estimation of Proper Compression Ratios for Korean Domestic Wood Species by Single Pellet Press", Journal of the Korean Wood Science and Technology, 2020

Publication

<1 %

33

Tyalif Gibran Takapaha, Arif Nindyo Kisworo, Rifa Rafi'atu Syabani Wihansah. "Economic Analysis and Burning Time of Bioarang Briquettes Based on Beef Cattle Feces", JURNAL TRITON, 2022

Publication

<1 %

34

ir-library.mmarau.ac.ke:8080

Internet Source

<1 %

35

Ji-Sook Lee. "Anti-inflammatory Effects of Neuregulin-1 via the Downregulation of IL-6, IL-8, and MCP-1 Secretion", Biomedical Science Letters, 2022

Publication

<1 %

36

Submitted to University of Leeds

Student Paper

<1 %

37

Yusuf Sudo Hadi, Dede Hermawan, Imam Busyra Abdillah, Mahdi Mubarak, Wa Ode Muliastuty Arsyad, Rohmah Pari. "Polystyrene-Impregnated Glulam Resistance to Subterranean Termite Attacks in a Laboratory Test", Polymers, 2022

<1 %

38 academicjournals.org <1 %
Internet Source

39 lutpub.lut.fi <1 %
Internet Source

40 www.iqjfmme.com <1 %
Internet Source

41 Andi Detti Yuniarti, Kidung Tirtayasa P.,
Suhasman, Ira Taskirawati, Agussalim,
Musrizal Muin. "Modified Densification
Process for Increasing Strength Properties
of Pine and Gmelina Wood from Community
Forests", Journal of the Korean Wood
Science and Technology, 2019
Publication

42 K Karelius, M Dirgantara, N Rumbang, N
Kristian, F Purwanto. "Increasing product
quality of torrefied palm kernel shell batch
model with internal surface area
modification", IOP Conference Series:
Materials Science and Engineering, 2021
Publication

43 N J Wistara, S Bahri, G Pari. "Biopellet
properties of agathis wood fortified with its
peeled-off bark", IOP Conference Series:
Materials Science and Engineering, 2020
Publication

44 Sunday Yusuf Kpalo, Mohamad Faiz
Zainuddin, Latifah Abd Manaf, Ahmad <1 %

Muhaimin Roslan. "Production and Characterization of Hybrid Briquettes from Corncobs and Oil Palm Trunk Bark under a Low Pressure Densification Technique", Sustainability, 2020

Publication

45

link.springer.com

Internet Source

<1 %

46

www.coursehero.com

Internet Source

<1 %

47

www.ijcmas.com

Internet Source

<1 %

48

Benjamin Salomon Diboma, Victor Hugo Atiotsia, Louis Colins Che, Philippe Blaise Essomba, Bill Vaneck Bot, Jean Gaston Tamba. "Gasification of charcoal derived from tropical wood residues in an updraft fixed bed reactor", Bioresource Technology Reports, 2022

Publication

<1 %

49

Kranti Navare, Bart Muys, Karl C. Vrancken, Karel Van Acker. "Circular economy monitoring – How to make it apt for biological cycles?", Resources, Conservation and Recycling, 2021

Publication

<1 %

50

Xiaoyun Xu, Yulin Zheng, Bin Gao, Xinde Cao. "N-doped biochar synthesized by a facile ball-milling method for enhanced

<1 %

sorption of CO₂ and reactive red", Chemical Engineering Journal, 2019

Publication

-
- | | | |
|----|--|------|
| 51 | Zhenyuan Li, Zhidong Pan, Yanmin Wang. "Mechanochemical preparation of ternary polyethyleneimine modified magnetic illite/smectite nanocomposite for removal of Cr(VI) in aqueous solution", Applied Clay Science, 2020
Publication | <1 % |
| 52 | bioresources.cnr.ncsu.edu
Internet Source | <1 % |
| 53 | repositoriotec.tec.ac.cr
Internet Source | <1 % |
| 54 | repository.umi.ac.id
Internet Source | <1 % |
| 55 | sitem.herts.ac.uk
Internet Source | <1 % |
| 56 | www.aps.or.id
Internet Source | <1 % |
| 57 | www.coresta.org
Internet Source | <1 % |
| 58 | I Gunawan, A Damayanti, N Muharyani, Murgunadi, Y Amin, G Pari. " Characteristics of wood pellet from 5 years old JPP teak (L.f.) ", IOP Conference Series: Earth and Environmental Science, 2020
Publication | <1 % |
-

59

Kevin Johnson, Yang Liu, Mingming Lu. "A Review of Recent Advances in Spent Coffee Grounds Upcycle Technologies and Practices", *Frontiers in Chemical Engineering*, 2022

Publication

<1 %

60

Nur Syahirah Kamal Baharin, Vidya Cundasari Koesoemadinata, Shunsuke Nakamura, Nadia Farhana Azman et al. "Production of Bio-Coke from spent mushroom substrate for a sustainable solid fuel", *Biomass Conversion and Biorefinery*, 2020

Publication

<1 %

61

Tej Pratap, Abhishek Kumar Chaubey, Manvendra Patel, Todd E. Mlsna, Charles U. Pittman, Dinesh Mohan. "Nanobiochar for aqueous contaminant removal", *Elsevier BV*, 2022

Publication

<1 %

62

Ajith Kumar TT, Neeraj Mech, S.T. Ramesh, R. Gandhimathi. "Evaluation of composite briquettes from dry leaves in energy applications for agrarian communities in India", *Journal of Cleaner Production*, 2022

Publication

<1 %

63

Duk-Gam Woo, Sang Hyeon Kim, Tae Han Kim. "Solid Fuel Characteristics of Pellets Comprising Spent Coffee Grounds and Wood Powder", *Energies*, 2021

<1 %

64 Francisco J. Lopez-Tenllado, Ingrid Lopes Motta, Josephine M. Hill. "Modification of biochar with high-energy ball milling: Development of porosity and surface acid functional groups", Bioresource Technology Reports, 2021
Publication <1 %

65 journal.upgris.ac.id
Internet Source <1 %

Exclude quotes On

Exclude matches < 5 words

Exclude bibliography On